


Ho₁₁Ge₁₀ Structure: A10B11_tI84_139_dehim_eh2n-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/HN10>

https://aflow.org/prototype-encyclopedia/A10B11_tI84_139_dehim_eh2n-001

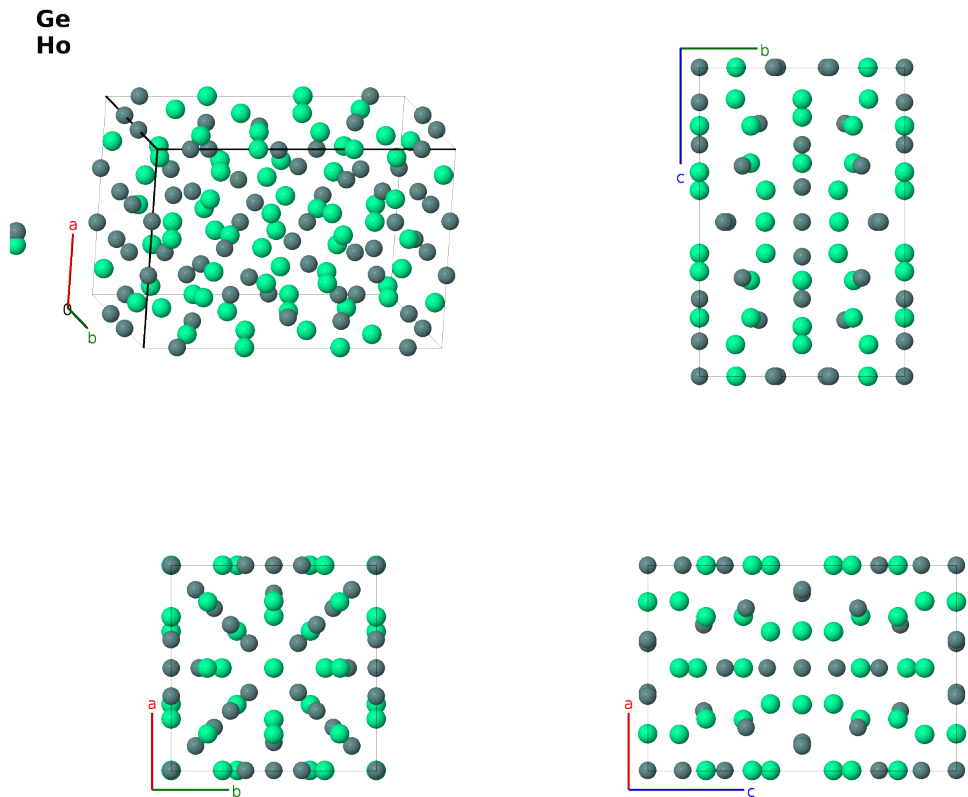

Prototype	Ge ₁₀ Ho ₁₁
AFLOW prototype label	A10B11_tI84_139_dehim_eh2n-001
ICSD	43052
CCDC	1612645
Pearson symbol	tI84
Space group number	139
Space group symbol	<i>I4/mmm</i>
AFLOW prototype command	<code>aflow --proto=A10B11_tI84_139_dehim_eh2n-001</code> <code>--params=a, c/a, z₂, z₃, x₄, x₅, x₆, x₇, z₇, y₈, z₈, y₉, z₉</code>


Other compounds with this structure

Ba₁₁Bi₁₀, Ca₁₁Bi₁₀, Ca₁₁Sb₁₀, Ce₁₁Sn₁₀, Dy₁₁Sn₁₀, Er₁₁Ge₁₀, Er₁₁Sn₁₀, Eu₁₁Bi₁₀, Eu₁₁Sb₁₀, Gd₁₁Sn₁₀, Hf₁₁Ga₁₀, Ho₁₁Ge₁₀, Ho₁₁Sn₁₀, La₁₁Sn₁₀, Lu₁₁Ge₁₀, Nd₁₁Sn₁₀, Pr₁₁Pb₁₀, Sc₁₁Ge₁₀, Sr₁₁Bi₁₀, Sr₁₁Sb₁₀, Tb₁₁Ge₁₀, Tb₁₁Sn₁₀, Tm₁₁Ge₁₀, Tm₁₁Sn₁₀, Yb₁₁Bi₁₀, Yb₁₁Ge₁₀, Yb₁₁Sb₁₀

- This is the binary form of the structure. Tb₁₁Si₄In₆ and Sc₁₁Al₂Ge₈ are ternary forms.

Body-centered Tetragonal primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= -\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} - \frac{1}{2}c \hat{\mathbf{z}} \end{aligned}$$

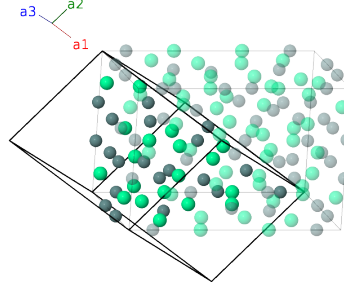

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{3}{4} \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4d)	Ge I
$\mathbf{B}_2$	$= \frac{1}{4} \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4d)	Ge I
$\mathbf{B}_3$	$= z_2 \mathbf{a}_1 + z_2 \mathbf{a}_2$	$=$	$cz_2 \hat{\mathbf{z}}$	(4e)	Ge II
$\mathbf{B}_4$	$= -z_2 \mathbf{a}_1 - z_2 \mathbf{a}_2$	$=$	$-cz_2 \hat{\mathbf{z}}$	(4e)	Ge II
$\mathbf{B}_5$	$= z_3 \mathbf{a}_1 + z_3 \mathbf{a}_2$	$=$	$cz_3 \hat{\mathbf{z}}$	(4e)	Ho I
$\mathbf{B}_6$	$= -z_3 \mathbf{a}_1 - z_3 \mathbf{a}_2$	$=$	$-cz_3 \hat{\mathbf{z}}$	(4e)	Ho I
$\mathbf{B}_7$	$= x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + 2x_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}}$	(8h)	Ge III
$\mathbf{B}_8$	$= -x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - 2x_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}}$	(8h)	Ge III
$\mathbf{B}_9$	$= x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2$	$=$	$-ax_4 \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}}$	(8h)	Ge III
$\mathbf{B}_{10}$	$= -x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2$	$=$	$ax_4 \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}}$	(8h)	Ge III
$\mathbf{B}_{11}$	$= x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + 2x_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} + ax_5 \hat{\mathbf{y}}$	(8h)	Ho II
$\mathbf{B}_{12}$	$= -x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 - 2x_5 \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} - ax_5 \hat{\mathbf{y}}$	(8h)	Ho II
$\mathbf{B}_{13}$	$= x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2$	$=$	$-ax_5 \hat{\mathbf{x}} + ax_5 \hat{\mathbf{y}}$	(8h)	Ho II
$\mathbf{B}_{14}$	$= -x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2$	$=$	$ax_5 \hat{\mathbf{x}} - ax_5 \hat{\mathbf{y}}$	(8h)	Ho II
$\mathbf{B}_{15}$	$= x_6 \mathbf{a}_2 + x_6 \mathbf{a}_3$	$=$	$ax_6 \hat{\mathbf{x}}$	(8i)	Ge IV
$\mathbf{B}_{16}$	$= -x_6 \mathbf{a}_2 - x_6 \mathbf{a}_3$	$=$	$-ax_6 \hat{\mathbf{x}}$	(8i)	Ge IV
$\mathbf{B}_{17}$	$= x_6 \mathbf{a}_1 + x_6 \mathbf{a}_3$	$=$	$ax_6 \hat{\mathbf{y}}$	(8i)	Ge IV
$\mathbf{B}_{18}$	$= -x_6 \mathbf{a}_1 - x_6 \mathbf{a}_3$	$=$	$-ax_6 \hat{\mathbf{y}}$	(8i)	Ge IV
$\mathbf{B}_{19}$	$= (x_7 + z_7) \mathbf{a}_1 + (x_7 + z_7) \mathbf{a}_2 + 2x_7 \mathbf{a}_3$	$=$	$ax_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
$\mathbf{B}_{20}$	$= -(x_7 - z_7) \mathbf{a}_1 - (x_7 - z_7) \mathbf{a}_2 - 2x_7 \mathbf{a}_3$	$=$	$-ax_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(16m)	Ge V

$\mathbf{B}_{21}$	$=$	$(x_7 + z_7) \mathbf{a}_1 - (x_7 - z_7) \mathbf{a}_2$	$=$	$-ax_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
$\mathbf{B}_{22}$	$=$	$-(x_7 - z_7) \mathbf{a}_1 + (x_7 + z_7) \mathbf{a}_2$	$=$	$ax_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
$\mathbf{B}_{23}$	$=$	$(x_7 - z_7) \mathbf{a}_1 - (x_7 + z_7) \mathbf{a}_2$	$=$	$-ax_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
$\mathbf{B}_{24}$	$=$	$-(x_7 + z_7) \mathbf{a}_1 + (x_7 - z_7) \mathbf{a}_2$	$=$	$ax_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
$\mathbf{B}_{25}$	$=$	$(x_7 - z_7) \mathbf{a}_1 + (x_7 - z_7) \mathbf{a}_2 +$ $2x_7 \mathbf{a}_3$	$=$	$ax_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
$\mathbf{B}_{26}$	$=$	$-(x_7 + z_7) \mathbf{a}_1 - (x_7 + z_7) \mathbf{a}_2 -$ $2x_7 \mathbf{a}_3$	$=$	$-ax_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$	(16m)	Ge V
$\mathbf{B}_{27}$	$=$	$(y_8 + z_8) \mathbf{a}_1 + z_8 \mathbf{a}_2 + y_8 \mathbf{a}_3$	$=$	$ay_8 \hat{\mathbf{y}} + cz_8 \hat{\mathbf{z}}$	(16n)	Ho III
$\mathbf{B}_{28}$	$=$	$-(y_8 - z_8) \mathbf{a}_1 + z_8 \mathbf{a}_2 - y_8 \mathbf{a}_3$	$=$	$-ay_8 \hat{\mathbf{y}} + cz_8 \hat{\mathbf{z}}$	(16n)	Ho III
$\mathbf{B}_{29}$	$=$	$z_8 \mathbf{a}_1 - (y_8 - z_8) \mathbf{a}_2 - y_8 \mathbf{a}_3$	$=$	$-ay_8 \hat{\mathbf{x}} + cz_8 \hat{\mathbf{z}}$	(16n)	Ho III
$\mathbf{B}_{30}$	$=$	$z_8 \mathbf{a}_1 + (y_8 + z_8) \mathbf{a}_2 + y_8 \mathbf{a}_3$	$=$	$ay_8 \hat{\mathbf{x}} + cz_8 \hat{\mathbf{z}}$	(16n)	Ho III
$\mathbf{B}_{31}$	$=$	$(y_8 - z_8) \mathbf{a}_1 - z_8 \mathbf{a}_2 + y_8 \mathbf{a}_3$	$=$	$ay_8 \hat{\mathbf{y}} - cz_8 \hat{\mathbf{z}}$	(16n)	Ho III
$\mathbf{B}_{32}$	$=$	$-(y_8 + z_8) \mathbf{a}_1 - z_8 \mathbf{a}_2 - y_8 \mathbf{a}_3$	$=$	$-ay_8 \hat{\mathbf{y}} - cz_8 \hat{\mathbf{z}}$	(16n)	Ho III
$\mathbf{B}_{33}$	$=$	$-z_8 \mathbf{a}_1 + (y_8 - z_8) \mathbf{a}_2 + y_8 \mathbf{a}_3$	$=$	$ay_8 \hat{\mathbf{x}} - cz_8 \hat{\mathbf{z}}$	(16n)	Ho III
$\mathbf{B}_{34}$	$=$	$-z_8 \mathbf{a}_1 - (y_8 + z_8) \mathbf{a}_2 - y_8 \mathbf{a}_3$	$=$	$-ay_8 \hat{\mathbf{x}} - cz_8 \hat{\mathbf{z}}$	(16n)	Ho III
$\mathbf{B}_{35}$	$=$	$(y_9 + z_9) \mathbf{a}_1 + z_9 \mathbf{a}_2 + y_9 \mathbf{a}_3$	$=$	$ay_9 \hat{\mathbf{y}} + cz_9 \hat{\mathbf{z}}$	(16n)	Ho IV
$\mathbf{B}_{36}$	$=$	$-(y_9 - z_9) \mathbf{a}_1 + z_9 \mathbf{a}_2 - y_9 \mathbf{a}_3$	$=$	$-ay_9 \hat{\mathbf{y}} + cz_9 \hat{\mathbf{z}}$	(16n)	Ho IV
$\mathbf{B}_{37}$	$=$	$z_9 \mathbf{a}_1 - (y_9 - z_9) \mathbf{a}_2 - y_9 \mathbf{a}_3$	$=$	$-ay_9 \hat{\mathbf{x}} + cz_9 \hat{\mathbf{z}}$	(16n)	Ho IV
$\mathbf{B}_{38}$	$=$	$z_9 \mathbf{a}_1 + (y_9 + z_9) \mathbf{a}_2 + y_9 \mathbf{a}_3$	$=$	$ay_9 \hat{\mathbf{x}} + cz_9 \hat{\mathbf{z}}$	(16n)	Ho IV
$\mathbf{B}_{39}$	$=$	$(y_9 - z_9) \mathbf{a}_1 - z_9 \mathbf{a}_2 + y_9 \mathbf{a}_3$	$=$	$ay_9 \hat{\mathbf{y}} - cz_9 \hat{\mathbf{z}}$	(16n)	Ho IV
$\mathbf{B}_{40}$	$=$	$-(y_9 + z_9) \mathbf{a}_1 - z_9 \mathbf{a}_2 - y_9 \mathbf{a}_3$	$=$	$-ay_9 \hat{\mathbf{y}} - cz_9 \hat{\mathbf{z}}$	(16n)	Ho IV
$\mathbf{B}_{41}$	$=$	$-z_9 \mathbf{a}_1 + (y_9 - z_9) \mathbf{a}_2 + y_9 \mathbf{a}_3$	$=$	$ay_9 \hat{\mathbf{x}} - cz_9 \hat{\mathbf{z}}$	(16n)	Ho IV
$\mathbf{B}_{42}$	$=$	$-z_9 \mathbf{a}_1 - (y_9 + z_9) \mathbf{a}_2 - y_9 \mathbf{a}_3$	$=$	$-ay_9 \hat{\mathbf{x}} - cz_9 \hat{\mathbf{z}}$	(16n)	Ho IV

References

- [1] G. S. Smith, Q. Johnson, and A. G. Tharp, *The Crystal Structure of $\text{Ho}_{11}\text{Ga}_{10}$* , *Acta Cryst.* **23**, 640–644 (1967), doi:10.1107/S0365110X67003329.

Found in

- [1] A. Rehr and S. M. Kauzlarich, *$\text{Sr}_{11}\text{Sb}_{10}$* , *Acta Crystallogr. Sect. C* **50**, 1859–1861 (1994), doi:10.1107/S0108270194003951.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, *Comput. Mater. Sci.* **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.