

W₃O₁₀ (WO₃ · $\frac{1}{3}$ H₂O) Structure: A10B3_oF52_42_2abce_ab-001


This structure previously used the label(s) **A10B3_oF52_42_2abce_ab**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/TH7F>

https://aflow.org/prototype-encyclopedia/A10B3_oF52_42_2abce_ab-001

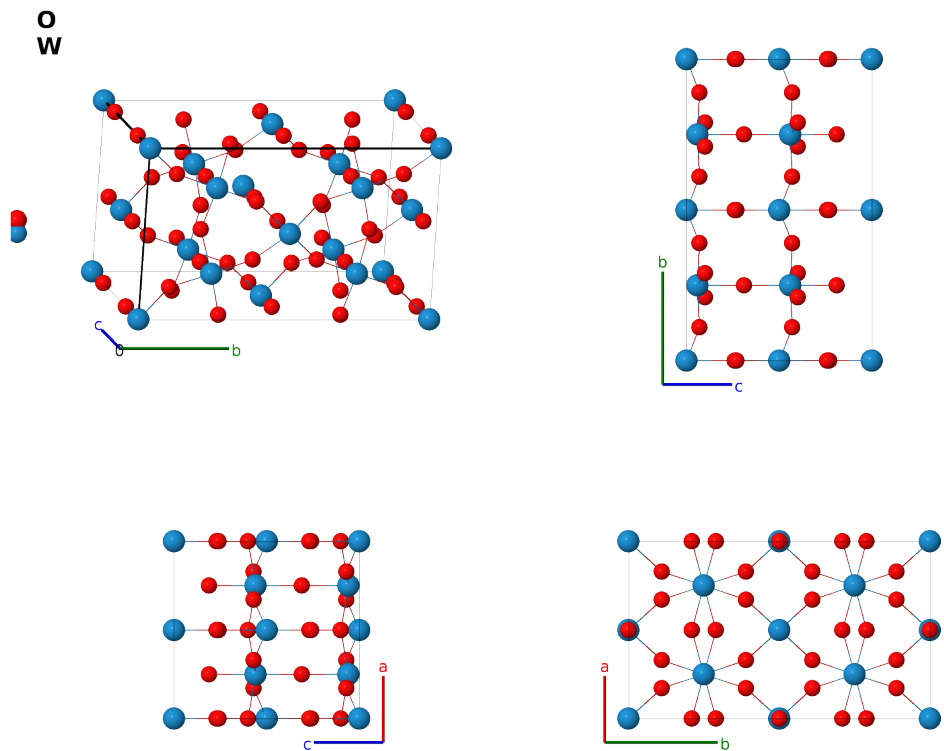


Prototype	O ₁₀ W ₃
AFLOW prototype label	A10B3_oF52_42_2abce_ab-001
ICSD	15514
CCDC	1596256
Pearson symbol	oF52
Space group number	42
Space group symbol	<i>Fmm</i> 2
AFLOW prototype command	<code>aflow --proto=A10B3_oF52_42_2abce_ab-001</code> <code>--params=a, b/a, c/a, z₁, z₂, z₃, z₄, z₅, y₆, z₆, x₇, y₇, z₇</code>

- The designation of this structure is somewhat confusing. (Gerand, 1981) call this structure $\text{WO}_3 \cdot \frac{1}{3}\text{H}_2\text{O}$, more properly written as $\text{W}_3\text{O}_9 \cdot \text{H}_2\text{O}$, but they do not give the positions of the hydrogen atoms, which are presumably associated with the O-V [O(2) in (Gerand, 1981)] atoms. Without further guidance we have left the hydrogens out of this study.

Face-centered Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}b\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}c\hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}b\hat{\mathbf{y}}\end{aligned}$$

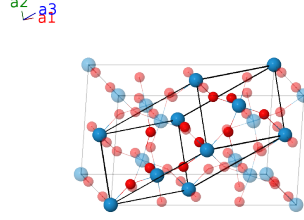

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= z_1 \mathbf{a}_1 + z_1 \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$cz_1 \hat{\mathbf{z}}$	(4a)	O I
$\mathbf{B}_2$	$= z_2 \mathbf{a}_1 + z_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$cz_2 \hat{\mathbf{z}}$	(4a)	O II
$\mathbf{B}_3$	$= z_3 \mathbf{a}_1 + z_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$cz_3 \hat{\mathbf{z}}$	(4a)	W I
$\mathbf{B}_4$	$= z_4 \mathbf{a}_1 + z_4 \mathbf{a}_2 - \left(z_4 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}b\hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(8b)	O III
$\mathbf{B}_5$	$= \left(z_4 + \frac{1}{2}\right) \mathbf{a}_1 + \left(z_4 + \frac{1}{2}\right) \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}b\hat{\mathbf{y}} + c\left(z_4 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8b)	O III
$\mathbf{B}_6$	$= z_5 \mathbf{a}_1 + z_5 \mathbf{a}_2 - \left(z_5 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}b\hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(8b)	W II
$\mathbf{B}_7$	$= \left(z_5 + \frac{1}{2}\right) \mathbf{a}_1 + \left(z_5 + \frac{1}{2}\right) \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}b\hat{\mathbf{y}} + c\left(z_5 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8b)	W II
$\mathbf{B}_8$	$= (y_6 + z_6) \mathbf{a}_1 - (y_6 - z_6) \mathbf{a}_2 + (y_6 - z_6) \mathbf{a}_3$	$=$	$by_6 \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}}$	(8c)	O IV
$\mathbf{B}_9$	$= -(y_6 - z_6) \mathbf{a}_1 + (y_6 + z_6) \mathbf{a}_2 - (y_6 + z_6) \mathbf{a}_3$	$=$	$-by_6 \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}}$	(8c)	O IV
$\mathbf{B}_{10}$	$= (-x_7 + y_7 + z_7) \mathbf{a}_1 + (x_7 - y_7 + z_7) \mathbf{a}_2 + (x_7 + y_7 - z_7) \mathbf{a}_3$	$=$	$ax_7 \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(16e)	O V
$\mathbf{B}_{11}$	$= (x_7 - y_7 + z_7) \mathbf{a}_1 + (-x_7 + y_7 + z_7) \mathbf{a}_2 - (x_7 + y_7 + z_7) \mathbf{a}_3$	$=$	$-ax_7 \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(16e)	O V
$\mathbf{B}_{12}$	$= -(x_7 + y_7 - z_7) \mathbf{a}_1 + (x_7 + y_7 + z_7) \mathbf{a}_2 + (x_7 - y_7 - z_7) \mathbf{a}_3$	$=$	$ax_7 \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(16e)	O V
$\mathbf{B}_{13}$	$= (x_7 + y_7 + z_7) \mathbf{a}_1 - (x_7 + y_7 - z_7) \mathbf{a}_2 - (x_7 - y_7 + z_7) \mathbf{a}_3$	$=$	$-ax_7 \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(16e)	O V

References

- [1] B. Gerand, G. Nowogrocki, and M. Figlarz, *A new tungsten trioxide hydrate, $\text{WO}_3 \cdot \frac{1}{3}\text{H}_2\text{O}$: Preparation, characterization, and crystallographic study*, J. Solid State Chem. **38**, 312–320 (1981), doi:10.1016/0022-4596(81)90062-1.

Found in

- [1] P. Villars and K. Cenzual, *Pearson's Crystal Data – Crystal Structure Database for Inorganic Compounds* (2013). ASM International.

First cited in

D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043