

Au₁₁Mn₃ Structure:


A11B3_mC28_12_a5i_ci-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/J58A>

https://aflow.org/prototype-encyclopedia/A11B3_mC28_12_a5i_ci-001

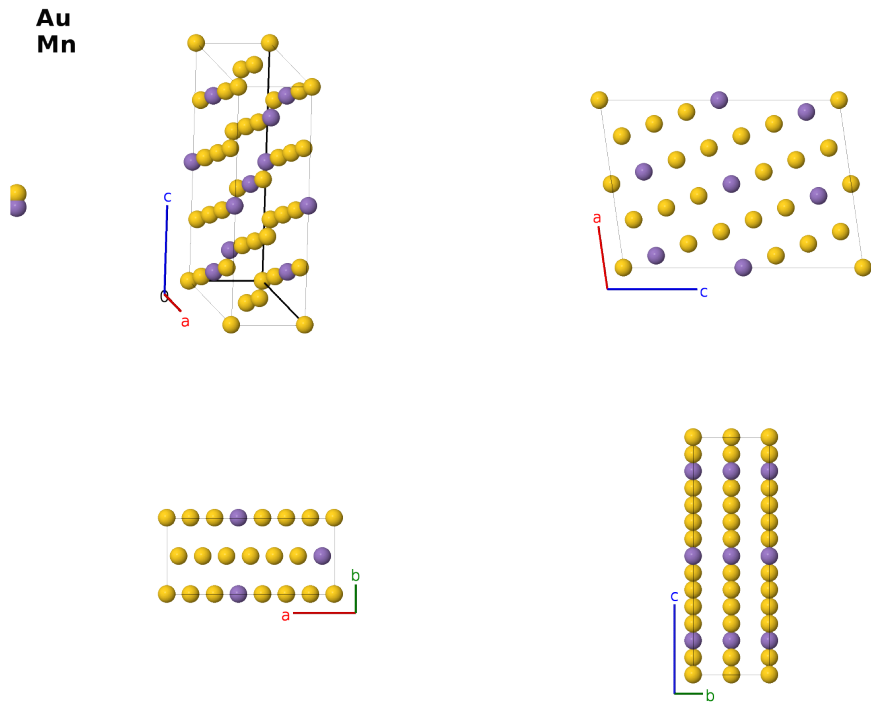


Prototype	Au ₁₁ Mn ₃
AFLOW prototype label	A11B3_mC28_12_a5i_ci-001
Pearson symbol	mC28
Space group number	12
Space group symbol	$C2/m$
AFLOW prototype command	<pre>aflow --proto=A11B3_mC28_12_a5i_ci-001 --params=a,b/a,c/a,β,x₃,z₃,x₄,z₄,x₅,z₅,x₆,z₆,x₇,z₇,x₈,z₈</pre>

- (Hiraga, 1982) give the structure in setting $P2_1/b$ of space group #14. There seems to be a misprint in Table 1 of this paper: the z -coordinate of the final gold atom is given as $1/7$. If we use this value, many of the Au-Au atomic distances are under $2\text{\AA}$, much too small for the Au-Mn system. (Villars, 2016) uses $z = 1/2$ instead. As this gives a reasonable structure, we follow their lead. This changes the space group from $P2_1/c$ to $C2/m$ #12, so we place the structure in space group #12.

Base-centered Monoclinic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}\end{aligned}$$

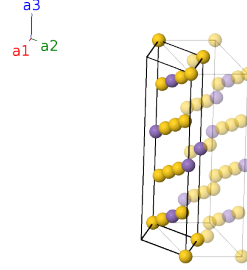

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	0	$=$	0	(2a)	Au I
$\mathbf{B}_2$	$\frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}c \cos \beta \hat{\mathbf{x}} + \frac{1}{2}c \sin \beta \hat{\mathbf{z}}$	(2c)	Mn I
$\mathbf{B}_3$	$x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(4i)	Au II
$\mathbf{B}_4$	$-x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(4i)	Au II
$\mathbf{B}_5$	$x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(4i)	Au III
$\mathbf{B}_6$	$-x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(4i)	Au III
$\mathbf{B}_7$	$x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(4i)	Au IV
$\mathbf{B}_8$	$-x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - cz_5 \sin \beta \hat{\mathbf{z}}$	(4i)	Au IV
$\mathbf{B}_9$	$x_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + cz_6 \sin \beta \hat{\mathbf{z}}$	(4i)	Au V
$\mathbf{B}_{10}$	$-x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$-(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - cz_6 \sin \beta \hat{\mathbf{z}}$	(4i)	Au V
$\mathbf{B}_{11}$	$x_7 \mathbf{a}_1 + x_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$	$=$	$(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} + cz_7 \sin \beta \hat{\mathbf{z}}$	(4i)	Au VI
$\mathbf{B}_{12}$	$-x_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 - z_7 \mathbf{a}_3$	$=$	$-(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} - cz_7 \sin \beta \hat{\mathbf{z}}$	(4i)	Au VI
$\mathbf{B}_{13}$	$x_8 \mathbf{a}_1 + x_8 \mathbf{a}_2 + z_8 \mathbf{a}_3$	$=$	$(ax_8 + cz_8 \cos \beta) \hat{\mathbf{x}} + cz_8 \sin \beta \hat{\mathbf{z}}$	(4i)	Mn II
$\mathbf{B}_{14}$	$-x_8 \mathbf{a}_1 - x_8 \mathbf{a}_2 - z_8 \mathbf{a}_3$	$=$	$-(ax_8 + cz_8 \cos \beta) \hat{\mathbf{x}} - cz_8 \sin \beta \hat{\mathbf{z}}$	(4i)	Mn II

References

- [1] K. Hiraga, M. Hirabayashi, O. Terasaki, and D. Watanabe, *One-dimensional antiphase structure of $\text{Au}_{22}\text{Mn}_6$ studied by high-voltage, high-resolution electron microscopy*, Acta Crystallogr. Sect. A **38** (1982), doi:10.1107/S0567739482000576.
- [2] P. Villars, ed., *PAULING FILE in: Inorganic Solid Phases, SpringerMaterials (online database)* (Springer Materials, 2016), chap. $\text{Au}_{22}\text{Mn}_6$ ($\text{Au}_{11}\text{Mn}_3$) Crystal Structure.

Found in

- [1] P. Villars, H. Okamoto, and K. Cenzual, eds., *ASM Alloy Phase Diagram Database* (ASM International, 2018), chap. Gold-Manganese Binary Phase Diagram (1990 Massalski T.B.). Copyright ©2006-2018 ASM International.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.