

Mn₁₂Th (*D*2_b) Structure: A12B_tI26_139_fij_a-001


This structure previously used the label(s) **A12B_tI26_139_fij_a**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/AJGV>

https://aflow.org/prototype-encyclopedia/A12B_tI26_139_fij_a-001

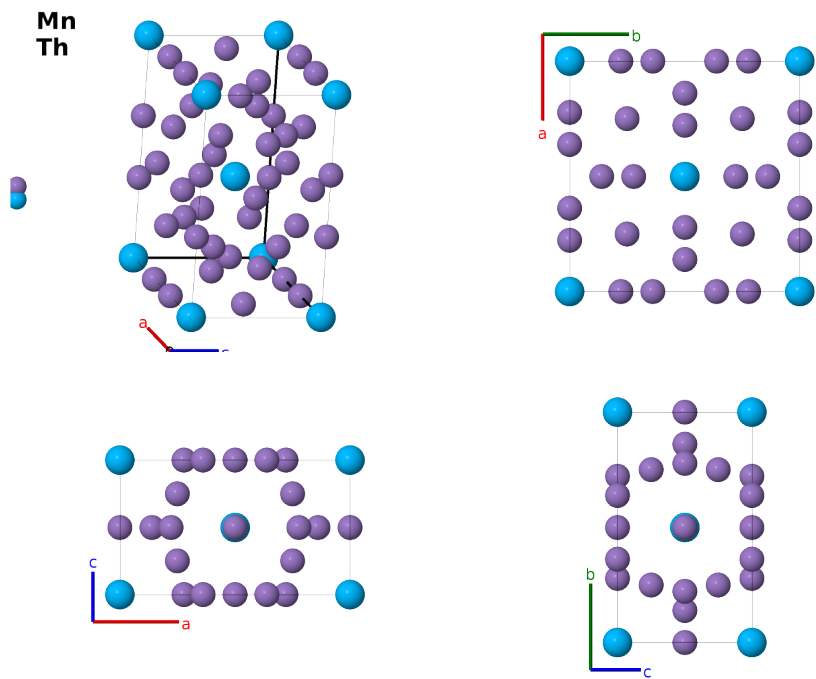


Prototype	Mn ₁₂ Th
AFLOW prototype label	A12B_tI26_139_fij_a-001
<i>Strukturbericht</i> designation	<i>D</i> 2 _b
ICSD	104986
CCDC	1662885
Pearson symbol	tI26
Space group number	139
Space group symbol	<i>I</i> 4/ <i>mmm</i>
AFLOW prototype command	<code>aflow --proto=A12B_tI26_139_fij_a-001 --params=a, c/a, x₃, x₄</code>

Other compounds with this structure

Be₁₂Ag, Be₁₂Co, Be₁₂Cr, Be₁₂Fe, Be₁₂Mn, Be₁₂Mo, Be₁₂Nb, Be₁₂Pd, Be₁₂Pt, Be₁₂Th, Be₁₂Ti, Be₁₂V, Be₁₂W, Mg₁₂Ce, Mg₁₂Nd, Mg₁₂Pr, Mn₁₂Y, Al₈Cr₄Er, Al₈Cu₄Ce, Al₈Mn₄Ce, Mn₈Fe₄, Fe₇Mn₅

Body-centered Tetragonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= -\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} - \frac{1}{2}c\hat{\mathbf{z}}\end{aligned}$$

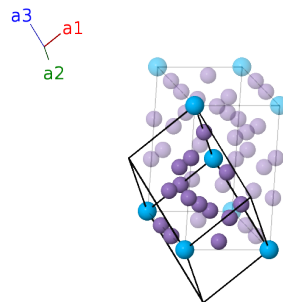

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	0	$=$	0	(2a)	Th I
$\mathbf{B}_2$	$\frac{1}{2}\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{y}} + \frac{1}{4}c\hat{\mathbf{z}}$	(8f)	Mn I
$\mathbf{B}_3$	$\frac{1}{2}\mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{y}} - \frac{1}{4}c\hat{\mathbf{z}}$	(8f)	Mn I
$\mathbf{B}_4$	$\frac{1}{2}\mathbf{a}_1$	$=$	$-\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{y}} + \frac{1}{4}c\hat{\mathbf{z}}$	(8f)	Mn I
$\mathbf{B}_5$	$\frac{1}{2}\mathbf{a}_2$	$=$	$\frac{1}{4}a\hat{\mathbf{x}} - \frac{1}{4}a\hat{\mathbf{y}} + \frac{1}{4}c\hat{\mathbf{z}}$	(8f)	Mn I
$\mathbf{B}_6$	$x_3\mathbf{a}_2 + x_3\mathbf{a}_3$	$=$	$ax_3\hat{\mathbf{x}}$	(8i)	Mn II
$\mathbf{B}_7$	$-x_3\mathbf{a}_2 - x_3\mathbf{a}_3$	$=$	$-ax_3\hat{\mathbf{x}}$	(8i)	Mn II
$\mathbf{B}_8$	$x_3\mathbf{a}_1 + x_3\mathbf{a}_3$	$=$	$ax_3\hat{\mathbf{y}}$	(8i)	Mn II
$\mathbf{B}_9$	$-x_3\mathbf{a}_1 - x_3\mathbf{a}_3$	$=$	$-ax_3\hat{\mathbf{y}}$	(8i)	Mn II
$\mathbf{B}_{10}$	$\frac{1}{2}\mathbf{a}_1 + x_4\mathbf{a}_2 + (x_4 + \frac{1}{2})\mathbf{a}_3$	$=$	$ax_4\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}}$	(8j)	Mn III
$\mathbf{B}_{11}$	$\frac{1}{2}\mathbf{a}_1 - x_4\mathbf{a}_2 - (x_4 - \frac{1}{2})\mathbf{a}_3$	$=$	$-ax_4\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}}$	(8j)	Mn III
$\mathbf{B}_{12}$	$x_4\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_2 + (x_4 + \frac{1}{2})\mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{x}} + ax_4\hat{\mathbf{y}}$	(8j)	Mn III
$\mathbf{B}_{13}$	$-x_4\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_2 - (x_4 - \frac{1}{2})\mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{x}} - ax_4\hat{\mathbf{y}}$	(8j)	Mn III

References

- [1] J. V. Florio, R. E. Rundle, and A. I. Snow, *Compounds of thorium with transition metals. I. The thorium-manganese system*, Acta Cryst. **5**, 449–457 (1952), doi:10.1107/S0365110X52001337.

Found in

- [1] P. Villars and L. Calvert, *Pearson's Handbook of Crystallographic Data for Intermetallic Phases* (ASM International, Materials Park, OH, 1991), 2nd edn.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017