

# Li<sub>13</sub>Sn<sub>5</sub> Structure:


## A13B5\_hP18\_164\_a2c4d\_b2d-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/G8A6>

[https://aflow.org/prototype-encyclopedia/A13B5\\_hP18\\_164\\_a2c4d\\_b2d-001](https://aflow.org/prototype-encyclopedia/A13B5_hP18_164_a2c4d_b2d-001)

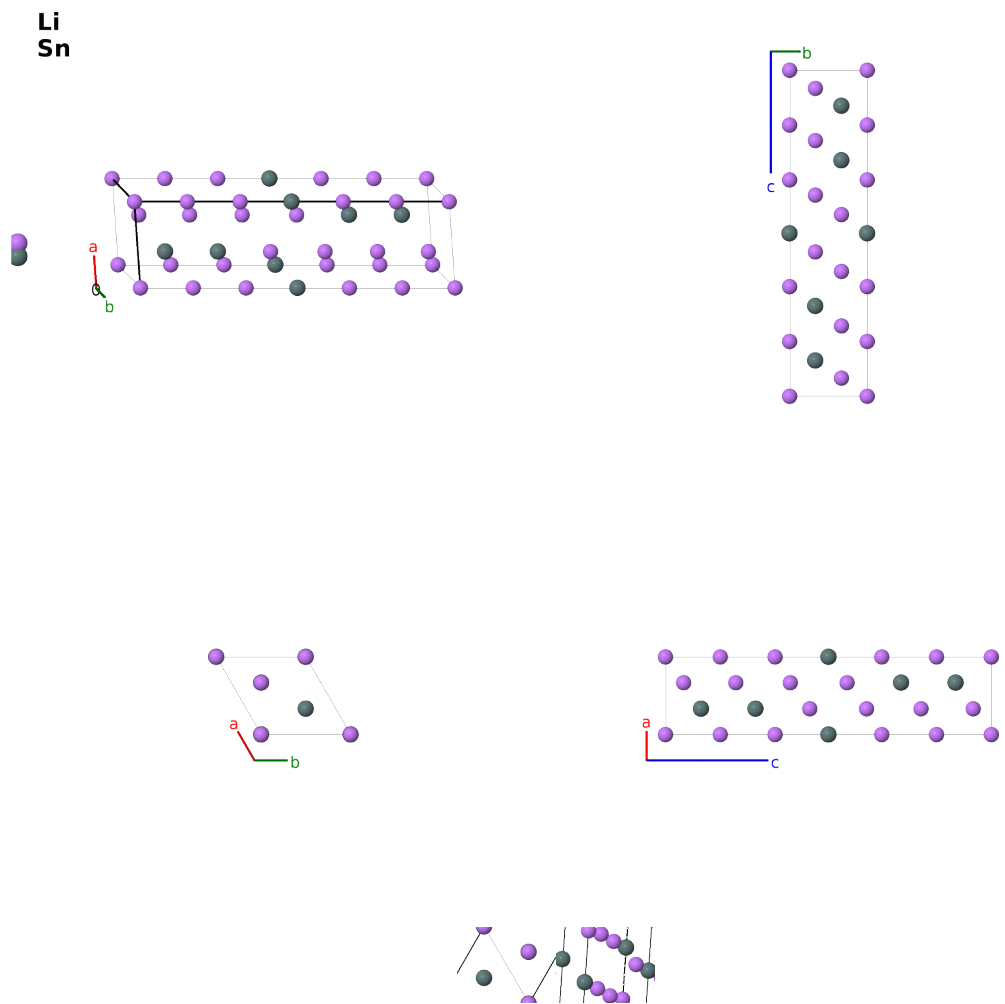

|                       |                                  |
|-----------------------|----------------------------------|
| Prototype             | Li <sub>13</sub> Sn <sub>5</sub> |
| AFLOW prototype label | A13B5_hP18_164_a2c4d_b2d-001     |
| ICSD                  | 104786                           |
| CCDC                  | 1662687                          |
| Pearson symbol        | hP18                             |
| Space group number    | 164                              |

Space group symbol  $P\bar{3}m1$


AFLOW prototype command `aflow --proto=A13B5_hP18_164_a2c4d_b2d-001`  
`--params=a, c/a, z3, z4, z5, z6, z7, z8, z9, z10`

---

- We have made two corrections to the data given in (Frank, 1975):
    - They do not give any information on the position of atom Li(5) (our Li-III) in Table I. Figure 1 places it on a (2c) site. We used the distance data in Table II to find the value of  $z_3$ .
    - They place atom Li(6) (our Li-IV) on a (2d) site. The figure shows it is on a (2c) site. The coordinate given is consistent with the distances found in the aforementioned table.
- 

### Trigonal (Hexagonal) primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}} \end{aligned}$$

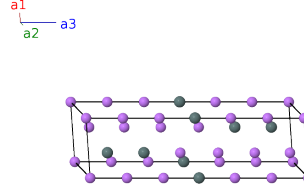

### Basis vectors

|                   | Lattice coordinates                                                         |     | Cartesian coordinates                                                                             | Wyckoff position | Atom type |
|-------------------|-----------------------------------------------------------------------------|-----|---------------------------------------------------------------------------------------------------|------------------|-----------|
| $\mathbf{B}_1$    | $0$                                                                         | $=$ | $0$                                                                                               | (1a)             | Li I      |
| $\mathbf{B}_2$    | $\frac{1}{2} \mathbf{a}_3$                                                  | $=$ | $\frac{1}{2}c \hat{\mathbf{z}}$                                                                   | (1b)             | Sn I      |
| $\mathbf{B}_3$    | $z_3 \mathbf{a}_3$                                                          | $=$ | $cz_3 \hat{\mathbf{z}}$                                                                           | (2c)             | Li II     |
| $\mathbf{B}_4$    | $-z_3 \mathbf{a}_3$                                                         | $=$ | $-cz_3 \hat{\mathbf{z}}$                                                                          | (2c)             | Li II     |
| $\mathbf{B}_5$    | $z_4 \mathbf{a}_3$                                                          | $=$ | $cz_4 \hat{\mathbf{z}}$                                                                           | (2c)             | Li III    |
| $\mathbf{B}_6$    | $-z_4 \mathbf{a}_3$                                                         | $=$ | $-cz_4 \hat{\mathbf{z}}$                                                                          | (2c)             | Li III    |
| $\mathbf{B}_7$    | $\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_5 \mathbf{a}_3$    | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$    | (2d)             | Li IV     |
| $\mathbf{B}_8$    | $\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_5 \mathbf{a}_3$    | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - cz_5 \hat{\mathbf{z}}$    | (2d)             | Li IV     |
| $\mathbf{B}_9$    | $\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_6 \mathbf{a}_3$    | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}}$    | (2d)             | Li V      |
| $\mathbf{B}_{10}$ | $\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_6 \mathbf{a}_3$    | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - cz_6 \hat{\mathbf{z}}$    | (2d)             | Li V      |
| $\mathbf{B}_{11}$ | $\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_7 \mathbf{a}_3$    | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$    | (2d)             | Li VI     |
| $\mathbf{B}_{12}$ | $\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_7 \mathbf{a}_3$    | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$    | (2d)             | Li VI     |
| $\mathbf{B}_{13}$ | $\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_8 \mathbf{a}_3$    | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + cz_8 \hat{\mathbf{z}}$    | (2d)             | Li VII    |
| $\mathbf{B}_{14}$ | $\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_8 \mathbf{a}_3$    | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - cz_8 \hat{\mathbf{z}}$    | (2d)             | Li VII    |
| $\mathbf{B}_{15}$ | $\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_9 \mathbf{a}_3$    | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + cz_9 \hat{\mathbf{z}}$    | (2d)             | Sn II     |
| $\mathbf{B}_{16}$ | $\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_9 \mathbf{a}_3$    | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - cz_9 \hat{\mathbf{z}}$    | (2d)             | Sn II     |
| $\mathbf{B}_{17}$ | $\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_{10} \mathbf{a}_3$ | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + cz_{10} \hat{\mathbf{z}}$ | (2d)             | Sn III    |
| $\mathbf{B}_{18}$ | $\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_{10} \mathbf{a}_3$ | $=$ | $\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - cz_{10} \hat{\mathbf{z}}$ | (2d)             | Sn III    |

## References

- [1] U. Frank and W. Müller, *Darstellung und Struktur der Phase  $Li_{13}Sn_5$  und die strukturelle Verwandtschaft der Phasen in den Systemen  $Li-Sn$  und  $Li-Pb$* , Z. Naturforsch. B **30**, 316–322 (1975), doi:10.1515/znb-1975-5-605.

## First cited in

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.