


Palladseite (Pd₁₇Se₁₅) Structure: A17B15_cP64_221_acfm_eij-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/RWLL>

https://aflow.org/prototype-encyclopedia/A17B15_cP64_221_acfm_eij-001

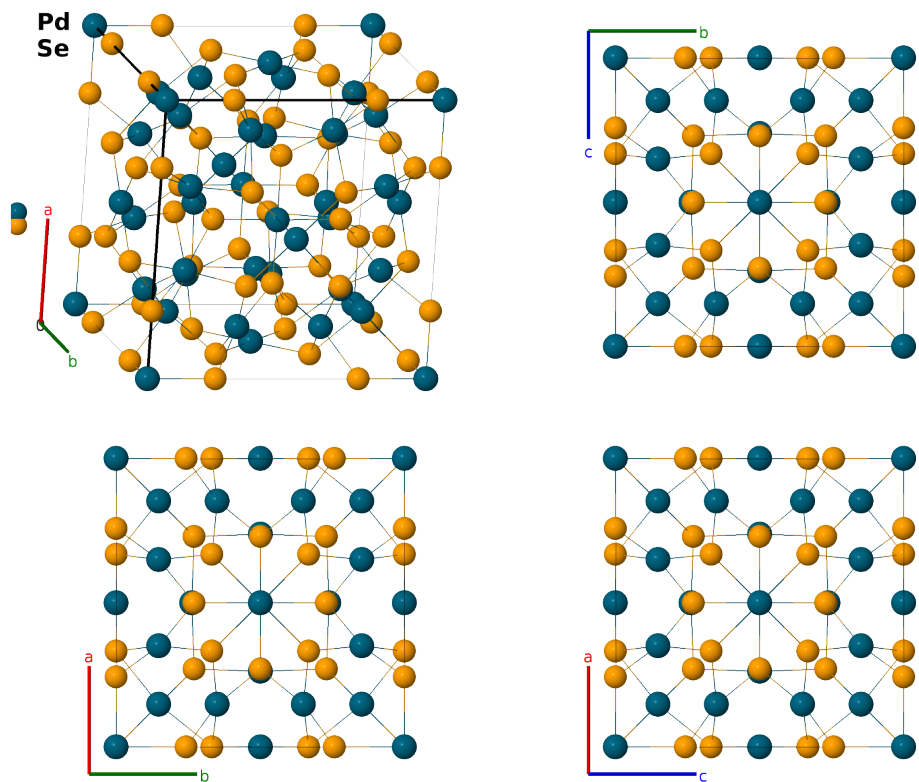

Prototype	Pd ₁₇ Se ₁₅
AFLOW prototype label	A17B15_cP64_221_acfm_eij-001
Mineral name	palladseite
ICSD	23907
CCDC	1599974
Pearson symbol	cP64
Space group number	221
Space group symbol	$Pm\bar{3}m$
AFLOW prototype command	<code>aflow --proto=A17B15_cP64_221_acfm_eij-001 --params=a, x₃, x₄, y₅, y₆, x₇, z₇</code>

Other compounds with this structure

Rh₁₇Se₁₅


- (Geller, 1962) determined that Pd₁₇Se₁₅ could be in space group $Pm\bar{3}m$ #221 (this structure), $P\bar{4}3m$ #215, or $P432$ #207, and finds that $Pm\bar{3}m$ gives the best fit to single-crystal X-ray diffraction pattern, even though the fit of the parameters for the all of the Wyckoff sites could not be converged. We therefore present all three structure possibilities.
- We shifted the coordinates of (Geller, 1962) to move the Pd-I atom from the center of the cubic cell, Wyckoff position (1b), to the origin, Wyckoff position (1a).

Simple Cubic primitive vectors

$$\mathbf{a}_1 = a \hat{\mathbf{x}}$$

$$\mathbf{a}_2 = a \hat{\mathbf{y}}$$

$$\mathbf{a}_3 = a \hat{\mathbf{z}}$$

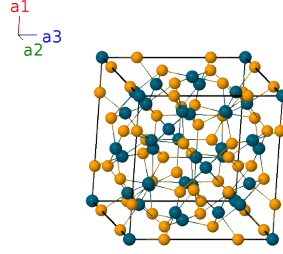

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	(1a) Pd I
$\mathbf{B}_2$	$=$	$\frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(3c) Pd II
$\mathbf{B}_3$	$=$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{z}}$	(3c) Pd II
$\mathbf{B}_4$	$=$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}}$	(3c) Pd II
$\mathbf{B}_5$	$=$	$x_3 \mathbf{a}_1$	$=$	$ax_3 \hat{\mathbf{x}}$	(6e) Se I
$\mathbf{B}_6$	$=$	$-x_3 \mathbf{a}_1$	$=$	$-ax_3 \hat{\mathbf{x}}$	(6e) Se I
$\mathbf{B}_7$	$=$	$x_3 \mathbf{a}_2$	$=$	$ax_3 \hat{\mathbf{y}}$	(6e) Se I
$\mathbf{B}_8$	$=$	$-x_3 \mathbf{a}_2$	$=$	$-ax_3 \hat{\mathbf{y}}$	(6e) Se I
$\mathbf{B}_9$	$=$	$x_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{z}}$	(6e) Se I
$\mathbf{B}_{10}$	$=$	$-x_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{z}}$	(6e) Se I
$\mathbf{B}_{11}$	$=$	$x_4 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(6f) Pd III
$\mathbf{B}_{12}$	$=$	$-x_4 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(6f) Pd III
$\mathbf{B}_{13}$	$=$	$\frac{1}{2} \mathbf{a}_1 + x_4 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(6f) Pd III
$\mathbf{B}_{14}$	$=$	$\frac{1}{2} \mathbf{a}_1 - x_4 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(6f) Pd III
$\mathbf{B}_{15}$	$=$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + x_4 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + ax_4 \hat{\mathbf{z}}$	(6f) Pd III
$\mathbf{B}_{16}$	$=$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 - x_4 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} - ax_4 \hat{\mathbf{z}}$	(6f) Pd III
$\mathbf{B}_{17}$	$=$	$y_5 \mathbf{a}_2 + y_5 \mathbf{a}_3$	$=$	$ay_5 \hat{\mathbf{y}} + ay_5 \hat{\mathbf{z}}$	(12i) Se II
$\mathbf{B}_{18}$	$=$	$-y_5 \mathbf{a}_2 + y_5 \mathbf{a}_3$	$=$	$-ay_5 \hat{\mathbf{y}} + ay_5 \hat{\mathbf{z}}$	(12i) Se II
$\mathbf{B}_{19}$	$=$	$y_5 \mathbf{a}_2 - y_5 \mathbf{a}_3$	$=$	$ay_5 \hat{\mathbf{y}} - ay_5 \hat{\mathbf{z}}$	(12i) Se II
$\mathbf{B}_{20}$	$=$	$-y_5 \mathbf{a}_2 - y_5 \mathbf{a}_3$	$=$	$-ay_5 \hat{\mathbf{y}} - ay_5 \hat{\mathbf{z}}$	(12i) Se II

$$\begin{array}{llllll}
\mathbf{B}_{62} & = & z_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 + x_7 \mathbf{a}_3 & = & az_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} + ax_7 \hat{\mathbf{z}} & (24m) \quad \text{Pd IV} \\
\mathbf{B}_{63} & = & -z_7 \mathbf{a}_1 + x_7 \mathbf{a}_2 + x_7 \mathbf{a}_3 & = & -az_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} + ax_7 \hat{\mathbf{z}} & (24m) \quad \text{Pd IV} \\
\mathbf{B}_{64} & = & -z_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 - x_7 \mathbf{a}_3 & = & -az_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} - ax_7 \hat{\mathbf{z}} & (24m) \quad \text{Pd IV}
\end{array}$$

References

- [1] S. Geller, *The Crystal Structure of $Pd_{17}Se_{15}$* , Acta Cryst. **15**, 713–721 (1962), doi:10.1107/S0365110X62001929.

Found in

- [1] D. Barthelmy, *Mineralogy Database* (2012). Palladseite Mineral Data.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.