

Co₂B₂O₅ Structure:

A2B2C5_aP18_2_2i_2i_5i-001


This structure previously used the label(s) **A2B2C5_aP18_2_2i_2i_5i**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/RJNZ>


https://aflow.org/prototype-encyclopedia/A2B2C5_aP18_2_2i_2i_5i-001

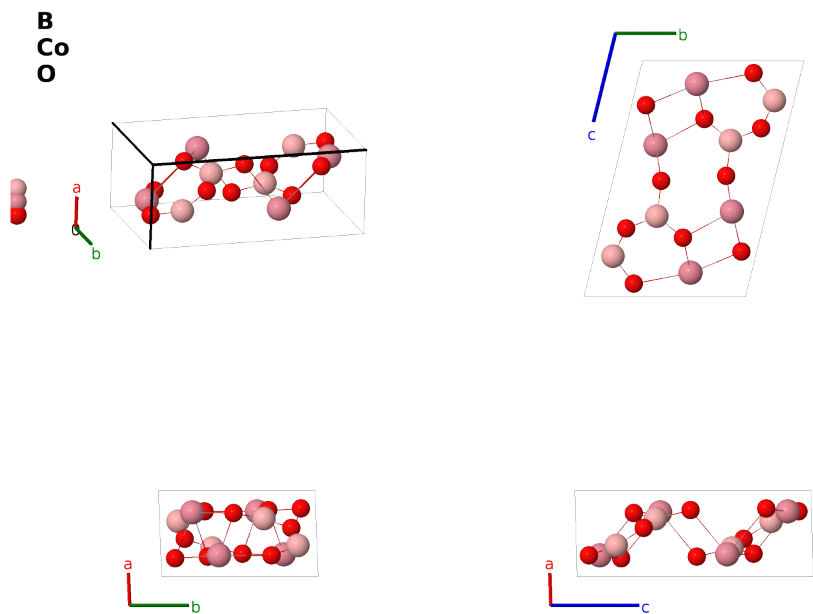

Prototype	B ₂ Co ₂ O ₅
AFLOW prototype label	A2B2C5_aP18_2_2i_2i_5i-001
ICSD	24284
CCDC	1600329
Pearson symbol	aP18
Space group number	2
Space group symbol	$P\bar{1}$
AFLOW prototype command	<pre>aflow --proto=A2B2C5_aP18_2_2i_2i_5i-001 --params=a,b/a,c/a,α,β,γ,x₁,y₁,z₁,x₂,y₂,z₂,x₃,y₃,z₃,x₄,y₄,z₄,x₅,y₅,z₅,x₆,y₆, z₆,x₇,y₇,z₇,x₈,y₈,z₈,x₉,y₉,z₉</pre>

Triclinic primitive vectors

$$\begin{aligned}
\mathbf{a}_1 &= a \hat{\mathbf{x}} \\
\mathbf{a}_2 &= b \cos \gamma \hat{\mathbf{x}} + b \sin \gamma \hat{\mathbf{y}} \\
\mathbf{a}_3 &= c_x \hat{\mathbf{x}} + c_y \hat{\mathbf{y}} + c_z \hat{\mathbf{z}} \\
c_x &= c \cos \beta \\
c_y &= c(\cos \alpha - \cos \beta \cos \gamma) / \sin \gamma \\
c_z &= \sqrt{c^2 - c_x^2 - c_y^2}
\end{aligned}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$x_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	=	$(ax_1 + by_1 \cos \gamma + c_x z_1) \hat{\mathbf{x}} + (by_1 \sin \gamma + c_y z_1) \hat{\mathbf{y}} + c_z z_1 \hat{\mathbf{z}}$	(2i)	B I
$\mathbf{B}_2$	$-x_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 - z_1 \mathbf{a}_3$	=	$-(ax_1 + by_1 \cos \gamma + c_x z_1) \hat{\mathbf{x}} - (by_1 \sin \gamma + c_y z_1) \hat{\mathbf{y}} - c_z z_1 \hat{\mathbf{z}}$	(2i)	B I
$\mathbf{B}_3$	$x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$(ax_2 + by_2 \cos \gamma + c_x z_2) \hat{\mathbf{x}} + (by_2 \sin \gamma + c_y z_2) \hat{\mathbf{y}} + c_z z_2 \hat{\mathbf{z}}$	(2i)	B II
$\mathbf{B}_4$	$-x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	=	$-(ax_2 + by_2 \cos \gamma + c_x z_2) \hat{\mathbf{x}} - (by_2 \sin \gamma + c_y z_2) \hat{\mathbf{y}} - c_z z_2 \hat{\mathbf{z}}$	(2i)	B II
$\mathbf{B}_5$	$x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$(ax_3 + by_3 \cos \gamma + c_x z_3) \hat{\mathbf{x}} + (by_3 \sin \gamma + c_y z_3) \hat{\mathbf{y}} + c_z z_3 \hat{\mathbf{z}}$	(2i)	Co I
$\mathbf{B}_6$	$-x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$-(ax_3 + by_3 \cos \gamma + c_x z_3) \hat{\mathbf{x}} - (by_3 \sin \gamma + c_y z_3) \hat{\mathbf{y}} - c_z z_3 \hat{\mathbf{z}}$	(2i)	Co I
$\mathbf{B}_7$	$x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	=	$(ax_4 + by_4 \cos \gamma + c_x z_4) \hat{\mathbf{x}} + (by_4 \sin \gamma + c_y z_4) \hat{\mathbf{y}} + c_z z_4 \hat{\mathbf{z}}$	(2i)	Co II
$\mathbf{B}_8$	$-x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	=	$-(ax_4 + by_4 \cos \gamma + c_x z_4) \hat{\mathbf{x}} - (by_4 \sin \gamma + c_y z_4) \hat{\mathbf{y}} - c_z z_4 \hat{\mathbf{z}}$	(2i)	Co II
$\mathbf{B}_9$	$x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	=	$(ax_5 + by_5 \cos \gamma + c_x z_5) \hat{\mathbf{x}} + (by_5 \sin \gamma + c_y z_5) \hat{\mathbf{y}} + c_z z_5 \hat{\mathbf{z}}$	(2i)	O I
$\mathbf{B}_{10}$	$-x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	=	$-(ax_5 + by_5 \cos \gamma + c_x z_5) \hat{\mathbf{x}} - (by_5 \sin \gamma + c_y z_5) \hat{\mathbf{y}} - c_z z_5 \hat{\mathbf{z}}$	(2i)	O I
$\mathbf{B}_{11}$	$x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	=	$(ax_6 + by_6 \cos \gamma + c_x z_6) \hat{\mathbf{x}} + (by_6 \sin \gamma + c_y z_6) \hat{\mathbf{y}} + c_z z_6 \hat{\mathbf{z}}$	(2i)	O II
$\mathbf{B}_{12}$	$-x_6 \mathbf{a}_1 - y_6 \mathbf{a}_2 - z_6 \mathbf{a}_3$	=	$-(ax_6 + by_6 \cos \gamma + c_x z_6) \hat{\mathbf{x}} - (by_6 \sin \gamma + c_y z_6) \hat{\mathbf{y}} - c_z z_6 \hat{\mathbf{z}}$	(2i)	O II
$\mathbf{B}_{13}$	$x_7 \mathbf{a}_1 + y_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$	=	$(ax_7 + by_7 \cos \gamma + c_x z_7) \hat{\mathbf{x}} + (by_7 \sin \gamma + c_y z_7) \hat{\mathbf{y}} + c_z z_7 \hat{\mathbf{z}}$	(2i)	O III
$\mathbf{B}_{14}$	$-x_7 \mathbf{a}_1 - y_7 \mathbf{a}_2 - z_7 \mathbf{a}_3$	=	$-(ax_7 + by_7 \cos \gamma + c_x z_7) \hat{\mathbf{x}} - (by_7 \sin \gamma + c_y z_7) \hat{\mathbf{y}} - c_z z_7 \hat{\mathbf{z}}$	(2i)	O III
$\mathbf{B}_{15}$	$x_8 \mathbf{a}_1 + y_8 \mathbf{a}_2 + z_8 \mathbf{a}_3$	=	$(ax_8 + by_8 \cos \gamma + c_x z_8) \hat{\mathbf{x}} + (by_8 \sin \gamma + c_y z_8) \hat{\mathbf{y}} + c_z z_8 \hat{\mathbf{z}}$	(2i)	O IV
$\mathbf{B}_{16}$	$-x_8 \mathbf{a}_1 - y_8 \mathbf{a}_2 - z_8 \mathbf{a}_3$	=	$-(ax_8 + by_8 \cos \gamma + c_x z_8) \hat{\mathbf{x}} - (by_8 \sin \gamma + c_y z_8) \hat{\mathbf{y}} - c_z z_8 \hat{\mathbf{z}}$	(2i)	O IV

$$\begin{aligned}
\mathbf{B}_{17} &= x_9 \mathbf{a}_1 + y_9 \mathbf{a}_2 + z_9 \mathbf{a}_3 &= (ax_9 + by_9 \cos \gamma + c_x z_9) \hat{\mathbf{x}} + (by_9 \sin \gamma + c_y z_9) \hat{\mathbf{y}} + c_z z_9 \hat{\mathbf{z}} &(2i) & \text{O V} \\
\mathbf{B}_{18} &= -x_9 \mathbf{a}_1 - y_9 \mathbf{a}_2 - z_9 \mathbf{a}_3 &= -(ax_9 + by_9 \cos \gamma + c_x z_9) \hat{\mathbf{x}} - (by_9 \sin \gamma + c_y z_9) \hat{\mathbf{y}} - c_z z_9 \hat{\mathbf{z}} &(2i) & \text{O V}
\end{aligned}$$

References

- [1] S. V. Berger, *The Crystal Structure of Cobaltpyroborate*, Acta Chem. Scand. **4**, 1054–1065 (1950), doi:10.3891/acta.chem.scand.04-1054.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.