

Pyrochlore Iridate ($\text{Eu}_2\text{Ir}_2\text{O}_7$, $E8_1$) Structure: A2B2C7_cF88_227_c_d_af-001


This structure previously used the label(s) **A2B2C7_cF88_227_c_d_af**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/0R9R>

https://aflow.org/prototype-encyclopedia/A2B2C7_cF88_227_c_d_af-001

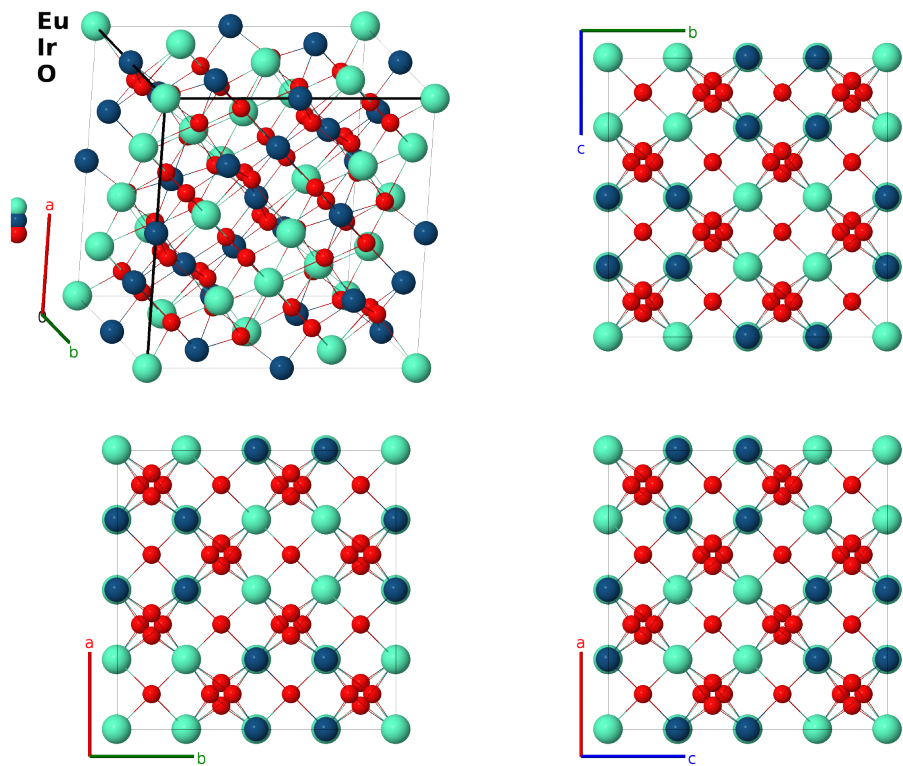

Prototype	$\text{Eu}_2\text{Ir}_2\text{O}_7$
AFLOW prototype label	A2B2C7_cF88_227_c_d_af-001
<i>Strukturbericht</i> designation	$E8_1$
Mineral name	pyrochlore iridate
ICSD	135031
CCDC	2198683
Pearson symbol	cF88
Space group number	227
Space group symbol	$Fd\bar{3}m$

AFLOW prototype command `aflow --proto=A2B2C7_cF88_227_c_d_af-001`
 `--params=a, x4`


Other compounds with this structure

Am₂Zr₂O₇, Bi₂Hf₂O₇, Bi₂InNbO₇, Bi₂InTaO₇, Bi₂Ir₂O₇, Bi₂LaTaO₇, Bi₂Pt₂O₇, Bi₂Ru₂O₇, Bi₂Sn₂O₇, Bi₂Ti₂O₇, Bi₂YTaO₇, Ca₂Bi₂O₇, Ca₂Nb₂O₇, Ca₂Ru₂O₇, Ca₂Ta₂O₇, Ca₂Ta₂O₆F, Cd₂Nb₂O₇, Cd₂Os₂O₇, Cd₂Re₂O₇, Cd₂Ru₂O₇, Cd₂Sb₂O₇, Cd₂Ta₂O₇, Cd₂Tc₂O₇, Ce₂Sn₂O₇, Ce₂Zr₂O₇, Co₂Sb₂O₇, Dy₂CrSbO₇, Dy₂GaSbO₇, Dy₂Ge₂O₇, Dy₂Hf₂O₇, Dy₂Mo₂O₇, Dy₂Ru₂O₇, Dy₂Sn₂O₇, Dy₂Tc₂O₇, Dy₂Ti₂O₇, Dy₂V₂O₇, Er₂Mn₂O₇, Er₂Ru₂O₇, Er₂Sn₂O₇, Er₂Tc₂O₇, Er₂Ti₂O₇, Er₂V₂O₇, Eu₂Hf₂O₇, Eu₂Ir₂O₇, Eu₂Mo₂O₇, Eu₂Pb₂O₇, Eu₂Pt₂O₇, Eu₂Ru₂O₇, Eu₂ScNbO₇, Eu₂Sn₂O₇, Eu₂Ti₂O₇, Eu₂Zr₂O₇, Gd₂Ge₂O₇, Gd₂Hf₂O₇, Gd₂InSbO₇, Gd₂MnSbO₇, Gd₂Mo₂O₇, Gd₂Pb₂O₇, Gd₂Pt₂O₇, Gd₂Ru₂O₇, Gd₂Sn₂O₇, Gd₂T₂O₇, Gd₂Ti₂O₇, Gd₂Zr₂O₇, GdEuTi₂O₇, Hg₂Cu₂F₆S, Hg₂Mn₂F₆S, Hg₂Nb₂O₇, Hg₂Ni₂F₆O, Hg₂Ni₂F₆S, Hg₂Os₂O₇, Hg₂Ru₂O₇, Hg₂Sb₂O₇, Hg₂Zn₂F₆O, Ho₂CrSbO₇, Ho₂Ge₂O₇, Ho₂Mo₂O₇, Ho₂Ru₂O₇, Ho₂Sn₂O₇, Ho₂Ti₂O₇, HoNdZr₂O₇, In₂Ge₂O₇, In₂Mn₂O₇, In₂Si₂O₇, La₂Hf₂O₇, La₂Pb₂O₇, La₂Sn₂O₇, La₂Zr₂O₇, Lu₂Ge₂O₇, Lu₂Mn₂O₇, Lu₂Ru₂O₇, Lu₂Sn₂O₇, Lu₂Ti₂O₇, Lu₂V₂O₇, Mn₂Sb₂O₇, Nd₂Hf₂O₇, Nd₂Ir₂O₇, Nd₂Mo₂O₇, Nd₂Pb₂O₇, Nd₂Pt₂O₇, Nd₂Ru₂O₇, Nd₂Sn₂O₇, Nd₂Tc₂O₇, Nd₂Zr₂O₇, Ni₂Sb₂O₇, Pb₂Co₂O₇, Pb₂Ir₂O₇, Pb₂Sb₂O₇, Pr₂Ir₂O₇, Pr₂Ru₂O₇, Pr₂Sn₂O₇, Pr₂Tc₂O₇, Pr₂Zr₂O₇, Sc₂Ge₂O₇, Sc₂Mn₂O₇, Sc₂Si₂O₇, Sm₂Mo₂O₇, Sm₂Ru₂O₇, Sm₂Sn₂O₇, Sm₂Tc₂O₇, Sm₂Ti₂O₇, Sm₂Zr₂O₇, Sn₂Ta₂O₇, Sr₂Bi₂O₇, Tb₂Mo₂O₇, Tb₂Ru₂O₇, Tb₂Sn₂O₇, Tb₂Ti₂O₇, Ti₂Y₂O₇, Tl₂Ir₂O₇, Tl₂Mn₂O₇, Tl₂Nb₂O₇, Tl₂Pt₂O₇, Tl₂Ru₂O₇, Tm₂Mn₂O₇, Tm₂Ru₂O₇, Tm₂Sn₂O₇, Tm₂Ti₂O₇, Tm₂V₂O₇, Y₂Ir₂O₇, Y₂Mn₂O₇, Y₂Mo₂O₇, Y₂Ru₂O₇, Y₂Sn₂O₇, Y₂Ti₂O₇, Y₂V₂O₇, Y₂Zr₂O₇, Yb₂Ge₂O₇, Yb₂Ru₂O₇, Yb₂Sn₂O₇, Yb₂Ti₂O₇, Yb₂V₂O₇, Ca₂Nb₂O₇, Ca₂Ru₂O₇, Dy₂Ti₂O₇, In₂Ge₂O₇, Sn₂Nb₂O₇, Sn₂Nd₂O₇, Sn₂Ta₂O₇, Y₂Mn₂O₇, Yb₂Ir₂O₇, FNb₂(Nb, Ca)₂O₆ ("synthetic" pyrochlore), (Nb, Ta, Ti)₂(Ca, Ce, Na, K)₂(F, O)₇ ("natural" pyrochlore), (F, O, OH)(Nb, Fe)₂(Ca, Ce, Na, K)₂O₆ (Koppit), (F, OH)Sb₂(Ca, Mn, Na)₂O₆ (Roméite), (OH)Sb₂(Ca, Fe, Na)₂O₆ (Scheebergite), (Sb, Ti)₂(Ca, Fe, Mn, Na)₂(O, OH)₆ (Lewisite), (OH, F)(Nb, Ta, Ti)₂(Ca, Fe, Na)₂O₆ (Pyrrhite), (OH, F)(Nb, Ta)₂(Ca, Fe, Na)₂O₆ (Mikrolith), Sb₂Pb₂O₇ (Bindheimite), (H₂O)_{0.875}(Al_{0.8125}Mg_{0.1875})₂Na_{0.375}[F_{0.65}(OH)_{0.35}]₆ (Ralstonite), MgZrSi₂O₇, NaCaFe₂F₇, NaCaMg₂F₇, NaCaNi₂F₇, NaCdZn₂F₇, NaSrCo₂F₇, NaSrFe₂F₇, NaSrMg₂F₇, NaSrMn₂F₇, Y₂CrSbO₇, Y₂FeSbO₇, Y₂GaSbO₇, Dy₂GaSbO₇, Sb₃O₆OH, BiTa₂O₆F, Pr₃IrO₇

- (Herrmann, 1943) uses *Strukturbericht E8₁* to describe the cubic pyrochlore structures. These have the general formula R₂Q₂X₇, where the X atoms or radicals occupy the (4a) and (48f) sites, and the R and Q atoms occupy the (16c) and (16d) sites. In many cases the sites are only partially filled and/or have mixed chemistry. We use Eu₂Ir₂O₇ as our prototype because it represents a fully filled system.
 - We take our data from (Sagayama, 2013), but the ICSD entry is from the later work of (Nenoff, 2021).
-

Face-centered Cubic primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}a\hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} \end{aligned}$$

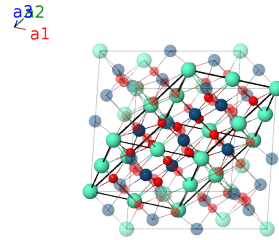

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{8}\mathbf{a}_1 + \frac{1}{8}\mathbf{a}_2 + \frac{1}{8}\mathbf{a}_3$	$=$	$\frac{1}{8}a\hat{\mathbf{x}} + \frac{1}{8}a\hat{\mathbf{y}} + \frac{1}{8}a\hat{\mathbf{z}}$	(8a)	O I
$\mathbf{B}_2$	$= \frac{7}{8}\mathbf{a}_1 + \frac{7}{8}\mathbf{a}_2 + \frac{7}{8}\mathbf{a}_3$	$=$	$\frac{7}{8}a\hat{\mathbf{x}} + \frac{7}{8}a\hat{\mathbf{y}} + \frac{7}{8}a\hat{\mathbf{z}}$	(8a)	O I
$\mathbf{B}_3$	$= 0$	$=$	0	(16c)	Eu I
$\mathbf{B}_4$	$= \frac{1}{2}\mathbf{a}_3$	$=$	$\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{y}}$	(16c)	Eu I

$$\begin{aligned}
\mathbf{B}_5 &= \frac{1}{2} \mathbf{a}_2 &= \frac{1}{4} a \hat{\mathbf{x}} + \frac{1}{4} a \hat{\mathbf{z}} & (16c) & \text{Eu I} \\
\mathbf{B}_6 &= \frac{1}{2} \mathbf{a}_1 &= \frac{1}{4} a \hat{\mathbf{y}} + \frac{1}{4} a \hat{\mathbf{z}} & (16c) & \text{Eu I} \\
\mathbf{B}_7 &= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 &= \frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}} & (16d) & \text{Ir I} \\
\mathbf{B}_8 &= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 &= \frac{1}{4} a \hat{\mathbf{x}} + \frac{1}{4} a \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}} & (16d) & \text{Ir I} \\
\mathbf{B}_9 &= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3 &= \frac{1}{4} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + \frac{1}{4} a \hat{\mathbf{z}} & (16d) & \text{Ir I} \\
\mathbf{B}_{10} &= \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 &= \frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{4} a \hat{\mathbf{y}} + \frac{1}{4} a \hat{\mathbf{z}} & (16d) & \text{Ir I} \\
\mathbf{B}_{11} &= -\left(x_4 - \frac{1}{4}\right) \mathbf{a}_1 + x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3 &= ax_4 \hat{\mathbf{x}} + \frac{1}{8} a \hat{\mathbf{y}} + \frac{1}{8} a \hat{\mathbf{z}} & (48f) & \text{O II} \\
\mathbf{B}_{12} &= x_4 \mathbf{a}_1 - \left(x_4 - \frac{1}{4}\right) \mathbf{a}_2 - \left(x_4 - \frac{1}{4}\right) \mathbf{a}_3 &= -a \left(x_4 - \frac{1}{4}\right) \hat{\mathbf{x}} + \frac{1}{8} a \hat{\mathbf{y}} + \frac{1}{8} a \hat{\mathbf{z}} & (48f) & \text{O II} \\
\mathbf{B}_{13} &= x_4 \mathbf{a}_1 - \left(x_4 - \frac{1}{4}\right) \mathbf{a}_2 + x_4 \mathbf{a}_3 &= \frac{1}{8} a \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}} + \frac{1}{8} a \hat{\mathbf{z}} & (48f) & \text{O II} \\
\mathbf{B}_{14} &= -\left(x_4 - \frac{1}{4}\right) \mathbf{a}_1 + x_4 \mathbf{a}_2 - \left(x_4 - \frac{1}{4}\right) \mathbf{a}_3 &= \frac{1}{8} a \hat{\mathbf{x}} - a \left(x_4 - \frac{1}{4}\right) \hat{\mathbf{y}} + \frac{1}{8} a \hat{\mathbf{z}} & (48f) & \text{O II} \\
\mathbf{B}_{15} &= x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 - \left(x_4 - \frac{1}{4}\right) \mathbf{a}_3 &= \frac{1}{8} a \hat{\mathbf{x}} + \frac{1}{8} a \hat{\mathbf{y}} + ax_4 \hat{\mathbf{z}} & (48f) & \text{O II} \\
\mathbf{B}_{16} &= -\left(x_4 - \frac{1}{4}\right) \mathbf{a}_1 - \left(x_4 - \frac{1}{4}\right) \mathbf{a}_2 + x_4 \mathbf{a}_3 &= \frac{1}{8} a \hat{\mathbf{x}} + \frac{1}{8} a \hat{\mathbf{y}} - a \left(x_4 - \frac{1}{4}\right) \hat{\mathbf{z}} & (48f) & \text{O II} \\
\mathbf{B}_{17} &= \left(x_4 + \frac{3}{4}\right) \mathbf{a}_1 - x_4 \mathbf{a}_2 + \left(x_4 + \frac{3}{4}\right) \mathbf{a}_3 &= \frac{3}{8} a \hat{\mathbf{x}} + a \left(x_4 + \frac{3}{4}\right) \hat{\mathbf{y}} + \frac{3}{8} a \hat{\mathbf{z}} & (48f) & \text{O II} \\
\mathbf{B}_{18} &= -x_4 \mathbf{a}_1 + \left(x_4 + \frac{3}{4}\right) \mathbf{a}_2 - x_4 \mathbf{a}_3 &= \frac{3}{8} a \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}} + \frac{3}{8} a \hat{\mathbf{z}} & (48f) & \text{O II} \\
\mathbf{B}_{19} &= -x_4 \mathbf{a}_1 + \left(x_4 + \frac{3}{4}\right) \mathbf{a}_2 + \left(x_4 + \frac{3}{4}\right) \mathbf{a}_3 &= a \left(x_4 + \frac{3}{4}\right) \hat{\mathbf{x}} + \frac{3}{8} a \hat{\mathbf{y}} + \frac{3}{8} a \hat{\mathbf{z}} & (48f) & \text{O II} \\
\mathbf{B}_{20} &= \left(x_4 + \frac{3}{4}\right) \mathbf{a}_1 - x_4 \mathbf{a}_2 - x_4 \mathbf{a}_3 &= -ax_4 \hat{\mathbf{x}} + \frac{3}{8} a \hat{\mathbf{y}} + \frac{3}{8} a \hat{\mathbf{z}} & (48f) & \text{O II} \\
\mathbf{B}_{21} &= -x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 + \left(x_4 + \frac{3}{4}\right) \mathbf{a}_3 &= \frac{3}{8} a \hat{\mathbf{x}} + \frac{3}{8} a \hat{\mathbf{y}} - ax_4 \hat{\mathbf{z}} & (48f) & \text{O II} \\
\mathbf{B}_{22} &= \left(x_4 + \frac{3}{4}\right) \mathbf{a}_1 + \left(x_4 + \frac{3}{4}\right) \mathbf{a}_2 - x_4 \mathbf{a}_3 &= \frac{3}{8} a \hat{\mathbf{x}} + \frac{3}{8} a \hat{\mathbf{y}} + a \left(x_4 + \frac{3}{4}\right) \hat{\mathbf{z}} & (48f) & \text{O II}
\end{aligned}$$

References

- [1] H. Sagayama, D. Uematsu, T. Arima, K. Sugimoto, J. J. Ishikawa, E. O'Farrell, and S. Nakatsuji, *Determination of long-range all-in-all-out ordering of Ir^{4+} moments in a pyrochlore iridate $\text{Eu}_2\text{Ir}_2\text{O}_7$ by resonant x-ray diffraction*, Phys. Rev. B **87**, 100403 (2013), doi:10.1103/PhysRevB.87.100403.
- [2] C. Hermann, O. Lohrmann, and H. Philipp, eds., *Strukturbericht Band II 1928-1932* (Akademische Verlagsgesellschaft M. B. H., Leipzig, 1937).
- [3] K. Herrmann, ed., *Strukturbericht Band VII 1939* (Akademische Verlagsgesellschaft M. B. H., Leipzig, 1943).
- [4] T. M. Nenoff, D. X. Rademacher, M. A. Rodriguez, T. J. Garino, T. Subramani, and A. Navrotsky, *Structure-Property and Thermodynamic Relationships in Rare Earth (Y, Eu, Pr) Iridate Pyrochlores*, J. Solid State Chem. **299**, 122163 (2021), doi:10.1016/j.jssc.2021.122163.

Found in

- [1] S. H. Chun, B. Yuan, D. Casa, J. Kim, C.-Y. Kim, Z. Tian, Y. Qiu, S. Nakatsuji, and Y.-J. Kim, *Magnetic Excitations across the Metal-Insulator Transition in the Pyrochlore Iridate $\text{Eu}_2\text{Ir}_2\text{O}_7$* , Phys. Rev. Lett. **120**, 177203 (2018), doi:10.1103/PhysRevLett.120.177203.

First cited in

D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043