

Pr₅Co₂Ge₄ Structure:


A2B3C5_mC40_12_2i_3i_5i-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/422U>

https://aflow.org/prototype-encyclopedia/A2B3C5_mC40_12_2i_3i_5i-001

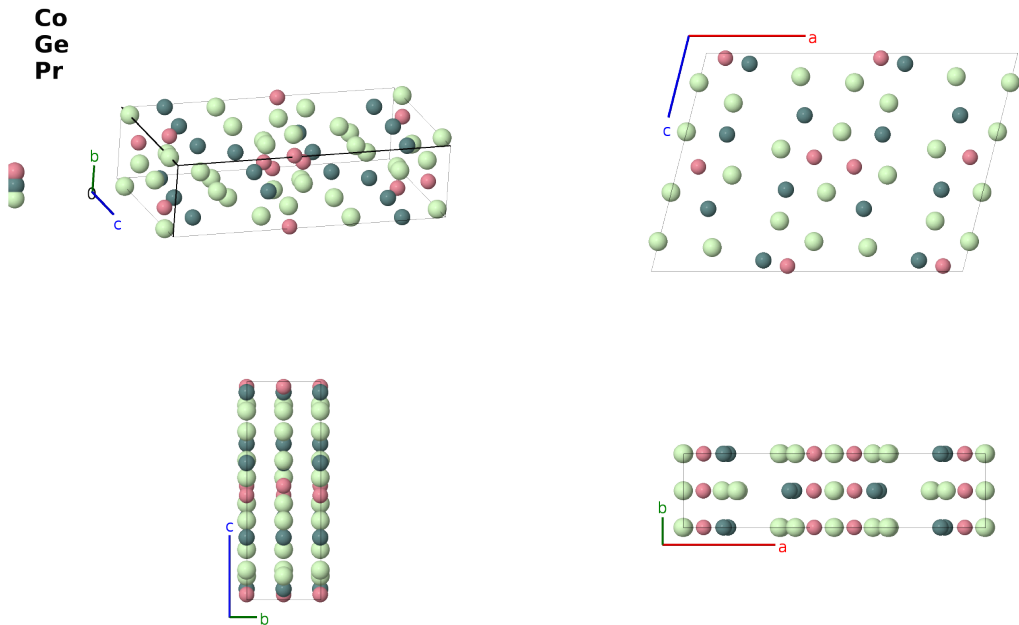


Prototype	Co ₂ Ge ₄ Pr ₅
AFLOW prototype label	A2B3C5_mC40_12_2i_3i_5i-001
CCDC	1882993
Pearson symbol	mC40
Space group number	12
Space group symbol	C2/m
AFLOW prototype command	<pre>aflow --proto=A2B3C5_mC40_12_2i_3i_5i-001 --params=a,b/a,c/a,β,x₁,z₁,x₂,z₂,x₃,z₃,x₄,z₄,x₅,z₅,x₆,z₆,x₇,z₇,x₈,z₈,x₉,z₉,x₁₀,z₁₀</pre>

Other compounds with this structure
Ce₅Co₂Ge₄, La₅Co₂Ge₄, Nd₅Co₂Ge₄, Pm₅Co₂Ge₄, Sm₅Co₂Ge₄

Base-centered Monoclinic primitive vectors

$$\begin{aligned}
\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\
\mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\
\mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}
\end{aligned}$$

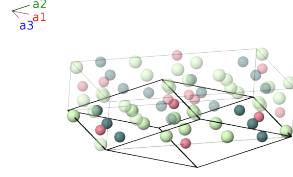

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + x_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(4i)	Co I
$\mathbf{B}_2$	$= -x_1 \mathbf{a}_1 - x_1 \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} - cz_1 \sin \beta \hat{\mathbf{z}}$	(4i)	Co I
$\mathbf{B}_3$	$= x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(4i)	Co II
$\mathbf{B}_4$	$= -x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(4i)	Co II
$\mathbf{B}_5$	$= x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(4i)	Ge I
$\mathbf{B}_6$	$= -x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(4i)	Ge I
$\mathbf{B}_7$	$= x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(4i)	Ge II
$\mathbf{B}_8$	$= -x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(4i)	Ge II
$\mathbf{B}_9$	$= x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(4i)	Ge III
$\mathbf{B}_{10}$	$= -x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - cz_5 \sin \beta \hat{\mathbf{z}}$	(4i)	Ge III
$\mathbf{B}_{11}$	$= x_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + cz_6 \sin \beta \hat{\mathbf{z}}$	(4i)	Pr I
$\mathbf{B}_{12}$	$= -x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$-(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - cz_6 \sin \beta \hat{\mathbf{z}}$	(4i)	Pr I
$\mathbf{B}_{13}$	$= x_7 \mathbf{a}_1 + x_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$	$=$	$(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} + cz_7 \sin \beta \hat{\mathbf{z}}$	(4i)	Pr II
$\mathbf{B}_{14}$	$= -x_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 - z_7 \mathbf{a}_3$	$=$	$-(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} - cz_7 \sin \beta \hat{\mathbf{z}}$	(4i)	Pr II
$\mathbf{B}_{15}$	$= x_8 \mathbf{a}_1 + x_8 \mathbf{a}_2 + z_8 \mathbf{a}_3$	$=$	$(ax_8 + cz_8 \cos \beta) \hat{\mathbf{x}} + cz_8 \sin \beta \hat{\mathbf{z}}$	(4i)	Pr III
$\mathbf{B}_{16}$	$= -x_8 \mathbf{a}_1 - x_8 \mathbf{a}_2 - z_8 \mathbf{a}_3$	$=$	$-(ax_8 + cz_8 \cos \beta) \hat{\mathbf{x}} - cz_8 \sin \beta \hat{\mathbf{z}}$	(4i)	Pr III
$\mathbf{B}_{17}$	$= x_9 \mathbf{a}_1 + x_9 \mathbf{a}_2 + z_9 \mathbf{a}_3$	$=$	$(ax_9 + cz_9 \cos \beta) \hat{\mathbf{x}} + cz_9 \sin \beta \hat{\mathbf{z}}$	(4i)	Pr IV
$\mathbf{B}_{18}$	$= -x_9 \mathbf{a}_1 - x_9 \mathbf{a}_2 - z_9 \mathbf{a}_3$	$=$	$-(ax_9 + cz_9 \cos \beta) \hat{\mathbf{x}} - cz_9 \sin \beta \hat{\mathbf{z}}$	(4i)	Pr IV
$\mathbf{B}_{19}$	$= x_{10} \mathbf{a}_1 + x_{10} \mathbf{a}_2 + z_{10} \mathbf{a}_3$	$=$	$(ax_{10} + cz_{10} \cos \beta) \hat{\mathbf{x}} + cz_{10} \sin \beta \hat{\mathbf{z}}$	(4i)	Pr V
$\mathbf{B}_{20}$	$= -x_{10} \mathbf{a}_1 - x_{10} \mathbf{a}_2 - z_{10} \mathbf{a}_3$	$=$	$-(ax_{10} + cz_{10} \cos \beta) \hat{\mathbf{x}} - cz_{10} \sin \beta \hat{\mathbf{z}}$	(4i)	Pr V

References

- [1] Q. Lin, K. Aguirre, S. M. Saunders, T. A. Hackett, Y. Liu, V. Taufour, D. Paudyal, S. Budko, P. C. Canfield, and G. J. Miller, *Polar Intermetallics $\text{Pr}_5\text{Co}_2\text{Ge}_3$ and $\text{Pr}_7\text{Co}_2\text{Ge}_4$ with Planar Hydrocarbon-Like Metal Clusters*, Chem. Europ. J. **23**, 10516–10521 (2017), doi:10.1002/chem.201702798.

Found in

- [1] L. Xiang, E. Gati, S. L. Bud'ko, S. M. Saunders, and P. C. Canfield, *Avoided ferromagnetic quantum critical point in pressurized $\text{La}_5\text{Co}_2\text{Ge}_3$* , Phys. Rev. B **103**, 054419 (2021), doi:10.1103/PhysRevB.103.054419.

First cited in

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.