

SrAu₃Al₂ Structure:


A2B3C_oP24_62_d_3c_c-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/DAG0>

https://aflow.org/prototype-encyclopedia/A2B3C_oP24_62_d_3c_c-001

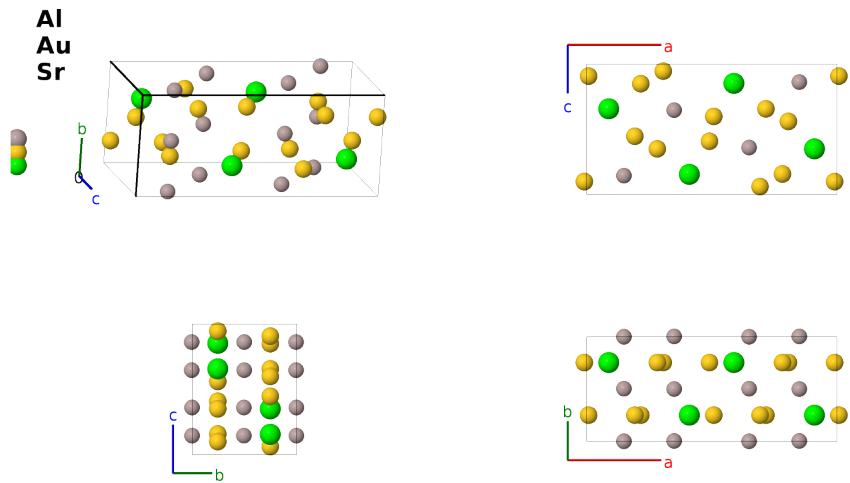

Prototype	Al ₂ Au ₃ Sr
AFLOW prototype label	A2B3C_oP24_62_d_3c_c-001
ICSD	429904
CCDC	1738321
Pearson symbol	oP24
Space group number	62
Space group symbol	<i>Pnma</i>
AFLOW prototype command	<code>aflow --proto=A2B3C_oP24_62_d_3c_c-001</code> <code>--params=a,b/a,c/a,x₁,z₁,x₂,z₂,x₃,z₃,x₄,z₄,x₅,y₅,z₅</code>


Other compounds with this structure

EuAu₃Al₂, RuAu₃Ga₂

- This is the ternary form of the SrZn₅ structure.

Simple Orthorhombic primitive vectors

$$\begin{aligned}
\mathbf{a}_1 &= a \hat{\mathbf{x}} \\
\mathbf{a}_2 &= b \hat{\mathbf{y}} \\
\mathbf{a}_3 &= c \hat{\mathbf{z}}
\end{aligned}$$

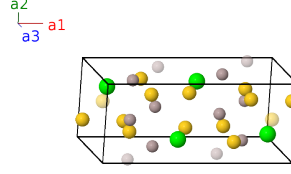

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(4c)	Au I
$\mathbf{B}_2$	$= -\left(x_1 - \frac{1}{2}\right) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \left(z_1 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_1 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c\left(z_1 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Au I
$\mathbf{B}_3$	$= -x_1 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_1 \hat{\mathbf{z}}$	(4c)	Au I
$\mathbf{B}_4$	$= \left(x_1 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_1 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_1 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c\left(z_1 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Au I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4c)	Au II
$\mathbf{B}_6$	$= -\left(x_2 - \frac{1}{2}\right) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \left(z_2 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_2 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c\left(z_2 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Au II
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4c)	Au II
$\mathbf{B}_8$	$= \left(x_2 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_2 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_2 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c\left(z_2 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Au II
$\mathbf{B}_9$	$= x_3 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(4c)	Au III
$\mathbf{B}_{10}$	$= -\left(x_3 - \frac{1}{2}\right) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \left(z_3 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_3 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c\left(z_3 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Au III
$\mathbf{B}_{11}$	$= -x_3 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(4c)	Au III
$\mathbf{B}_{12}$	$= \left(x_3 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_3 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_3 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c\left(z_3 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Au III
$\mathbf{B}_{13}$	$= x_4 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(4c)	Sr I
$\mathbf{B}_{14}$	$= -\left(x_4 - \frac{1}{2}\right) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \left(z_4 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_4 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c\left(z_4 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Sr I
$\mathbf{B}_{15}$	$= -x_4 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(4c)	Sr I
$\mathbf{B}_{16}$	$= \left(x_4 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_4 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_4 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c\left(z_4 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Sr I
$\mathbf{B}_{17}$	$= x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(8d)	Al I
$\mathbf{B}_{18}$	$= -\left(x_5 - \frac{1}{2}\right) \mathbf{a}_1 - y_5 \mathbf{a}_2 + \left(z_5 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_5 - \frac{1}{2}\right) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} + c\left(z_5 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8d)	Al I
$\mathbf{B}_{19}$	$= -x_5 \mathbf{a}_1 + \left(y_5 + \frac{1}{2}\right) \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} + b\left(y_5 + \frac{1}{2}\right) \hat{\mathbf{y}} - cz_5 \hat{\mathbf{z}}$	(8d)	Al I
$\mathbf{B}_{20}$	$= \left(x_5 + \frac{1}{2}\right) \mathbf{a}_1 - \left(y_5 - \frac{1}{2}\right) \mathbf{a}_2 - \left(z_5 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_5 + \frac{1}{2}\right) \hat{\mathbf{x}} - b\left(y_5 - \frac{1}{2}\right) \hat{\mathbf{y}} - c\left(z_5 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(8d)	Al I
$\mathbf{B}_{21}$	$= -x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} - cz_5 \hat{\mathbf{z}}$	(8d)	Al I
$\mathbf{B}_{22}$	$= \left(x_5 + \frac{1}{2}\right) \mathbf{a}_1 + y_5 \mathbf{a}_2 - \left(z_5 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_5 + \frac{1}{2}\right) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} - c\left(z_5 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(8d)	Al I
$\mathbf{B}_{23}$	$= x_5 \mathbf{a}_1 - \left(y_5 - \frac{1}{2}\right) \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} - b\left(y_5 - \frac{1}{2}\right) \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(8d)	Al I
$\mathbf{B}_{24}$	$= -\left(x_5 - \frac{1}{2}\right) \mathbf{a}_1 + \left(y_5 + \frac{1}{2}\right) \mathbf{a}_2 + \left(z_5 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_5 - \frac{1}{2}\right) \hat{\mathbf{x}} + b\left(y_5 + \frac{1}{2}\right) \hat{\mathbf{y}} + c\left(z_5 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8d)	Al I

References

- [1] B. Gerke and R. Pöttgen, *Alkaline earth-gold-aluminides: synthesis and structure of $SrAu_3Al_2$, $SrAu_{2.83}Al_{2.17}$, $BaAu_{2.89}Al_{2.11}$ and $BaAu_{7.09}Al_{5.91}$* , Z. Naturforsch. B **70**, 903–909 (2015), doi:10.1515/znb-2015-0119.

Found in

- [1] J.-P. Schmiegel, T. Block, B. Gerke, T. Fickenscher, R. S. Touzani, B. P. T. Fokwa, and O. Janka, *EuAu₃Al₂: Crystal and Electronic Structures and Spectroscopic, Magnetic, and Magnetocaloric Properties*, Inorg. Chem. **55**, 9057–9064 (2016), doi:10.1021/acs.inorgchem.6b01530.

First cited in

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.