


Room Temperature Ga₂Se₃ Structure: A2B3_mC20_9_2a_3a-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/4F67>

https://aflow.org/prototype-encyclopedia/A2B3_mC20_9_2a_3a-001

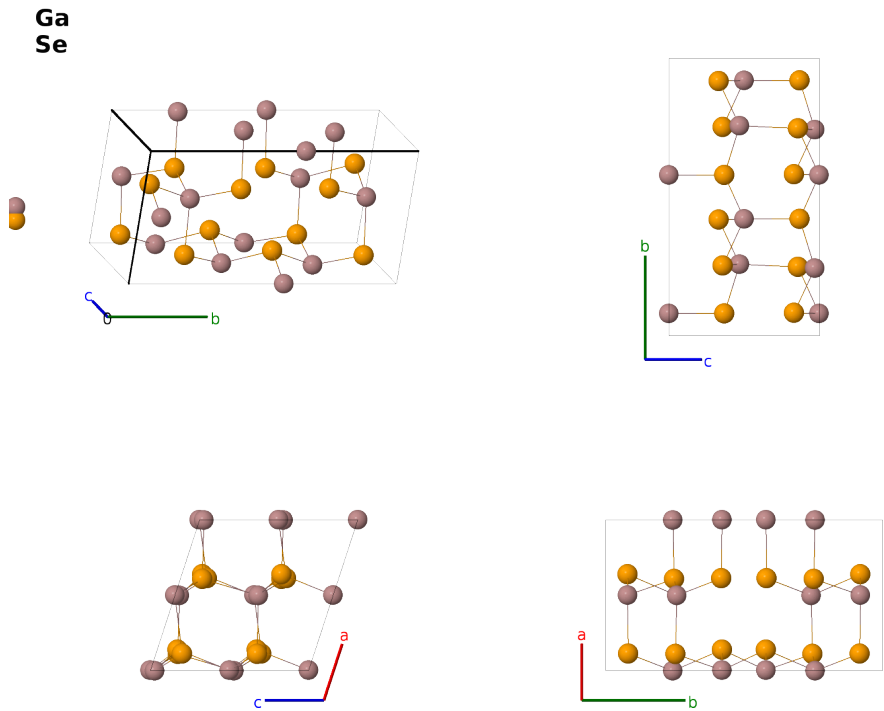


Prototype	Ga ₂ Se ₃
AFLOW prototype label	A2B3_mC20_9_2a_3a-001
ICSD	635356
CCDC	1756645
Pearson symbol	mC20
Space group number	9
Space group symbol	<i>Cc</i>
AFLOW prototype command	<code>aflow --proto=A2B3_mC20_9_2a_3a-001</code> <code>--params=a, b/a, c/a, β, $x_1, y_1, z_1, x_2, y_2, z_2, x_3, y_3, z_3, x_4, y_4, z_4, x_5, y_5, z_5$</code>

Other compounds with this structure
Ga₂S₃

- Above 645-694K (Villars, 2018) this structure transforms to the cubic zincblende (*B3*) phase, with vacancies on the gallium sites to adjust the symmetry (Lübbbers, 1982).
- (Ghémard, 1983) give this structure in the “unique axis-*c*” setting of space group #9. We used FINDSYM to transform this to the standard “unique axis-*b*” setting.

Base-centered Monoclinic primitive vectors

$$\begin{aligned}
\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\
\mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\
\mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}
\end{aligned}$$

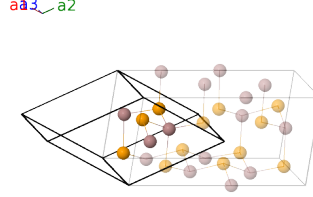

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$(x_1 - y_1) \mathbf{a}_1 + (x_1 + y_1) \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(4a)	Ga I
$\mathbf{B}_2$	$(x_1 + y_1) \mathbf{a}_1 + (x_1 - y_1) \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_1 + c(z_1 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4a)	Ga I
$\mathbf{B}_3$	$(x_2 - y_2) \mathbf{a}_1 + (x_2 + y_2) \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(4a)	Ga II
$\mathbf{B}_4$	$(x_2 + y_2) \mathbf{a}_1 + (x_2 - y_2) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4a)	Ga II
$\mathbf{B}_5$	$(x_3 - y_3) \mathbf{a}_1 + (x_3 + y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(4a)	Se I
$\mathbf{B}_6$	$(x_3 + y_3) \mathbf{a}_1 + (x_3 - y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4a)	Se I
$\mathbf{B}_7$	$(x_4 - y_4) \mathbf{a}_1 + (x_4 + y_4) \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(4a)	Se II
$\mathbf{B}_8$	$(x_4 + y_4) \mathbf{a}_1 + (x_4 - y_4) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4a)	Se II
$\mathbf{B}_9$	$(x_5 - y_5) \mathbf{a}_1 + (x_5 + y_5) \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(4a)	Se III
$\mathbf{B}_{10}$	$(x_5 + y_5) \mathbf{a}_1 + (x_5 - y_5) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_5 + c(z_5 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4a)	Se III

References

- [1] G. Ghémard, S. Jaulmes, J. Etienne, and J. Flahaut, *Structure de la phase ordonnée du sesquiséléniure de gallium, Ga₂Se₃*, Acta Crystallogr. Sect. C **39**, 968–971 (1983), doi:10.1107/S0108270183007039.
- [2] D. Lübbbers and V. Leute, *The Crystal Structure of β -Ga₂Se₃*, J. Solid State Chem. **43**, 339–345 (1982), doi:10.1016/0022-4596(82)90250-X.

Found in

- [1] P. Villars, H. Okamoto, and K. Cenzual, eds., *ASM Alloy Phase Diagram Database* (ASM International, 2018), chap. Gallium-Selenium Binary Phase Diagram (2008 Zheng F.). Copyright ©2006-2018 ASM International.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.