

Orthorhombic B₂O₃ Structure:


A2B3_oC20_36_b_ab-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/KLS9>

https://aflow.org/prototype-encyclopedia/A2B3_oC20_36_b_ab-001

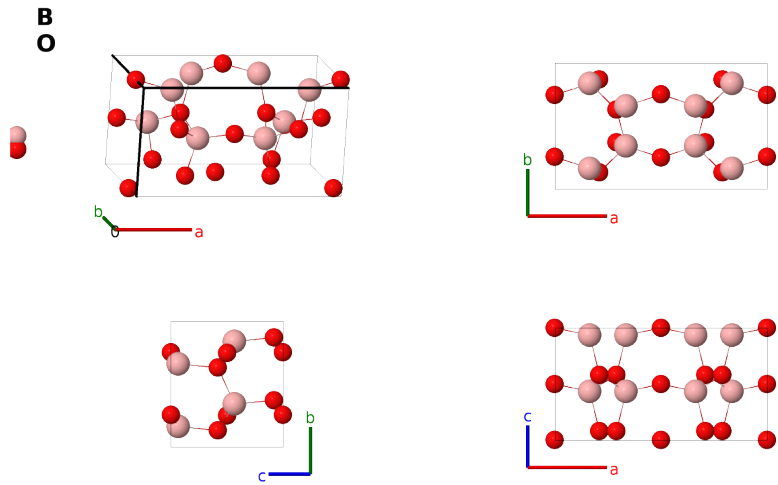


Prototype	B ₂ O ₃
AFLOW prototype label	A2B3_oC20_36_b_ab-001
ICSD	34685
CCDC	1607049
Pearson symbol	oC20
Space group number	36
Space group symbol	<i>Cmc</i> 2 ₁
AFLOW prototype command	<pre>aflow --proto=A2B3_oC20_36_b_ab-001 --params=a, b/a, c/a, y₁, z₁, x₂, y₂, z₂, x₃, y₃, z₃</pre>

- This is the high-pressure structure of B₂O₃, stable above ≈ 2 GPa. The ground state is trigonal.
- Data was taken a 6.5 GPa. (Prewitt, 1968) give the structure in the *Cmc*2₁ setting of space group #36. We used FINDSYM to transform it to the standard *Cmc*2₁ setting. This space group allows for an arbitrary placement of the origin of the *z*-axis, which we fixed by setting $z_1 = 0$ for the O-I (2a) Wyckoff position.
- The ICSD 34685 website entry for this structure states that it was refined at ambient pressure, but the data is consistent with the high-pressure structure shown here.

Base-centered Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

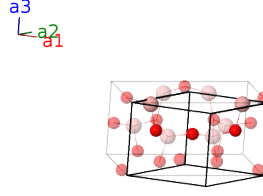

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= -y_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$by_1 \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(4a)	O I
$\mathbf{B}_2$	$= y_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-by_1 \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	O I
$\mathbf{B}_3$	$= (x_2 - y_2) \mathbf{a}_1 + (x_2 + y_2) \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(8b)	B I
$\mathbf{B}_4$	$= -(x_2 - y_2) \mathbf{a}_1 - (x_2 + y_2) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(8b)	B I
$\mathbf{B}_5$	$= (x_2 + y_2) \mathbf{a}_1 + (x_2 - y_2) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(8b)	B I
$\mathbf{B}_6$	$= -(x_2 + y_2) \mathbf{a}_1 - (x_2 - y_2) \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(8b)	B I
$\mathbf{B}_7$	$= (x_3 - y_3) \mathbf{a}_1 + (x_3 + y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(8b)	O II
$\mathbf{B}_8$	$= -(x_3 - y_3) \mathbf{a}_1 - (x_3 + y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(8b)	O II
$\mathbf{B}_9$	$= (x_3 + y_3) \mathbf{a}_1 + (x_3 - y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(8b)	O II
$\mathbf{B}_{10}$	$= -(x_3 + y_3) \mathbf{a}_1 - (x_3 - y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(8b)	O II

References

- [1] C. T. Prewitt and R. D. Shannon, *Crystal Structure of a High-Pressure Form of B_2O_3* , Acta Crystallogr. Sect. B **24**, 869–874 (1968), doi:10.1107/S0567740868003304.

Found in

- [1] H. Effenberger, C. L. Lengauer, and E. Parthé, *Trigonal B_2O_3 with Higher Space-Group Symmetry: Results of a Reevaluation*, Monatsh. Chem. **132**, 1515–1517 (2001), doi:10.1007/s007060170008.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.