

Rh₂O₃ Structure:

A2B3_oP20_60_d_cd-001


This structure previously used the label(s) **A2B3_oP20_60_d_cd**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/WEMD>

https://aflow.org/prototype-encyclopedia/A2B3_oP20_60_d_cd-001

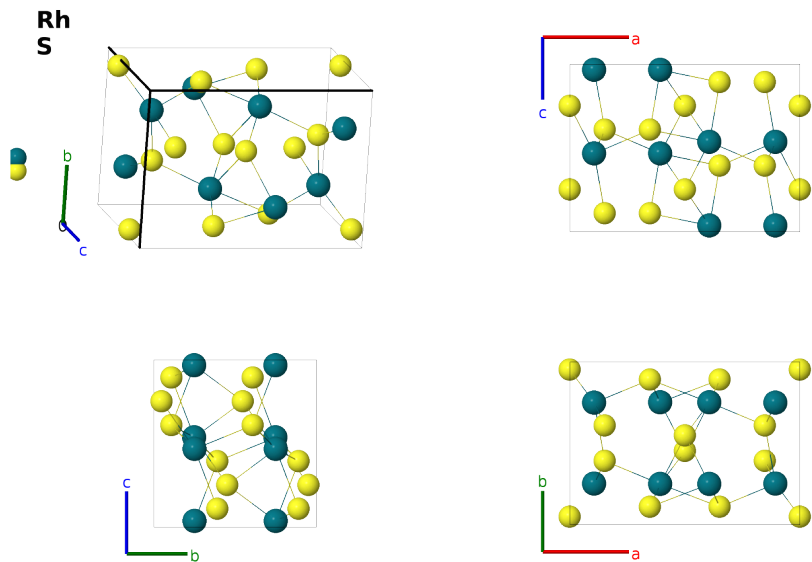

Prototype	Rh ₂ O ₃
AFLOW prototype label	A2B3_oP20_60_d_cd-001
ICSD	15344
CCDC	1596104
Pearson symbol	oP20
Space group number	60
Space group symbol	<i>Pbcn</i>
AFLOW prototype command	<code>aflow --proto=A2B3_oP20_60_d_cd-001</code> <code>--params=a, b/a, c/a, y₁, x₂, y₂, z₂, x₃, y₃, z₃</code>


Other compounds with this structure

Rh₂S₂Se, Rh₂SSe₂, Rh₂Se₃, Ir₂S₃

- (Villars, 2016) gives an incorrect link for the primary reference (Parthé, 1967). (Downs, 2003) has the correct reference.

Simple Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

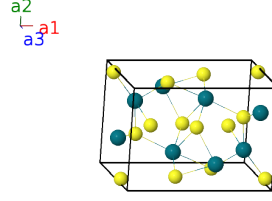

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= y_1 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$by_1 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B}_2$	$= \frac{1}{2} \mathbf{a}_1 - (y_1 - \frac{1}{2}) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - b(y_1 - \frac{1}{2}) \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B}_3$	$= -y_1 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-by_1 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B}_4$	$= \frac{1}{2} \mathbf{a}_1 + (y_1 + \frac{1}{2}) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + b(y_1 + \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(8d)	Rh I
$\mathbf{B}_6$	$= -(x_2 - \frac{1}{2}) \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} - b(y_2 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Rh I
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Rh I
$\mathbf{B}_8$	$= (x_2 + \frac{1}{2}) \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} - b(y_2 - \frac{1}{2}) \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(8d)	Rh I
$\mathbf{B}_9$	$= -x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(8d)	Rh I
$\mathbf{B}_{10}$	$= (x_2 + \frac{1}{2}) \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} + b(y_2 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Rh I
$\mathbf{B}_{11}$	$= x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Rh I
$\mathbf{B}_{12}$	$= -(x_2 - \frac{1}{2}) \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} + b(y_2 + \frac{1}{2}) \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(8d)	Rh I
$\mathbf{B}_{13}$	$= x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(8d)	S II
$\mathbf{B}_{14}$	$= -(x_3 - \frac{1}{2}) \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{2}) \hat{\mathbf{x}} - b(y_3 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	S II
$\mathbf{B}_{15}$	$= -x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	S II
$\mathbf{B}_{16}$	$= (x_3 + \frac{1}{2}) \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$a(x_3 + \frac{1}{2}) \hat{\mathbf{x}} - b(y_3 - \frac{1}{2}) \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(8d)	S II
$\mathbf{B}_{17}$	$= -x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(8d)	S II
$\mathbf{B}_{18}$	$= (x_3 + \frac{1}{2}) \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_3 + \frac{1}{2}) \hat{\mathbf{x}} + b(y_3 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	S II
$\mathbf{B}_{19}$	$= x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	S II
$\mathbf{B}_{20}$	$= -(x_3 - \frac{1}{2}) \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{2}) \hat{\mathbf{x}} + b(y_3 + \frac{1}{2}) \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(8d)	S II

References

- [1] E. Parthé, E. Hohnke, and F. Hulliger, *A new structure type with octahedron pairs for Rh_2S_3 , Rh_2Se_3 and Ir_2S_3* , Acta Cryst. **23**, 832–840 (1967), doi:10.1107/S0365110X67003767.

Found in

- [1] R. T. Downs and M. Hall-Wallace, *The American Mineralogist Crystal Structure Database*, Am. Mineral. **88**, 247–250 (2003).
- [2] P. Villars, *Rh₂S₃ orth Crystal Structure* (2016). PAULING FILE in: Inorganic Solid Phases, SpringerMaterials (online database), Springer, Heidelberg (ed.) SpringerMaterials.

First cited in

D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043