

Si₂U₃ (*D*5_{*a*}) Structure: A2B3_tP10_127_g_ah-001


This structure previously used the label(s) **A2B3_tP10_127_g_ah**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/6QGS>

https://aflow.org/prototype-encyclopedia/A2B3_tP10_127_g_ah-001

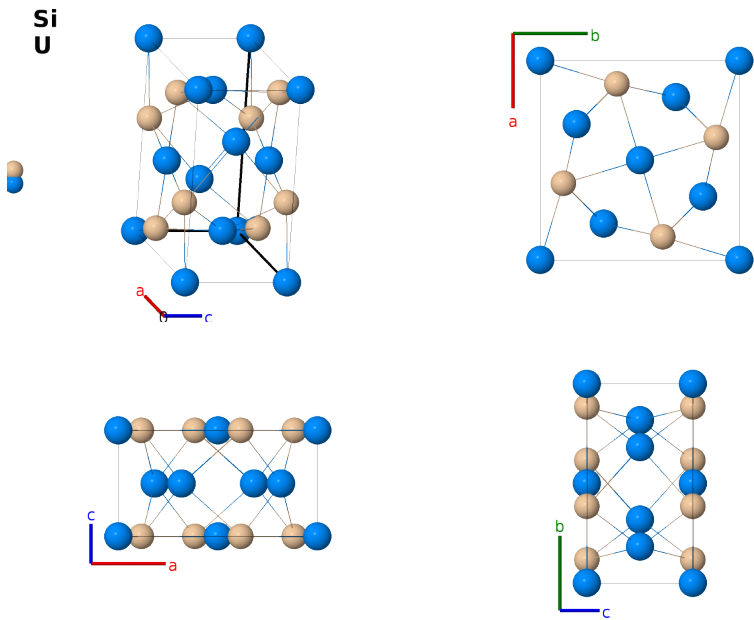


Prototype	Si ₂ U ₃
AFLOW prototype label	A2B3_tP10_127_g_ah-001
<i>Strukturbericht</i> designation	<i>D</i> 5 _{<i>a</i>}
ICSD	73695
CCDC	1634462
Pearson symbol	tP10
Space group number	127
Space group symbol	<i>P</i> 4/ <i>mbm</i>
AFLOW prototype command	<code>aflow --proto=A2B3_tP10_127_g_ah-001</code> <code>--params=<i>a</i>, <i>c/a</i>, <i>x</i>₂, <i>x</i>₃</code>

Other compounds with this structure

Ag₂Eu₃, Ag₂Yb₃, Al₂Th₃, Au₂La₃, Au₂Y₃, B₂Mo₃, B₂Nb₃, B₂Ta₃, B₂V₃, Be₂Nb₃, Be₂Ta₃, Ga₂Nb₃, Ga₂Ta₃, Ga₂Th₃, Ga₂Zr₃, Ge₂Hf₃, Ge₂Th₃, Hg₂Ca₃, Hg₂Sr₃, Pd₂Er₃, Pd₂Gd₃, Si₂Ce₃, Si₂Hf₃, Si₂La₃, Si₂Mo₃, Si₂Nb₃, Si₂Np₃, Si₂Pr₃, Si₂Pu₃, Si₂Th₃, Si₂U₃, Si₂W₃, Si₂Zr₃, Sr₂Pb₃, Al₂Th₃, B₂Mo₃, B₂Nb₃, B₂Ta₃, B₂V₃, Be₂Nb₃, Be₂Ta₃, Ga₂Nb₃, Ga₂Ta₃, Ga₂Zr₃, Ge₂Th₃, Pd₂Dy₃, Pd₂Ho₃, Si₂Hf₃, Si₂Th₃, Si₂Zr₃

- If we consider the Si₂ dimers as a pseudo-atom then this is a tetragonal distortion of the Cu₃Au (*L*₁₂) structure.
- Mo₂FeB₂ is the ternary form of this structure.
- We use the lattice constants taken by (Remsching, 1992) at 1200°C, while the ICSD entry uses what are apparently the room temperature values.

Simple Tetragonal primitive vectors

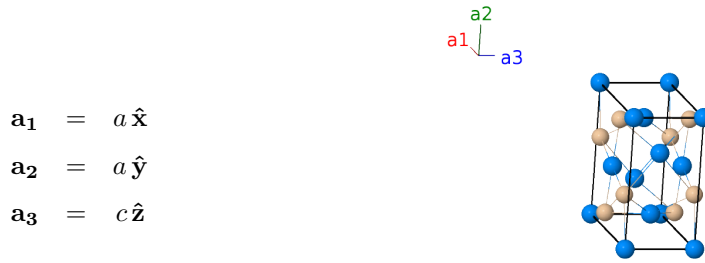

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	(2a) U I
$\mathbf{B}_2$	$=$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}}$	(2a) U I
$\mathbf{B}_3$	$=$	$x_2 \mathbf{a}_1 + (x_2 + \frac{1}{2}) \mathbf{a}_2$	$=$	$ax_2 \hat{\mathbf{x}} + a(x_2 + \frac{1}{2}) \hat{\mathbf{y}}$	(4g) Si I
$\mathbf{B}_4$	$=$	$-x_2 \mathbf{a}_1 - (x_2 - \frac{1}{2}) \mathbf{a}_2$	$=$	$-ax_2 \hat{\mathbf{x}} - a(x_2 - \frac{1}{2}) \hat{\mathbf{y}}$	(4g) Si I
$\mathbf{B}_5$	$=$	$-(x_2 - \frac{1}{2}) \mathbf{a}_1 + x_2 \mathbf{a}_2$	$=$	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} + ax_2 \hat{\mathbf{y}}$	(4g) Si I
$\mathbf{B}_6$	$=$	$(x_2 + \frac{1}{2}) \mathbf{a}_1 - x_2 \mathbf{a}_2$	$=$	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} - ax_2 \hat{\mathbf{y}}$	(4g) Si I
$\mathbf{B}_7$	$=$	$x_3 \mathbf{a}_1 + (x_3 + \frac{1}{2}) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + a(x_3 + \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(4h) U II
$\mathbf{B}_8$	$=$	$-x_3 \mathbf{a}_1 - (x_3 - \frac{1}{2}) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} - a(x_3 - \frac{1}{2}) \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(4h) U II
$\mathbf{B}_9$	$=$	$-(x_3 - \frac{1}{2}) \mathbf{a}_1 + x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{2}) \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(4h) U II
$\mathbf{B}_{10}$	$=$	$(x_3 + \frac{1}{2}) \mathbf{a}_1 - x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$a(x_3 + \frac{1}{2}) \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	(4h) U II

References

- [1] K. Remschnig, T. L. Bihan, H. Noël, and P. Rogl, *Structural chemistry and magnetic behavior of binary uranium silicides*, J. Solid State Chem. **97**, 391–399 (1992), doi:10.1016/0022-4596(92)90048-Z.

Found in

- [1] P. Villars, K. Cenzual, R. Gladyshevskii, O. Shcherban, V. Dubenskyy, V. Kuprysyuk, I. Savesyuk, and R. Zaremba, *Landolt-Börnstein - Group III Condensed Matter* (2012). URL http://materials.springer.com/lb/docs/sm_lbs_978-3-642-22847-6_359.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017