

Rh₃P₂ Structure:

A2B3_tP5_115_g_ag-001


This structure previously used the label(s) **A2B3_tP5_115_g_ag**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/EXDQ>

https://aflow.org/prototype-encyclopedia/A2B3_tP5_115_g_ag-001

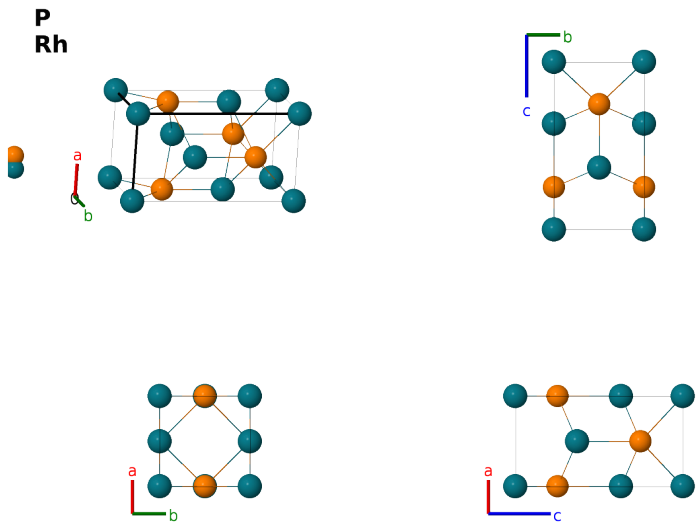


Prototype	P ₂ Rh ₃
AFLOW prototype label	A2B3_tP5_115_g_ag-001
ICSD	35626
CCDC	1607673
Pearson symbol	tP5
Space group number	115
Space group symbol	$P\bar{4}m2$
AFLOW prototype command	<code>aflow --proto=A2B3_tP5_115_g_ag-001</code> <code>--params=a, c/a, z₂, z₃</code>

Simple Tetragonal primitive vectors



$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	(1a) Rh I
$\mathbf{B}_2$	$=$	$\frac{1}{2} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(2g) P I
$\mathbf{B}_3$	$=$	$\frac{1}{2} \mathbf{a}_1 - z_2 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} - cz_2 \hat{\mathbf{z}}$	(2g) P I
$\mathbf{B}_4$	$=$	$\frac{1}{2} \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(2g) Rh II
$\mathbf{B}_5$	$=$	$\frac{1}{2} \mathbf{a}_1 - z_3 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} - cz_3 \hat{\mathbf{z}}$	(2g) Rh II

References

- [1] E. H. E. Ghadraoui, R. Guerin, and M. Sergent, *Diphosphure de trirhodium, Rh_3P_2 : premier exemple d'une structure lacunaire ordonnée de type anti- $PbFCl$* , Acta Crystallogr. Sect. C **39**, 1493–1494 (1983), doi:10.1107/S0108270183009002.

Found in

- [1] P. Villars and K. Cenzual, *Pearson's Crystal Data – Crystal Structure Database for Inorganic Compounds* (2013). ASM International.

First cited in

D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043