

Gd₂SiO₅ (RE₂SiO₅ X1) Structure: A2B5C_mP32_14_2e_5e_e-001


This structure previously used the label(s) **A2B5C_mP32_14_2e_5e_e**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/HBLG>

https://aflow.org/prototype-encyclopedia/A2B5C_mP32_14_2e_5e_e-001

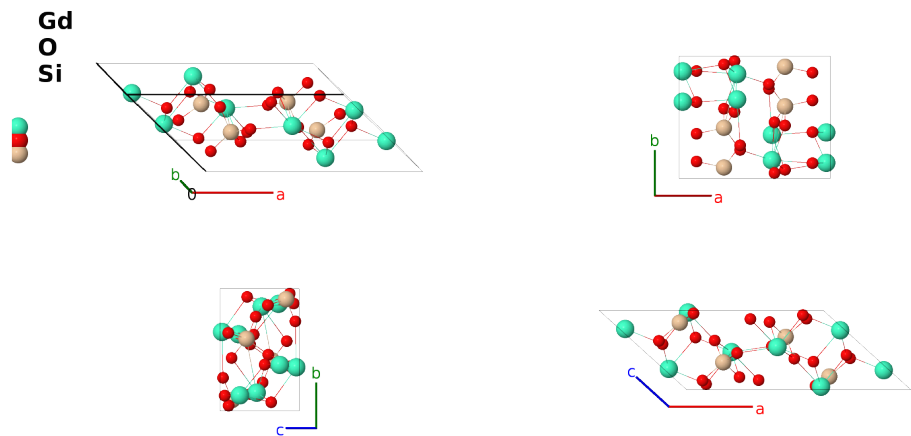

Prototype	Gd ₂ O ₅ Si
AFLOW prototype label	A2B5C_mP32_14_2e_5e_e-001
ICSD	154796
CCDC	1671419
Pearson symbol	mP32
Space group number	14
Space group symbol	$P2_1/c$
AFLOW prototype command	<pre>aflow --proto=A2B5C_mP32_14_2e_5e_e-001 --params=a,b/a,c/a,β,x₁,y₁,z₁,x₂,y₂,z₂,x₃,y₃,z₃,x₄,y₄,z₄,x₅,y₅,z₅,x₆,y₆,z₆,x₇,y₇,z₇,x₈,y₈,z₈</pre>

Other compounds with this structure


Dy₂SiO₅, La₂SiO₅, Tb₂SiO₅, Y₂SiO₅

- Compounds of the form RE₂SiO₅ (RE = Rare Earth and related elements) crystallize in one of two forms (Wang, 2001 and Tian, 2016):
- X1, shown here, for rare earths between lanthanum and gadolinium, and

- X2, space group $C2/c$ #15 for the later rare earths, with the dysprosium, yttrium and ytterbium compounds existing in both structures.
- The ICSD entry is from the later work of (Dramićanin, 2006).

Simple Monoclinic primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}} \end{aligned}$$

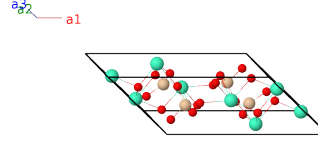

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	Gd I
$\mathbf{B}_2$	$= -x_1 \mathbf{a}_1 + (y_1 + \frac{1}{2}) \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_1 + c(z_1 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_1 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Gd I
$\mathbf{B}_3$	$= -x_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} - cz_1 \sin \beta \hat{\mathbf{z}}$	(4e)	Gd I
$\mathbf{B}_4$	$= x_1 \mathbf{a}_1 - (y_1 - \frac{1}{2}) \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_1 + c(z_1 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_1 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Gd I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	Gd II
$\mathbf{B}_6$	$= -x_2 \mathbf{a}_1 + (y_2 + \frac{1}{2}) \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_2 + c(z_2 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_2 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Gd II
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(4e)	Gd II
$\mathbf{B}_8$	$= x_2 \mathbf{a}_1 - (y_2 - \frac{1}{2}) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_2 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	Gd II
$\mathbf{B}_9$	$= x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	O I
$\mathbf{B}_{10}$	$= -x_3 \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_3 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O I
$\mathbf{B}_{11}$	$= -x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(4e)	O I
$\mathbf{B}_{12}$	$= x_3 \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_3 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O I
$\mathbf{B}_{13}$	$= x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(4e)	O II
$\mathbf{B}_{14}$	$= -x_4 \mathbf{a}_1 + (y_4 + \frac{1}{2}) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_4 + c(z_4 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_4 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O II
$\mathbf{B}_{15}$	$= -x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(4e)	O II
$\mathbf{B}_{16}$	$= x_4 \mathbf{a}_1 - (y_4 - \frac{1}{2}) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_4 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O II
$\mathbf{B}_{17}$	$= x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(4e)	O III
$\mathbf{B}_{18}$	$= -x_5 \mathbf{a}_1 + (y_5 + \frac{1}{2}) \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_5 + c(z_5 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + b(y_5 + \frac{1}{2}) \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O III
$\mathbf{B}_{19}$	$= -x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} - cz_5 \sin \beta \hat{\mathbf{z}}$	(4e)	O III
$\mathbf{B}_{20}$	$= x_5 \mathbf{a}_1 - (y_5 - \frac{1}{2}) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_5 + c(z_5 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - b(y_5 - \frac{1}{2}) \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(4e)	O III

$$\begin{aligned}
\mathbf{B}_{21} &= x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 + z_6 \mathbf{a}_3 &= (ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}} &(4e) &\text{O IV} \\
\mathbf{B}_{22} &= -x_6 \mathbf{a}_1 + \left(y_6 + \frac{1}{2}\right) \mathbf{a}_2 - \left(z_6 - \frac{1}{2}\right) \mathbf{a}_3 &= -\left(ax_6 + c\left(z_6 - \frac{1}{2}\right) \cos \beta\right) \hat{\mathbf{x}} + b\left(y_6 + \frac{1}{2}\right) \hat{\mathbf{y}} - c\left(z_6 - \frac{1}{2}\right) \sin \beta \hat{\mathbf{z}} &(4e) &\text{O IV} \\
\mathbf{B}_{23} &= -x_6 \mathbf{a}_1 - y_6 \mathbf{a}_2 - z_6 \mathbf{a}_3 &= -(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} - cz_6 \sin \beta \hat{\mathbf{z}} &(4e) &\text{O IV} \\
\mathbf{B}_{24} &= x_6 \mathbf{a}_1 - \left(y_6 - \frac{1}{2}\right) \mathbf{a}_2 + \left(z_6 + \frac{1}{2}\right) \mathbf{a}_3 &= \left(ax_6 + c\left(z_6 + \frac{1}{2}\right) \cos \beta\right) \hat{\mathbf{x}} - b\left(y_6 - \frac{1}{2}\right) \hat{\mathbf{y}} + c\left(z_6 + \frac{1}{2}\right) \sin \beta \hat{\mathbf{z}} &(4e) &\text{O IV} \\
\mathbf{B}_{25} &= x_7 \mathbf{a}_1 + y_7 \mathbf{a}_2 + z_7 \mathbf{a}_3 &= (ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \sin \beta \hat{\mathbf{z}} &(4e) &\text{O V} \\
\mathbf{B}_{26} &= -x_7 \mathbf{a}_1 + \left(y_7 + \frac{1}{2}\right) \mathbf{a}_2 - \left(z_7 - \frac{1}{2}\right) \mathbf{a}_3 &= -\left(ax_7 + c\left(z_7 - \frac{1}{2}\right) \cos \beta\right) \hat{\mathbf{x}} + b\left(y_7 + \frac{1}{2}\right) \hat{\mathbf{y}} - c\left(z_7 - \frac{1}{2}\right) \sin \beta \hat{\mathbf{z}} &(4e) &\text{O V} \\
\mathbf{B}_{27} &= -x_7 \mathbf{a}_1 - y_7 \mathbf{a}_2 - z_7 \mathbf{a}_3 &= -(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} - cz_7 \sin \beta \hat{\mathbf{z}} &(4e) &\text{O V} \\
\mathbf{B}_{28} &= x_7 \mathbf{a}_1 - \left(y_7 - \frac{1}{2}\right) \mathbf{a}_2 + \left(z_7 + \frac{1}{2}\right) \mathbf{a}_3 &= \left(ax_7 + c\left(z_7 + \frac{1}{2}\right) \cos \beta\right) \hat{\mathbf{x}} - b\left(y_7 - \frac{1}{2}\right) \hat{\mathbf{y}} + c\left(z_7 + \frac{1}{2}\right) \sin \beta \hat{\mathbf{z}} &(4e) &\text{O V} \\
\mathbf{B}_{29} &= x_8 \mathbf{a}_1 + y_8 \mathbf{a}_2 + z_8 \mathbf{a}_3 &= (ax_8 + cz_8 \cos \beta) \hat{\mathbf{x}} + by_8 \hat{\mathbf{y}} + cz_8 \sin \beta \hat{\mathbf{z}} &(4e) &\text{Si I} \\
\mathbf{B}_{30} &= -x_8 \mathbf{a}_1 + \left(y_8 + \frac{1}{2}\right) \mathbf{a}_2 - \left(z_8 - \frac{1}{2}\right) \mathbf{a}_3 &= -\left(ax_8 + c\left(z_8 - \frac{1}{2}\right) \cos \beta\right) \hat{\mathbf{x}} + b\left(y_8 + \frac{1}{2}\right) \hat{\mathbf{y}} - c\left(z_8 - \frac{1}{2}\right) \sin \beta \hat{\mathbf{z}} &(4e) &\text{Si I} \\
\mathbf{B}_{31} &= -x_8 \mathbf{a}_1 - y_8 \mathbf{a}_2 - z_8 \mathbf{a}_3 &= -(ax_8 + cz_8 \cos \beta) \hat{\mathbf{x}} - by_8 \hat{\mathbf{y}} - cz_8 \sin \beta \hat{\mathbf{z}} &(4e) &\text{Si I} \\
\mathbf{B}_{32} &= x_8 \mathbf{a}_1 - \left(y_8 - \frac{1}{2}\right) \mathbf{a}_2 + \left(z_8 + \frac{1}{2}\right) \mathbf{a}_3 &= \left(ax_8 + c\left(z_8 + \frac{1}{2}\right) \cos \beta\right) \hat{\mathbf{x}} - b\left(y_8 - \frac{1}{2}\right) \hat{\mathbf{y}} + c\left(z_8 + \frac{1}{2}\right) \sin \beta \hat{\mathbf{z}} &(4e) &\text{Si I}
\end{aligned}$$

References

- [1] G. V. Anan'eva, A. M. Korovkin, T. I. Merkulyaeva, A. M. Morozova, M. V. Petrov, I. R. Savinova, V. R. Startsev, and P. P. Feofilov, *Growth of lanthanide oxyorthosilicate single crystals, and their structural and optical characteristics*, Inorg. Mater. **17**, 754–758 (1981). Translated from *Neorganicheskie Materialy*.
- [2] J. Wang, S. Tian, G. Li, F. Liao, and X. Jing, *Preparation and X-ray characterization of low-temperature phases of $R_2\text{SiO}_5$ (R = rare earth elements)*, Mater. Res. Bull. **36**, 1855–1861 (2001), doi:10.1016/S0025-5408(01)00664-X.
- [3] Z. Tian, L. Zheng, J. Wang, P. Wan, J. Li, and J. Wang, *Theoretical and experimental determination of the major thermo-mechanical properties of RE_2SiO_5 ($\text{RE} = \text{Tb, Dy, Ho, Er, Tm, Yb, Lu, and Y}$) for environmental and thermal barrier coating applications*, J. Am. Ceram. Soc. **36**, 189–202 (2016), doi:10.1016/j.jeurceramsoc.2015.09.013.
- [4] C. Michel, G. Buisson, and E. F. Bertaut, *Structure de Y_2SiO_5* , Compt. Rend. B: Sci. Phys. **264**, 397–399 (1967).
- [5] M. D. Dramićanin, V. Jokanović, B. Viana, E. Antic-Fidancev, M. Mitrić, and ž. Andrić, *Luminescence and structural properties of $\text{Gd}_2\text{SiO}_5:\text{Eu}^{3+}$ nanophosphors synthesized from the hydrothermal obtained silica sol*, Journal of Alloys and Compounds **424**, 213–217 (2006), doi:10.1016/j.jallcom.2005.10.086.

Found in

- [1] P. Villars, *Gd₂SiO₅ (Gd₂[SiO₄]O) Crystal Structure* (2016). PAULING FILE in: Inorganic Solid Phases, SpringerMaterials (online database), Springer, Heidelberg (ed.) SpringerMaterials.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.