

B₂Pd₅ Structure: A2B5_mC28_15_f_e2f-001


This structure previously used the label(s) **A2B5_mC28_15_f_e2f**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/CZ5K>

https://aflow.org/prototype-encyclopedia/A2B5_mC28_15_f_e2f-001

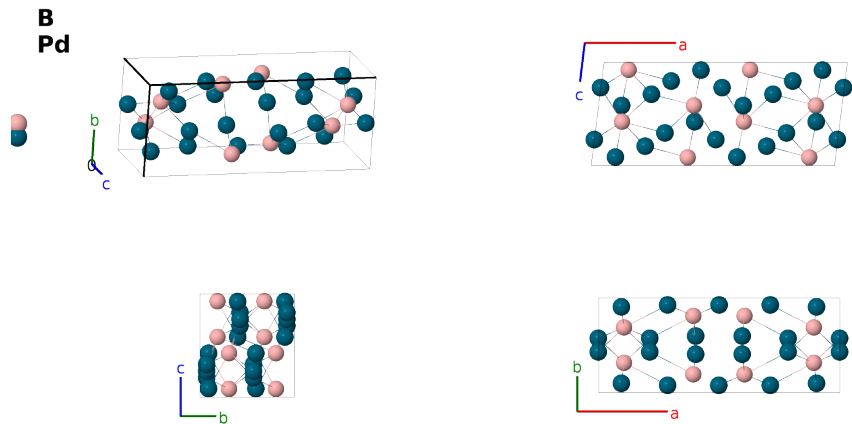

Prototype	B ₂ Pd ₅
AFLOW prototype label	A2B5_mC28_15_f_e2f-001
ICSD	43513
CCDC	1612997
Pearson symbol	mC28
Space group number	15
Space group symbol	<i>C</i> 2/ <i>c</i>
AFLOW prototype command	<code>aflow --proto=A2B5_mC28_15_f_e2f-001</code> <code>--params=a, b/a, c/a, β, y_1, x_2, y_2, z_2, x_3, y_3, z_3, x_4, y_4, z_4</code>

Other compounds with this structure


Au₂Ca₅, C₂Fe₅, C₂Mn₅, Co₂Nd₅, Co₂Pr₅, Co₂Sm₅, Ir₂Dy₅, Ir₂Er₅, Ir₂Gd₅, Ir₂Ho₅, Ir₂La₅, Ir₂Lu₅, Ir₂Nd₅, Ir₂Pr₅, Ir₂Sm₅, Ir₂Tb₅, Ir₂Tm₅, Ir₂Y₅, Pd₂Ca₅, Pd₂Eu₅, Pd₂Yb₅, Pt₂Ca₅, Pt₂Eu₅, Pt₂Yb₅, Rh₂Er₅, Rh₂Eu₅, Rh₂La₅, Rh₂Nd₅, Rh₂Sm₅, Ru₂Dy₅, Ru₂Er₅, Ru₂Gd₅, Ru₂Ho₅, Ru₂La₅, Ru₂Lu₅, Ru₂Nd₅, Ru₂Pr₅, Ru₂Sm₅, Ru₂Tb₅, Ru₂Tm₅, Ru₂Y₅

- Although the earliest entry in the ICSD for this structure refers to B₂Pd₅, they designate C₂Mn₅ as the prototype for this system.
- The ICSD lists Sm₂ScCl₄ under this structure, but we find the two forms sufficiently different to justify listing that as a new prototype.

- B_2Pd_5 and Nb_2O_5 share the same AFLOW prototype label, A2B5_mC28_15_f_e2f, but have substantially different environments around each atom. The structures are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Base-centered Monoclinic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}\end{aligned}$$

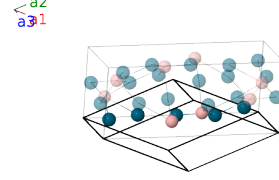

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= -y_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \cos \beta \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + \frac{1}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Pd I
$\mathbf{B}_2$	$= y_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \cos \beta \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} + \frac{3}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Pd I
$\mathbf{B}_3$	$= (x_2 - y_2) \mathbf{a}_1 + (x_2 + y_2) \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(8f)	B I
$\mathbf{B}_4$	$= -(x_2 + y_2) \mathbf{a}_1 - (x_2 - y_2) \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_2 + c(z_2 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	B I
$\mathbf{B}_5$	$= -(x_2 - y_2) \mathbf{a}_1 - (x_2 + y_2) \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(8f)	B I
$\mathbf{B}_6$	$= (x_2 + y_2) \mathbf{a}_1 + (x_2 - y_2) \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	B I
$\mathbf{B}_7$	$= (x_3 - y_3) \mathbf{a}_1 + (x_3 + y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	Pd II
$\mathbf{B}_8$	$= -(x_3 + y_3) \mathbf{a}_1 - (x_3 - y_3) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_3 + c(z_3 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Pd II
$\mathbf{B}_9$	$= -(x_3 - y_3) \mathbf{a}_1 - (x_3 + y_3) \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(8f)	Pd II
$\mathbf{B}_{10}$	$= (x_3 + y_3) \mathbf{a}_1 + (x_3 - y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Pd II
$\mathbf{B}_{11}$	$= (x_4 - y_4) \mathbf{a}_1 + (x_4 + y_4) \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	Pd III
$\mathbf{B}_{12}$	$= -(x_4 + y_4) \mathbf{a}_1 - (x_4 - y_4) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_4 + c(z_4 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Pd III
$\mathbf{B}_{13}$	$= -(x_4 - y_4) \mathbf{a}_1 - (x_4 + y_4) \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(8f)	Pd III
$\mathbf{B}_{14}$	$= (x_4 + y_4) \mathbf{a}_1 + (x_4 - y_4) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Pd III

References

- [1] E. Stenberg, *The Crystal Structures of Pd_5B_2 , (Mn_5C_2) , and Pd_3B* , Acta Chem. Scand. **15**, 861–870 (1961), doi:10.3891/acta.chem.scand.15-0861.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017