

Brucite [Mg(OH)₂] Structure: A2BC2_hP5_164_d_a_d-001


This structure previously used the label(s) **A2BC2_hP5_164_d_a_d**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/N2MR>

https://aflow.org/prototype-encyclopedia/A2BC2_hP5_164_d_a_d-001

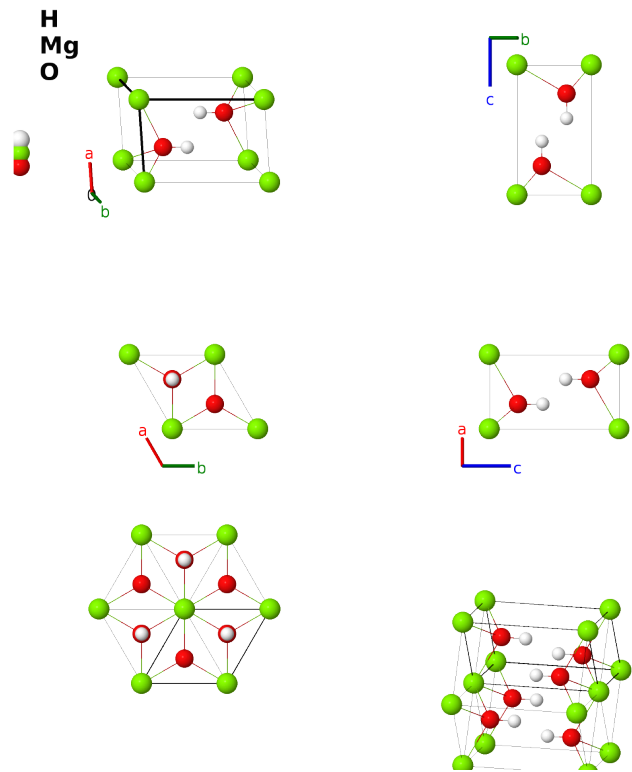


Prototype	H ₂ MgO ₂
AFLOW prototype label	A2BC2_hP5_164_d_a_d-001
Mineral name	brucite
ICSD	79031
CCDC	1639294
Pearson symbol	hP5
Space group number	164
Space group symbol	$P\bar{3}m1$
AFLOW prototype command	<code>aflow --proto=A2BC2_hP5_164_d_a_d-001 --params=a, c/a, z₂, z₃</code>

Other compounds with this structure

Ca(OH)₂ (Portlandite), Fe(OH)₂, Mn(OH)₂ (Pyrochroite), Ni(OH)₂ (Theophrastite), β -Co(OH)₂

- We used the data from (Catti, 1995) at ambient pressure. In some Brucite-like materials the hydrogen atoms are displaced to the (6i) Wyckoff positions $(x, -x, z)$ of space group $P3m1$ #164, and these sites are 1/3 occupied.
-

Trigonal (Hexagonal) primitive vectors
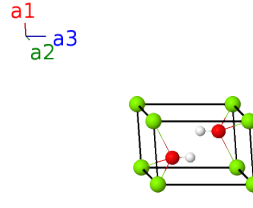
$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a\hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a\hat{\mathbf{y}} \\ \mathbf{a}_3 &= c\hat{\mathbf{z}}\end{aligned}$$


Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	=	0	=	0	(1a) Mg I
$\mathbf{B}_2$	=	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_2\mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + cz_2\hat{\mathbf{z}}$	(2d) H I
$\mathbf{B}_3$	=	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 - z_2\mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} - cz_2\hat{\mathbf{z}}$	(2d) H I
$\mathbf{B}_4$	=	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_3\mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + cz_3\hat{\mathbf{z}}$	(2d) O I
$\mathbf{B}_5$	=	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 - z_3\mathbf{a}_3$	=	$\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} - cz_3\hat{\mathbf{z}}$	(2d) O I

References

- [1] M. Catti, G. Ferraris, S. Hull, and A. Pavese, *Static compression and H disorder in brucite, Mg(OH)₂, to 11 GPa: a powder neutron diffraction study*, Phys. Chem. Min. **22**, 200–206 (1995), doi:10.1007/BF00202300.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.