

MnGa₂Sb₂ Structure:

A2BC2_oI20_45_c_a_c-001


This structure previously used the label(s) **A2BC2.oI20_45.c.b.c**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/LNLG>

https://aflow.org/prototype-encyclopedia/A2BC2_oI20_45_c_a_c-001

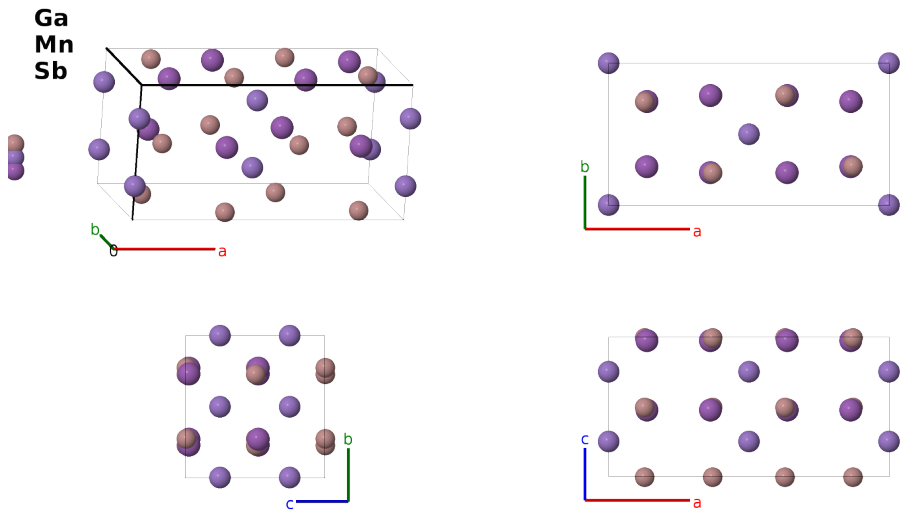


Prototype	Ga ₂ MnSb ₂
AFLOW prototype label	A2BC2_oI20_45_c_a_c-001
Pearson symbol	oI20
Space group number	45
Space group symbol	Iba2
AFLOW prototype command	<code>aflow --proto=A2BC2_oI20_45_c_a_c-001</code> <code>--params=a, b/a, c/a, z₁, x₂, y₂, z₂, x₃, y₃, z₃</code>

- The Mn site has an occupation of 0.9365.
- We shifted the origin so that the Mn atom is at the (4a) site rather than the (4b) site.

Body-centered Orthorhombic primitive vectors

$$\begin{aligned}
\mathbf{a}_1 &= -\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\
\mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\
\mathbf{a}_3 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} - \frac{1}{2}c \hat{\mathbf{z}}
\end{aligned}$$

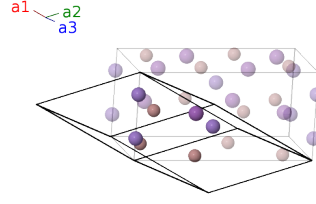

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= z_1 \mathbf{a}_1 + z_1 \mathbf{a}_2$	$=$	$c z_1 \hat{\mathbf{z}}$	(4a)	Mn I
$\mathbf{B}_2$	$= \left(z_1 + \frac{1}{2}\right) \mathbf{a}_1 + \left(z_1 + \frac{1}{2}\right) \mathbf{a}_2$	$=$	$c \left(z_1 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4a)	Mn I
$\mathbf{B}_3$	$= (y_2 + z_2) \mathbf{a}_1 + (x_2 + z_2) \mathbf{a}_2 + (x_2 + y_2) \mathbf{a}_3$	$=$	$a x_2 \hat{\mathbf{x}} + b y_2 \hat{\mathbf{y}} + c z_2 \hat{\mathbf{z}}$	(8c)	Ga I
$\mathbf{B}_4$	$= -(y_2 - z_2) \mathbf{a}_1 - (x_2 - z_2) \mathbf{a}_2 - (x_2 + y_2) \mathbf{a}_3$	$=$	$-a x_2 \hat{\mathbf{x}} - b y_2 \hat{\mathbf{y}} + c z_2 \hat{\mathbf{z}}$	(8c)	Ga I
$\mathbf{B}_5$	$= \left(-y_2 + z_2 + \frac{1}{2}\right) \mathbf{a}_1 + \left(x_2 + z_2 + \frac{1}{2}\right) \mathbf{a}_2 + (x_2 - y_2) \mathbf{a}_3$	$=$	$a x_2 \hat{\mathbf{x}} - b y_2 \hat{\mathbf{y}} + c \left(z_2 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8c)	Ga I
$\mathbf{B}_6$	$= \left(y_2 + z_2 + \frac{1}{2}\right) \mathbf{a}_1 + \left(-x_2 + z_2 + \frac{1}{2}\right) \mathbf{a}_2 - (x_2 - y_2) \mathbf{a}_3$	$=$	$-a x_2 \hat{\mathbf{x}} + b y_2 \hat{\mathbf{y}} + c \left(z_2 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8c)	Ga I
$\mathbf{B}_7$	$= (y_3 + z_3) \mathbf{a}_1 + (x_3 + z_3) \mathbf{a}_2 + (x_3 + y_3) \mathbf{a}_3$	$=$	$a x_3 \hat{\mathbf{x}} + b y_3 \hat{\mathbf{y}} + c z_3 \hat{\mathbf{z}}$	(8c)	Sb I
$\mathbf{B}_8$	$= -(y_3 - z_3) \mathbf{a}_1 - (x_3 - z_3) \mathbf{a}_2 - (x_3 + y_3) \mathbf{a}_3$	$=$	$-a x_3 \hat{\mathbf{x}} - b y_3 \hat{\mathbf{y}} + c z_3 \hat{\mathbf{z}}$	(8c)	Sb I
$\mathbf{B}_9$	$= \left(-y_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_1 + \left(x_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_2 + (x_3 - y_3) \mathbf{a}_3$	$=$	$a x_3 \hat{\mathbf{x}} - b y_3 \hat{\mathbf{y}} + c \left(z_3 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8c)	Sb I
$\mathbf{B}_{10}$	$= \left(y_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_1 + \left(-x_3 + z_3 + \frac{1}{2}\right) \mathbf{a}_2 - (x_3 - y_3) \mathbf{a}_3$	$=$	$-a x_3 \hat{\mathbf{x}} + b y_3 \hat{\mathbf{y}} + c \left(z_3 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8c)	Sb I

References

- [1] W. Sakakibara, Y. Hayashi, and H. Takizawa, *MnGa₂Sb₂, a new ferromagnetic compound synthesized under high pressure*, J. Ceram. Soc. Jpn. **117**, 72–75 (2009), doi:10.2109/jcersj2.117.72.

Found in

- [1] P. Villars and K. Cenzual, *Pearson's Crystal Data – Crystal Structure Database for Inorganic Compounds* (2013). ASM International.

First cited in

D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043