

Mo₂FeB₂ Structure:


A2BC2_tP10_127_g_a_h-002

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/5SWM>

https://aflow.org/prototype-encyclopedia/A2BC2_tP10_127_g_a_h-002

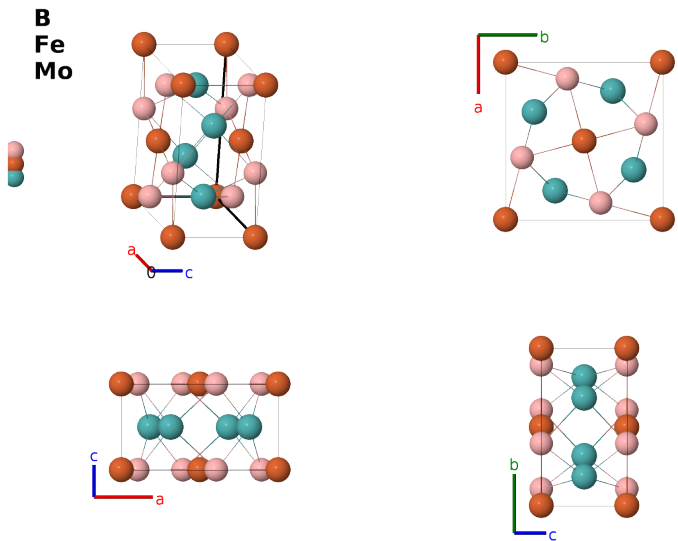

Prototype	B ₂ FeMo ₂
AFLOW prototype label	A2BC2_tP10_127_g_a_h-002
ICSD	5431
CCDC	1593493
Pearson symbol	tP10
Space group number	127
Space group symbol	<i>P4/mbm</i>
AFLOW prototype command	<code>aflow --proto=A2BC2_tP10_127_g_a_h-002 --params=a, c/a, x₂, x₃</code>

Other compounds with this structure


Al₂CrB₂, Al₂FeB₂, Al₂NiB₂, Ce₂InPd₂, Dy₂CdPd₂, Dy₂InPd₂, Er₂CdPd₂, Er₂InPd₂, Gd₂CdPd₂, Gd₂InPd₂, Ho₂CdPd₂, Ho₂InPd₂, La₂InCu₂, La₂InPd₂, Lu₂CdPd₂, Lu₂InPd₂, Mo₂CrB₂, Mo₂NiB₂, Nb₂FeB₂, Nd₂InPd₂, Ni₂SnZr₂, Pr₂CdPd₂, Pr₂InPd₂, Sm₂CdPd₂, Sm₂InPd₂, Ta₂FeB₂, Tb₂CdPd₂, Tb₂InPd₂, Th₂InPd₂, Ti₂CrB₂, Ti₂FeB₂, Ti₂NiB₂, Tm₂CdPd₂, Tm₂InCu₂, Tm₂InPd₂, U₂PbRh₂, Yb₂PbPt₂

- This is the ternary form of the Si₂U₃ (*D*5_a structure).

Simple Tetragonal primitive vectors



$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	Fe I
$\mathbf{B}_2$	$=$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}}$	Fe I
$\mathbf{B}_3$	$=$	$x_2 \mathbf{a}_1 + \left(x_2 + \frac{1}{2}\right) \mathbf{a}_2$	$=$	$ax_2 \hat{\mathbf{x}} + a \left(x_2 + \frac{1}{2}\right) \hat{\mathbf{y}}$	B I
$\mathbf{B}_4$	$=$	$-x_2 \mathbf{a}_1 - \left(x_2 - \frac{1}{2}\right) \mathbf{a}_2$	$=$	$-ax_2 \hat{\mathbf{x}} - a \left(x_2 - \frac{1}{2}\right) \hat{\mathbf{y}}$	B I
$\mathbf{B}_5$	$=$	$-\left(x_2 - \frac{1}{2}\right) \mathbf{a}_1 + x_2 \mathbf{a}_2$	$=$	$-a \left(x_2 - \frac{1}{2}\right) \hat{\mathbf{x}} + ax_2 \hat{\mathbf{y}}$	B I
$\mathbf{B}_6$	$=$	$\left(x_2 + \frac{1}{2}\right) \mathbf{a}_1 - x_2 \mathbf{a}_2$	$=$	$a \left(x_2 + \frac{1}{2}\right) \hat{\mathbf{x}} - ax_2 \hat{\mathbf{y}}$	B I
$\mathbf{B}_7$	$=$	$x_3 \mathbf{a}_1 + \left(x_3 + \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + a \left(x_3 + \frac{1}{2}\right) \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	Mo I
$\mathbf{B}_8$	$=$	$-x_3 \mathbf{a}_1 - \left(x_3 - \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} - a \left(x_3 - \frac{1}{2}\right) \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	Mo I
$\mathbf{B}_9$	$=$	$-\left(x_3 - \frac{1}{2}\right) \mathbf{a}_1 + x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-a \left(x_3 - \frac{1}{2}\right) \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	Mo I
$\mathbf{B}_{10}$	$=$	$\left(x_3 + \frac{1}{2}\right) \mathbf{a}_1 - x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$a \left(x_3 + \frac{1}{2}\right) \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}} + \frac{1}{2} c \hat{\mathbf{z}}$	Mo I

References

- [1] W. Rieger, H. Nowotny, and F. Benesovsky, *Die Kristallstruktur von Mo_2FeB_2* , Monatsh. Chem. **95**, 1502–1503 (1964), doi:10.1007/BF00901704.

Found in

- [1] Y. Jian, Z. Huang, X. Liu, and J. Xing, *Comparative investigation on the stability, electronic structures and mechanical properties of Mo_2FeB_2 and Mo_2NiB_2 ternary borides by first-principles calculations*, Results in Physics **15**, 102698 (2019), doi:10.1016/j.rinp.2019.102698.

First cited in

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.