

MnBi₂Te₄ Structure:

A2BC4_hR7_166_c_a_2c-002

This structure previously used the label(s) **A2BC4_hR7_166_c_a_2c**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/MU2V>

https://aflow.org/prototype-encyclopedia/A2BC4_hR7_166_c_a_2c-002

Prototype	Bi ₂ MnTe ₄
AFLOW prototype label	A2BC4_hR7_166_c_a_2c-002
ICSD	37566
CCDC	2227556
Pearson symbol	hR7
Space group number	166
Space group symbol	$R\bar{3}m$
AFLOW prototype command	<code>aflow --proto=A2BC4_hR7_166_c_a_2c-002</code> <code>--params=a, c/a, x₂, x₃, x₄</code>

Other compounds with this structure

GeAs₂Te₄, MnSb₂Te₄, SSe₂Bi₄, Bi₃Se₄, Se₃Bi₄

- We use the data taken at 10K. Except for the magnetic ordering there is no substantial change in the structure up to room temperature.
- The ICSD entry is from the room-temperature measurements of (Aliev, 2019).
- This structure is nearly identical to GeSb₂Te₄, but the ordering of the tellurium atoms is different in the two cases.

Rhombohedral primitive vectors






$$\mathbf{a}_1 = \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}}$$

$$\mathbf{a}_2 = \frac{1}{\sqrt{3}}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}}$$

$$\mathbf{a}_3 = -\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}}$$



Bi
Mn
Te

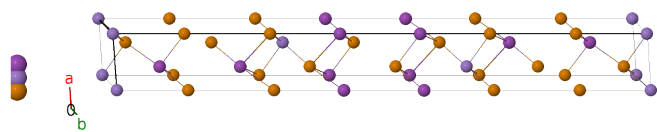

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	Mn I
$\mathbf{B}_2$	$=$	$x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + x_2 \mathbf{a}_3$	$=$	$cx_2 \hat{\mathbf{z}}$	Bi I
$\mathbf{B}_3$	$=$	$-x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2 - x_2 \mathbf{a}_3$	$=$	$-cx_2 \hat{\mathbf{z}}$	Bi I
$\mathbf{B}_4$	$=$	$x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	$=$	$cx_3 \hat{\mathbf{z}}$	Te I
$\mathbf{B}_5$	$=$	$-x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 - x_3 \mathbf{a}_3$	$=$	$-cx_3 \hat{\mathbf{z}}$	Te I
$\mathbf{B}_6$	$=$	$x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3$	$=$	$cx_4 \hat{\mathbf{z}}$	Te II
$\mathbf{B}_7$	$=$	$-x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - x_4 \mathbf{a}_3$	$=$	$-cx_4 \hat{\mathbf{z}}$	Te II

References

- [1] J.-Q. Yan, Q. Zhang, T. Heitmann, Z. Huang, K. Y. Chen, J.-G. Cheng, W. Wu, D. Vaknin, B. C. Sales, and R. J. McQueeney, *Crystal growth and magnetic structure of $MnBi_2Te_4$* , Phys. Rev. Mat. **3**, 064202 (2019), doi:10.1103/PhysRevMaterials.3.064202.
- [2] Z. S. Aliev, I. R. Amiraslanov, D. I. Nasonova, A. V. Shevelkov, N. A. Abdullayev, Z. A. Jahangirli, E. N. Orujlu, M. M. Otrokov, N. T. Mamedov, M. B. Babanly, and E. V. Chulkov, *Novel ternary layered manganese bismuth tellurides of the $MnTe-Bi_2Te_3$ system: Synthesis and crystal structure*, J. Alloys Compd. **789**, 443–450 (2019), doi:10.1016/j.jallcom.2019.03.030.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.