

Bi₂GeO₅ Structure:

A2BC5_oC32_36_b_a_a2b-001


This structure previously used the label(s) **A2BC5_oC32_36_b_a_a2b**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/ZATP>

https://aflow.org/prototype-encyclopedia/A2BC5_oC32_36_b_a_a2b-001

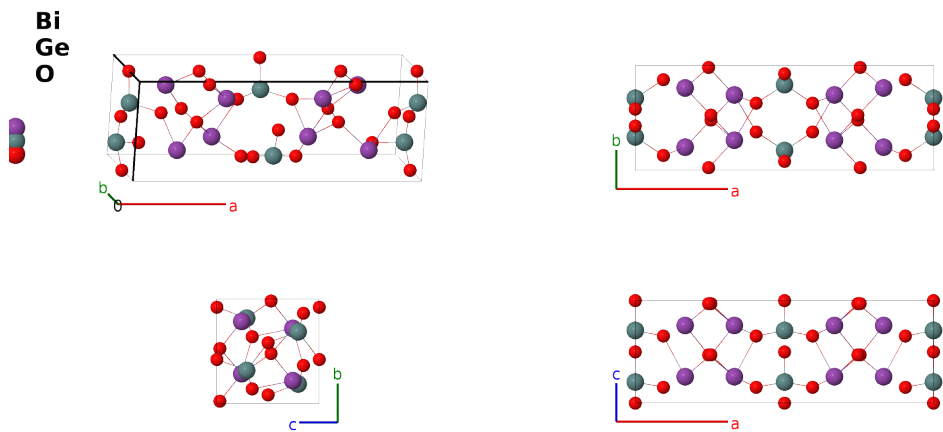

Prototype	Bi ₂ GeO ₅
AFLOW prototype label	A2BC5_oC32_36_b_a_a2b-001
ICSD	49685
CCDC	1614834
Pearson symbol	oC32
Space group number	36
Space group symbol	<i>Cmc</i> 2 ₁
AFLOW prototype command	<code>aflow --proto=A2BC5_oC32_36_b_a_a2b-001</code> <code>--params=a, b/a, c/a, y₁, z₁, y₂, z₂, x₃, y₃, z₃, x₄, y₄, z₄, x₅, y₅, z₅</code>


Other compounds with this structure

Bi₂SiO₅

- Space group *Cmc*2₁ #36 allows an arbitrary choice of the zero of the *z*-axis. Here it is chosen so that *z*₃ = 0 for the bismuth atom.

Base-centered Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

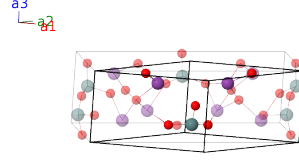

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= -y_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$by_1 \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(4a)	Ge I
$\mathbf{B}_2$	$= y_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-by_1 \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	Ge I
$\mathbf{B}_3$	$= -y_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$by_2 \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4a)	O I
$\mathbf{B}_4$	$= y_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-by_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4a)	O I
$\mathbf{B}_5$	$= (x_3 - y_3) \mathbf{a}_1 + (x_3 + y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(8b)	Bi I
$\mathbf{B}_6$	$= -(x_3 - y_3) \mathbf{a}_1 - (x_3 + y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(8b)	Bi I
$\mathbf{B}_7$	$= (x_3 + y_3) \mathbf{a}_1 + (x_3 - y_3) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(8b)	Bi I
$\mathbf{B}_8$	$= -(x_3 + y_3) \mathbf{a}_1 - (x_3 - y_3) \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(8b)	Bi I
$\mathbf{B}_9$	$= (x_4 - y_4) \mathbf{a}_1 + (x_4 + y_4) \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(8b)	O II
$\mathbf{B}_{10}$	$= -(x_4 - y_4) \mathbf{a}_1 - (x_4 + y_4) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(8b)	O II
$\mathbf{B}_{11}$	$= (x_4 + y_4) \mathbf{a}_1 + (x_4 - y_4) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(8b)	O II
$\mathbf{B}_{12}$	$= -(x_4 + y_4) \mathbf{a}_1 - (x_4 - y_4) \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(8b)	O II
$\mathbf{B}_{13}$	$= (x_5 - y_5) \mathbf{a}_1 + (x_5 + y_5) \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(8b)	O III
$\mathbf{B}_{14}$	$= -(x_5 - y_5) \mathbf{a}_1 - (x_5 + y_5) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \hat{\mathbf{z}}$	(8b)	O III
$\mathbf{B}_{15}$	$= (x_5 + y_5) \mathbf{a}_1 + (x_5 - y_5) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \hat{\mathbf{z}}$	(8b)	O III
$\mathbf{B}_{16}$	$= -(x_5 + y_5) \mathbf{a}_1 - (x_5 - y_5) \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(8b)	O III

References

- [1] B. Aurivillius, C.-I. Lindblom, and P. Sténson, *The Crystal Structure of Bi_2GeO_5* , Acta Chem. Scand. **18** (1964), doi:10.3891/acta.chem.scand.18-1555.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.