

KHF₂ (*F*5₂) Structure: A2BC_tI16_140_h_d_a-001


This structure previously used the label(s) **A2BC_tI16_140_h_d_a**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/B7FR>

https://aflow.org/prototype-encyclopedia/A2BC_tI16_140_h_d_a-001

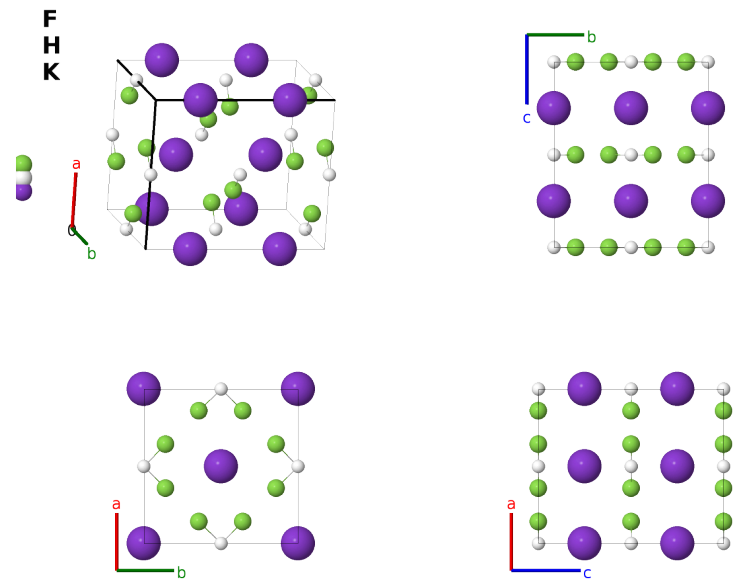


Prototype	F ₂ HK
AFLOW prototype label	A2BC_tI16_140_h_d_a-001
<i>Strukturbericht</i> designation	<i>F</i> 5 ₂
ICSD	18094
CCDC	1597651
Pearson symbol	tI16
Space group number	140
Space group symbol	<i>I</i> 4/ <i>mcm</i>
AFLOW prototype command	<code>aflow --proto=A2BC_tI16_140_h_d_a-001 --params=a, c/a, x₃</code>

Other compounds with this structure
KN₃, CsN₃

- (Bozorth, 1923) originally determined the lattice constants of KHF_2 along with the positions of the potassium and fluorine atoms. He also assumed that the hydrogen atoms were on the (4d) Wyckoff sites. Both (Peterson, 1952) and (Ibers, 1964) confirmed his data. All three papers point out that it is possible that the hydrogen atoms are on half-filled (8h) sites, which would reduce to the (4d) site as the x coordinate approached zero. In KN_3 and CsN_3 the nitrogen atoms occupy the (4d) and (8h) Wyckoff sites, while the cation occupies the (4a) site.

Body-centered Tetragonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= -\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} - \frac{1}{2}c \hat{\mathbf{z}}\end{aligned}$$

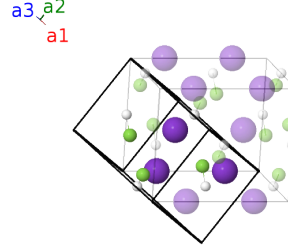

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{4} \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2$	$=$	$\frac{1}{4}c \hat{\mathbf{z}}$	(4a)	K I
$\mathbf{B}_2$	$= \frac{3}{4} \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2$	$=$	$\frac{3}{4}c \hat{\mathbf{z}}$	(4a)	K I
$\mathbf{B}_3$	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{y}}$	(4d)	H I
$\mathbf{B}_4$	$= \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}}$	(4d)	H I
$\mathbf{B}_5$	$= \left(x_3 + \frac{1}{2}\right) \mathbf{a}_1 + x_3 \mathbf{a}_2 + \left(2x_3 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + a \left(x_3 + \frac{1}{2}\right) \hat{\mathbf{y}}$	(8h)	F I
$\mathbf{B}_6$	$= -\left(x_3 - \frac{1}{2}\right) \mathbf{a}_1 - x_3 \mathbf{a}_2 - \left(2x_3 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} - a \left(x_3 - \frac{1}{2}\right) \hat{\mathbf{y}}$	(8h)	F I
$\mathbf{B}_7$	$= x_3 \mathbf{a}_1 - \left(x_3 - \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-a \left(x_3 - \frac{1}{2}\right) \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}}$	(8h)	F I
$\mathbf{B}_8$	$= -x_3 \mathbf{a}_1 + \left(x_3 + \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$a \left(x_3 + \frac{1}{2}\right) \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}}$	(8h)	F I

References

- [1] J. A. Ibers, *Refinement of Peterson and Levy's Neutron Diffraction Data on KHF_2* , J. Chem. Phys. **40**, 402–404 (1964), doi:10.1063/1.1725126.
- [2] S. W. Peterson and H. A. Levy, *A Single Crystal Neutron Diffraction Determination of the Hydrogen Position in Potassium Bifluoride*, J. Chem. Phys. **20**, 704–707 (1952), doi:10.1063/1.1700520.
- [3] R. M. Bozorth, *The crystal structure of potassium hydrogen fluoride*, J. Am. Chem. Soc. **45**, 2128–2132 (1923), doi:10.1021/ja01662a013.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.