

Li₂Sb Structure:

A2B_hP18_190_gh_bf-001


This structure previously used the label(s) **A2B_hP18_190_gh_bf**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/DA98>

https://aflow.org/prototype-encyclopedia/A2B_hP18_190_gh_bf-001

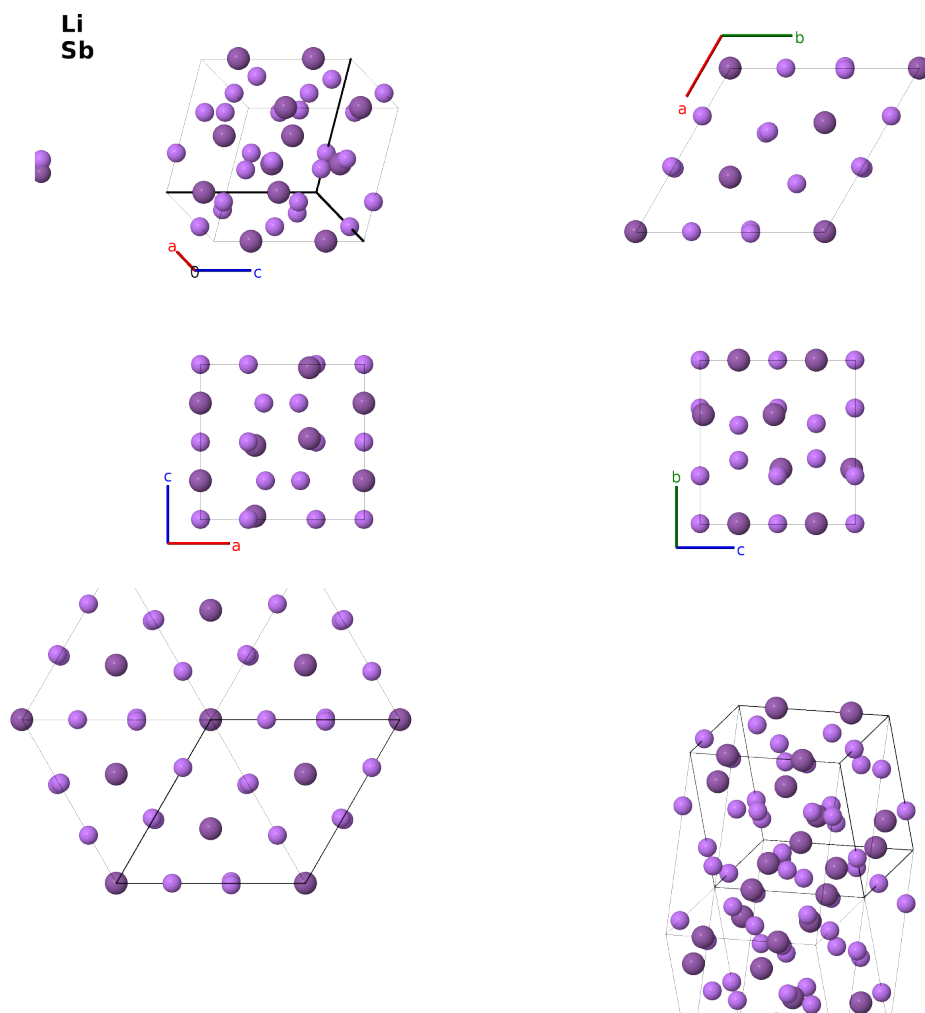


Prototype	Li ₂ Sb
AFLOW prototype label	A2B_hP18_190_gh_bf-001
ICSD	100020
CCDC	1659211
Pearson symbol	hP18

Space group number 190
Space group symbol $P\bar{6}2c$
AFLOW prototype command `aflow --proto=A2B_hP18_190_gh_bf-001`
`--params=a, c/a, z2, x3, x4, y4`

Hexagonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

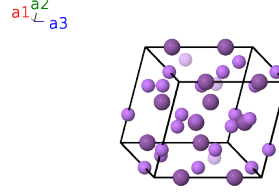

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \hat{\mathbf{z}}$	(2b)	Sb I
$\mathbf{B}_2$	$= \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \hat{\mathbf{z}}$	(2b)	Sb I
$\mathbf{B}_3$	$= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4f)	Sb II
$\mathbf{B}_4$	$= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(4f)	Sb II
$\mathbf{B}_5$	$= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4f)	Sb II
$\mathbf{B}_6$	$= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4f)	Sb II
$\mathbf{B}_7$	$= x_3 \mathbf{a}_1$	$=$	$\frac{1}{2}ax_3 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}}$	(6g)	Li I
$\mathbf{B}_8$	$= x_3 \mathbf{a}_2$	$=$	$\frac{1}{2}ax_3 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}}$	(6g)	Li I
$\mathbf{B}_9$	$= -x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2$	$=$	$-ax_3 \hat{\mathbf{x}}$	(6g)	Li I
$\mathbf{B}_{10}$	$= x_3 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}ax_3 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(6g)	Li I
$\mathbf{B}_{11}$	$= x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}ax_3 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(6g)	Li I
$\mathbf{B}_{12}$	$= -x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$	(6g)	Li I
$\mathbf{B}_{13}$	$= x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_4 + y_4) \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a(x_4 - y_4) \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6h)	Li II
$\mathbf{B}_{14}$	$= -y_4 \mathbf{a}_1 + (x_4 - y_4) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_4 - 2y_4) \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6h)	Li II
$\mathbf{B}_{15}$	$= -(x_4 - y_4) \mathbf{a}_1 - x_4 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$-\frac{1}{2}a(2x_4 - y_4) \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ay_4 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6h)	Li II
$\mathbf{B}_{16}$	$= y_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_4 + y_4) \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a(x_4 - y_4) \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6h)	Li II
$\mathbf{B}_{17}$	$= (x_4 - y_4) \mathbf{a}_1 - y_4 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_4 - 2y_4) \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6h)	Li II
$\mathbf{B}_{18}$	$= -x_4 \mathbf{a}_1 - (x_4 - y_4) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-\frac{1}{2}a(2x_4 - y_4) \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ay_4 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6h)	Li II

References

[1] W. Müller, *Darstellung und Struktur der Phase Li₂Sb*, Z. Naturforsch. B **32**, 357–359 (1977).

First cited in

D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043