


β -CuI (Bührer-Hälg) Structure: A2B_hP6_187_gi_ad-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/P31P>

https://aflow.org/prototype-encyclopedia/A2B_hP6_187_gi_ad-001

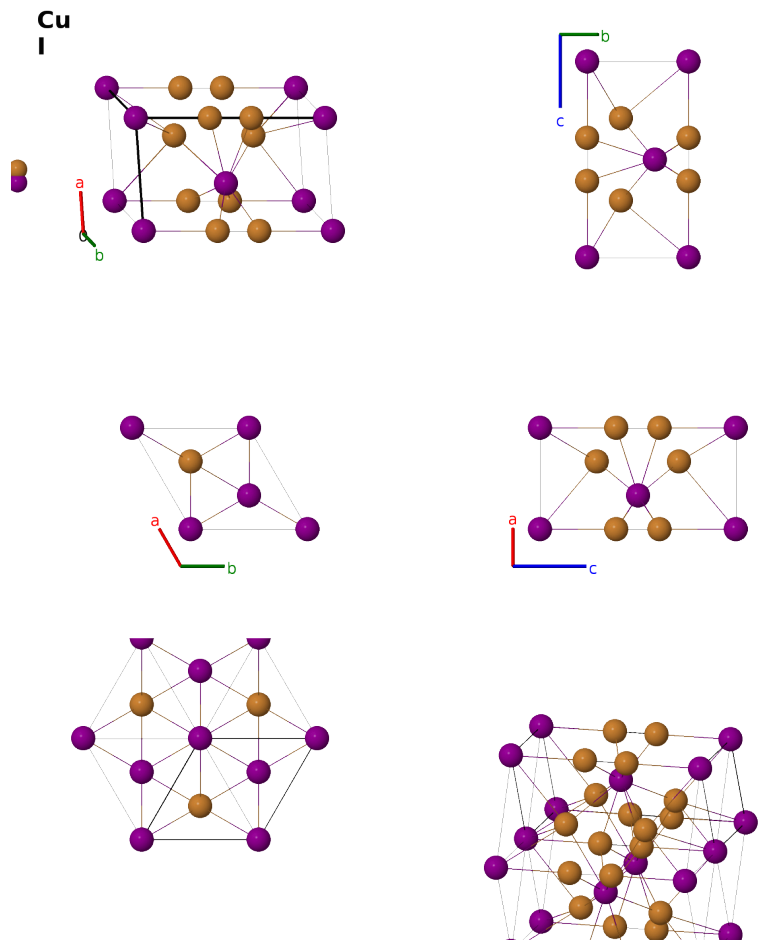


Prototype	CuI
AFLOW prototype label	A2B_hP6_187_gi_ad-001
ICSD	30088
CCDC	1604543
Pearson symbol	hP6
Space group number	187
Space group symbol	$P\bar{6}m2$

AFLOW prototype command `aflow --proto=A2B_hP6_187_gi_ad-001`
 `--params=a, c/a, z3, z4`

- Copper(I) iodide can be found in three forms (Keen, 1995):
 - α -CuI is stable above $673 \pm 8\text{K}$, and is in the $\delta\text{-Bi}_2\text{O}_3$ structure, with the iodine atoms on the (2a) Wyckoff positions and the copper atoms occupying 1/8 of the (32f) positions.
 - γ -CuI (marshite) is the ground state, stable below $643 \pm 2\text{K}$, and is also in the $\delta\text{-Bi}_2\text{O}_3$ structure.
 - In the intermediate temperature range β -CuI is generally agreed to be trigonal or hexagonal, but the exact structure is under dispute:
 - * (Kurdyumova, 1961) placed it in trigonal space group $P3m1$ #156. Their unit cell is three times larger than the standard cell for this structure, and is now considered erroneous. (Abrahams, 2008).
 - * (Bührer, 1977) placed it in hexagonal space group $P\bar{6}m2$ #187 (this structure), with the copper atoms partially occupying two sites.
 - * (Sakuma, 1988) placed it in trigonal space group $P3m1$ #156 with a smaller unit cell than (Kurdyumova, 1961) and no disorder on the copper sites.
 - * (Keen, 1994) placed it in trigonal space group $P\bar{3}m1$ #164, with a unit cell similar to (Bührer, 1977) and (Sakuma, 1988). Like the former paper, the oxygen positions are disordered.
 - The data from (Bührer, 1977) was taken at 653K.
 - The copper sites are only partially occupied: Cu-I (2g) is 70% filled, with the remaining 30% of the copper atoms going on the Cu-II (2i) site.
-

Hexagonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

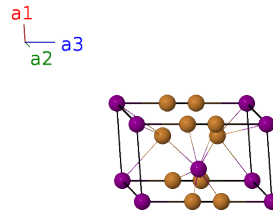

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	(1a) I I
$\mathbf{B}_2$	$=$	$\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(1d) I II
$\mathbf{B}_3$	$=$	$z_3 \mathbf{a}_3$	$=$	$cz_3 \hat{\mathbf{z}}$	(2g) Cu I
$\mathbf{B}_4$	$=$	$-z_3 \mathbf{a}_3$	$=$	$-cz_3 \hat{\mathbf{z}}$	(2g) Cu I
$\mathbf{B}_5$	$=$	$\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(2i) Cu II
$\mathbf{B}_6$	$=$	$\frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(2i) Cu II

References

- [1] W. Bührer and W. Hälg, *Crystal structure of high-temperature cuprous iodide and cuprous bromide*, *Electrochimica Acta* **22**, 701–704 (1977), doi:10.1016/0013-4686(77)80021-2.

- [2] R. N. Kurdyumova and R. V. Baranova, *An electron diffraction study of thin films of cuprous iodide*, Sov. Phys. Cryst. **6**, 318–321 (1961).
- [3] D. A. Keen and S. Hull, *Determination of the structure of β -CuI by high-resolution neutron powder diffraction*, J. Phys.: Condens. Matter **6**, 1637–1644 (1994), doi:10.1088/0953-8984/6/9/006.
- [4] D. A. Keen and S. Hull, *The high-temperature structural behaviour of copper(I) iodide*, J. Phys.: Condens. Matter **7**, 5793–5804 (1995), doi:10.1088/0953-8984/7/29/007.
- [5] S. C. Abrahams, *Inorganic structures in space group $P3m1$; coordinate analysis and systematic prediction of new ferroelectrics*, Acta Crystallogr. Sect. B **64**, 426–437 (2008), doi:10.1107/S0108768108018144.

Found in

- [1] T. Sakuma, *Crystal Structure of β -CuI*, J. Phys. Soc. Jpn. **57**, 565–569 (1988), doi:10.1143/JPSJ.57.565.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.