

Nb₂Se Structure:


A2B_mC24_12_4i_2i-004

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/2691>

https://aflow.org/prototype-encyclopedia/A2B_mC24_12_4i_2i-004

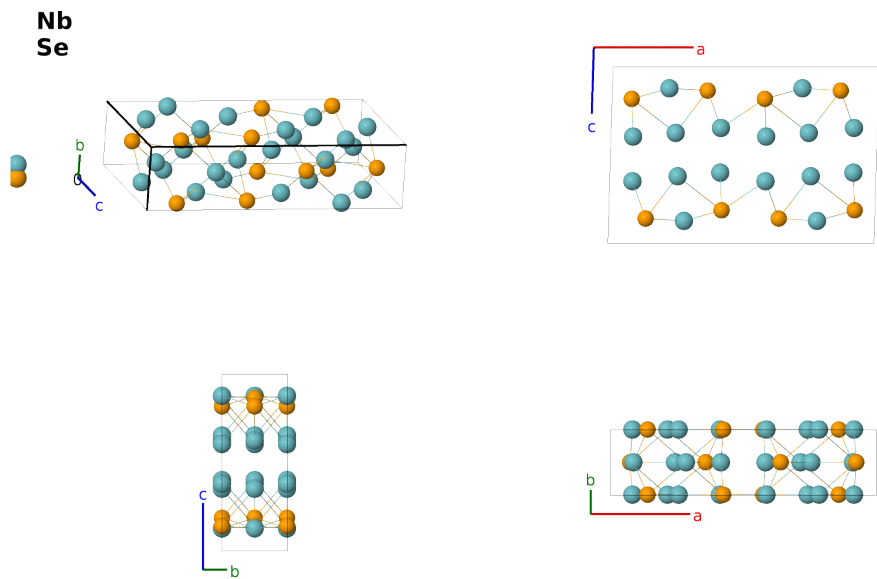


Prototype	Nb ₂ Se
AFLOW prototype label	A2B_mC24_12_4i_2i-004
ICSD	26183
CCDC	1601616
Pearson symbol	mC24
Space group number	12
Space group symbol	<i>C</i> 2/ <i>m</i>
AFLOW prototype command	<code>aflow --proto=A2B_mC24_12_4i_2i-004</code> <code>--params=a, b/a, c/a, β, x_1, z_1, x_2, z_2, x_3, z_3, x_4, z_4, x_5, z_5, x_6, z_6</code>

Other compounds with this structure

Hf₂Se

Base-centered Monoclinic primitive vectors

$$\begin{aligned}
\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\
\mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\
\mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}
\end{aligned}$$

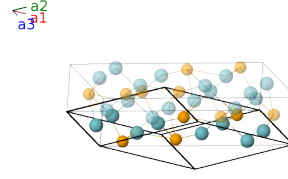

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + x_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(4i)	Nb I
$\mathbf{B}_2$	$= -x_1 \mathbf{a}_1 - x_1 \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} - cz_1 \sin \beta \hat{\mathbf{z}}$	(4i)	Nb I
$\mathbf{B}_3$	$= x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(4i)	Nb II
$\mathbf{B}_4$	$= -x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} - cz_2 \sin \beta \hat{\mathbf{z}}$	(4i)	Nb II
$\mathbf{B}_5$	$= x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(4i)	Nb III
$\mathbf{B}_6$	$= -x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} - cz_3 \sin \beta \hat{\mathbf{z}}$	(4i)	Nb III
$\mathbf{B}_7$	$= x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(4i)	Nb IV
$\mathbf{B}_8$	$= -x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} - cz_4 \sin \beta \hat{\mathbf{z}}$	(4i)	Nb IV
$\mathbf{B}_9$	$= x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(4i)	Se I
$\mathbf{B}_{10}$	$= -x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - cz_5 \sin \beta \hat{\mathbf{z}}$	(4i)	Se I
$\mathbf{B}_{11}$	$= x_6 \mathbf{a}_1 + x_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + cz_6 \sin \beta \hat{\mathbf{z}}$	(4i)	Se II
$\mathbf{B}_{12}$	$= -x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$-(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - cz_6 \sin \beta \hat{\mathbf{z}}$	(4i)	Se II

References

- [1] B. R. Conard, L. J. Norrby, and H. F. Franzen, *The crystal structure of Nb₂Se*, Acta Crystallogr. Sect. B **25**, 1729–1736 (1969), doi:10.1107/S0567740869004663.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.