

ZrSi₂ (*C*49) Structure: A2B_oC12_63_2c_c-001


This structure previously used the label(s) **A2B_oC12_63_2c_c**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/HPCM>

https://aflow.org/prototype-encyclopedia/A2B_oC12_63_2c_c-001

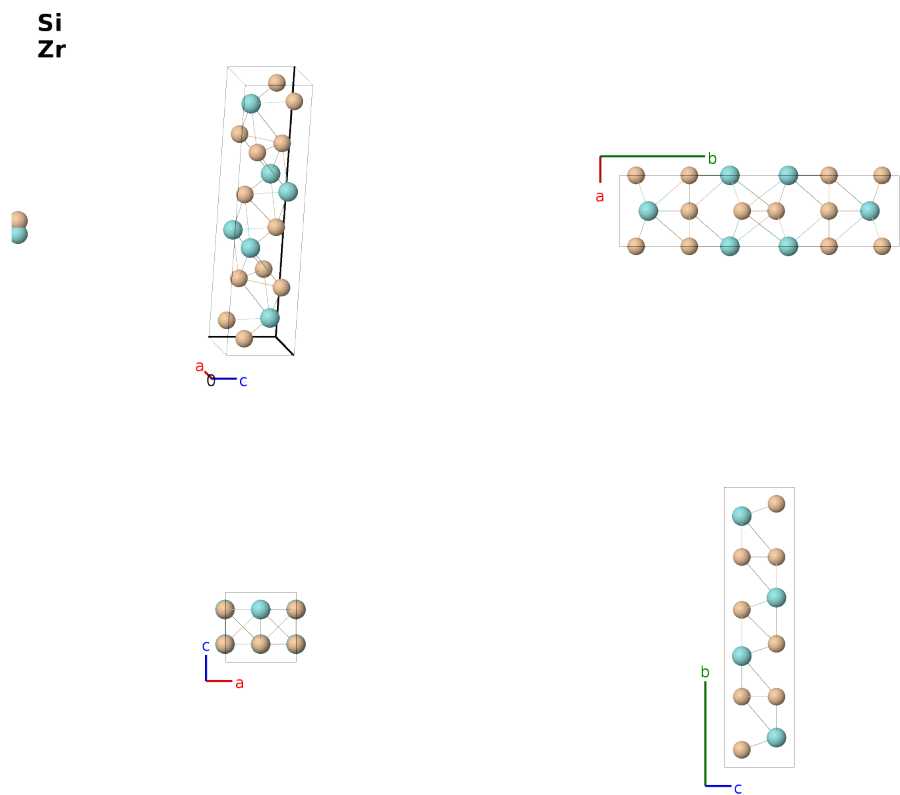

Prototype	Si ₂ Zr
AFLOW prototype label	A2B_oC12_63_2c_c-001
<i>Strukturbericht</i> designation	<i>C</i> 49
ICSD	652610
CCDC	1765229
Pearson symbol	oC12
Space group number	63
Space group symbol	<i>Cmcm</i>


AFLOW prototype command `aflow --proto=A2B_oC12_63_2c_c-001`
 `--params=a, b/a, c/a, y1, y2, y3`

Other compounds with this structure

Bi₂Ca, Bi₂Eu, Ge₂Hf, Ge₂Th, Ge₂U, Ge₂Zr, Si₂Hf, Si₂Ti, Sn₂Er, Sn₂Dy, Sn₂Gd, Sn₂Ho, Sn₂Lu, Sn₂Tb, Sn₂Tm, Sn₂Y, Sn₂Yb

Base-centered Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

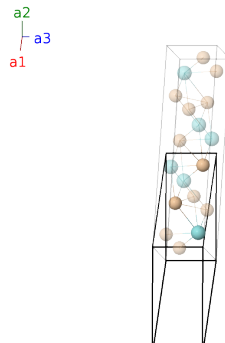

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= -y_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$by_1 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4c)	Si I
$\mathbf{B}_2$	$= y_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-by_1 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(4c)	Si I
$\mathbf{B}_3$	$= -y_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$by_2 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4c)	Si II
$\mathbf{B}_4$	$= y_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-by_2 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(4c)	Si II
$\mathbf{B}_5$	$= -y_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$by_3 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(4c)	Zr I
$\mathbf{B}_6$	$= y_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-by_3 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(4c)	Zr I

References

- [1] P. G. Cotter, J. A. Kohn, and R. A. Potter, *Physical and X-Ray Study of the Disilicides of Titanium, Zirconium, and Hafnium*, J. Am. Ceram. Soc. **39**, 11–12 (1956), doi:10.1111/j.1151-2916.1956.tb15590.x.

Found in

- [1] P. Villars, *ZrSi₂ Crystal Structure* (2016). PAULING FILE in: Inorganic Solid Phases, SpringerMaterials (online database), Springer, Heidelberg (ed.) SpringerMaterials.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017