

γ -TeO₂ Structure (*Erroneous*): A2B_oP12_18_2c_c-001


This structure previously used the label(s) **A2B_oP12_18_2c_c**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/4QQ6>


https://aflow.org/prototype-encyclopedia/A2B_oP12_18_2c_c-001

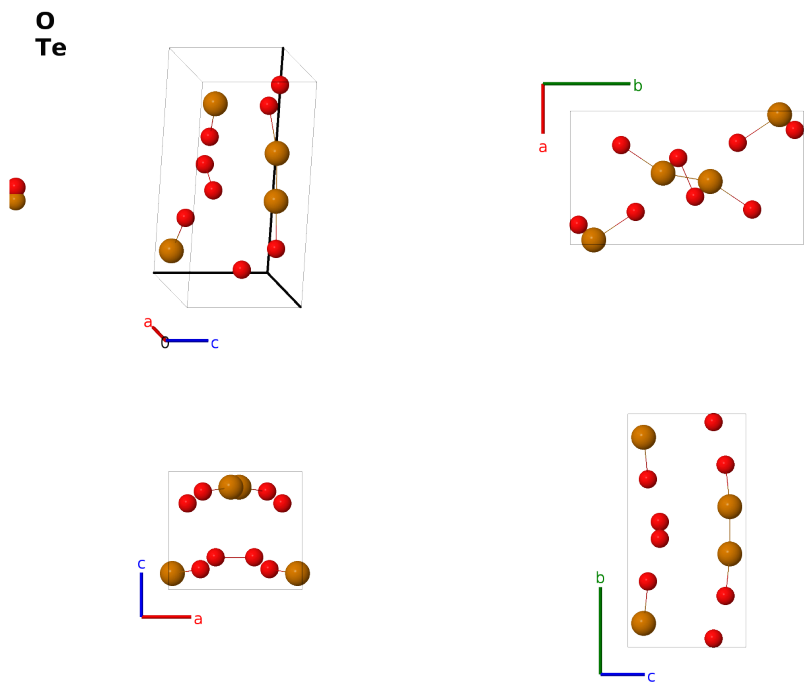

Prototype	O ₂ Te
AFLOW prototype label	A2B_oP12_18_2c_c-001
ICSD	90733
CCDC	1650349
Pearson symbol	oP12
Space group number	18
Space group symbol	$P2_12_12$
AFLOW prototype command	<code>aflow --proto=A2B_oP12_18_2c_c-001</code> <code>--params=a, b/a, c/a, x₁, y₁, z₁, x₂, y₂, z₂, x₃, y₃, z₃</code>

- This structure, which we published in (Hicks, 2021), is in error. We followed the text of (Champarnaud-Mesjard, 2000), which put this structure in space group $P2_12_12$ #18. In fact, the structure is in $P2_12_12_1$ #19, as an examination of the figures in that paper demonstrate, and shows that γ -TeO₂ takes on the β -SnF₂ structure.
- The ICSD entry for (Champarnaud-Mesjard, 2000), 90733, correctly identifies the space group for this structure.
- We regret the error, but leave the structure in place as it has already been published.
- In reality, TeO₂ has been observed in three different forms (Ceriotti, 2006; Liu, 2016):
 - α -TeO₂, paratellurite is the ground state
 - β -TeO₂, tellurite is stable under ambient conditions and is the most commonly observed phase
 - γ -TeO₂ is metastable, and forms at 663K in the β -SnF₂ structure.

Simple Orthorhombic primitive vectors

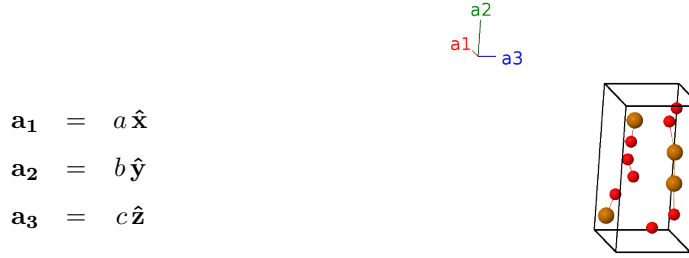

Basis vectors

	Lattice coordinates		Cartesian coordinates		Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	$(4c)$		O I
$\mathbf{B}_2$	$= -x_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	$(4c)$		O I
$\mathbf{B}_3$	$= -\left(x_1 - \frac{1}{2}\right) \mathbf{a}_1 + \left(y_1 + \frac{1}{2}\right) \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-a\left(x_1 - \frac{1}{2}\right) \hat{\mathbf{x}} + b\left(y_1 + \frac{1}{2}\right) \hat{\mathbf{y}} - cz_1 \hat{\mathbf{z}}$	$(4c)$		O I
$\mathbf{B}_4$	$= \left(x_1 + \frac{1}{2}\right) \mathbf{a}_1 - \left(y_1 - \frac{1}{2}\right) \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$a\left(x_1 + \frac{1}{2}\right) \hat{\mathbf{x}} - b\left(y_1 - \frac{1}{2}\right) \hat{\mathbf{y}} - cz_1 \hat{\mathbf{z}}$	$(4c)$		O I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	$(4c)$		O II
$\mathbf{B}_6$	$= -x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	$(4c)$		O II
$\mathbf{B}_7$	$= -\left(x_2 - \frac{1}{2}\right) \mathbf{a}_1 + \left(y_2 + \frac{1}{2}\right) \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-a\left(x_2 - \frac{1}{2}\right) \hat{\mathbf{x}} + b\left(y_2 + \frac{1}{2}\right) \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	$(4c)$		O II
$\mathbf{B}_8$	$= \left(x_2 + \frac{1}{2}\right) \mathbf{a}_1 - \left(y_2 - \frac{1}{2}\right) \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$a\left(x_2 + \frac{1}{2}\right) \hat{\mathbf{x}} - b\left(y_2 - \frac{1}{2}\right) \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	$(4c)$		O II
$\mathbf{B}_9$	$= x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	$(4c)$		Te I
$\mathbf{B}_{10}$	$= -x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	$(4c)$		Te I
$\mathbf{B}_{11}$	$= -\left(x_3 - \frac{1}{2}\right) \mathbf{a}_1 + \left(y_3 + \frac{1}{2}\right) \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-a\left(x_3 - \frac{1}{2}\right) \hat{\mathbf{x}} + b\left(y_3 + \frac{1}{2}\right) \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	$(4c)$		Te I
$\mathbf{B}_{12}$	$= \left(x_3 + \frac{1}{2}\right) \mathbf{a}_1 - \left(y_3 - \frac{1}{2}\right) \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$a\left(x_3 + \frac{1}{2}\right) \hat{\mathbf{x}} - b\left(y_3 - \frac{1}{2}\right) \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	$(4c)$		Te I

References

- [1] J. C. Champarnaud-Mesjard, S. Blanchandin, P. Thomas, A. Mirgorodsky, T. Merle-Méjean, and B. Frit, *Crystal structure, Raman spectrum and lattice dynamics of a new metastable form of tellurium dioxide: γ -TeO₂*, J. Phys. Chem. Solids **61**, 1499–1507 (2000), doi:10.1016/S0022-3697(00)00012-3.
- [2] D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi:10.1016/j.commatsci.2021.110450.

Found in

- [1] M. Ceriotti, F. Pietrucci, and M. Bernasconi, *Ab initio study of the vibrational properties of crystalline TeO_2 : The α , β , and γ phases*, Phys. Rev. B **73**, 104304 (2006), doi:10.1103/PhysRevB.73.104304.

First cited in

- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.