

Shandite (Ni₃Pb₂S₂) Structure:

A3B2C2_hR7_166_d_ab_c-001


This structure previously used the label(s) **A3B2C2_hR7_166_d_ab_c**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/SD1B>

https://aflow.org/prototype-encyclopedia/A3B2C2_hR7_166_d_ab_c-001

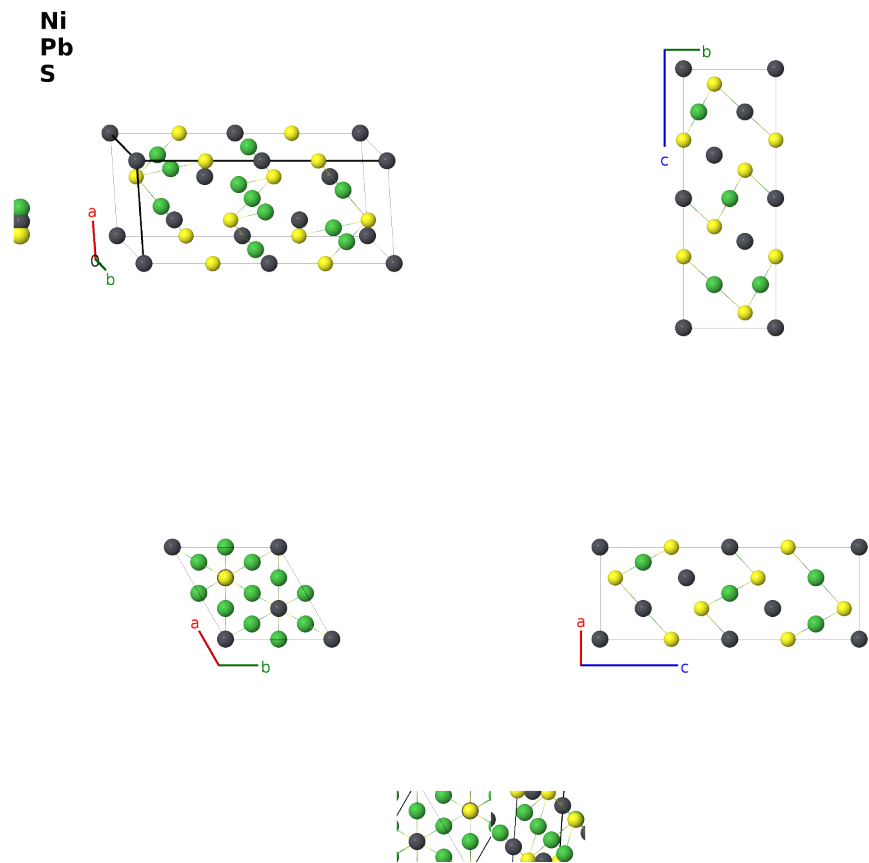

Prototype	Ni ₃ Pb ₂ S ₂
AFLOW prototype label	A3B2C2_hR7_166_d_ab_c-001
Mineral name	shandite
ICSD	417632
CCDC	1730948
Pearson symbol	hR7
Space group number	166
Space group symbol	$R\bar{3}m$


AFLOW prototype command `aflow --proto=A3B2C2_hR7_166_d_ab_c-001`
 `--params=a, c/a, x3`

Other compounds with this structure

Co₃In₂S₂, Co₃Sn₂S₂, Ni₃In₂S₂, Ni₃Sn₂S₂, Ni₃Tl₂S₂, O₃K₂Sn₂, Pd₃Bi₂S₂, Pd₃Pb₂S₂, Pt₃Pb₂S₂, Rh₃Pb₂S₂, Rh₃Tl₂S₂

Rhombohedral primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{\sqrt{3}}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}} \\ \mathbf{a}_3 &= -\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{3}c \hat{\mathbf{z}}\end{aligned}$$

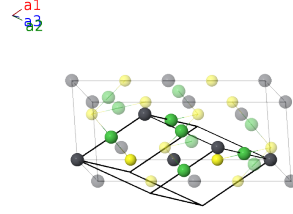

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	=	0	=	0	(1a) Pb I
$\mathbf{B}_2$	=	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2}c \hat{\mathbf{z}}$	(1b) Pb II
$\mathbf{B}_3$	=	$x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	=	$cx_3 \hat{\mathbf{z}}$	(2c) S I
$\mathbf{B}_4$	=	$-x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 - x_3 \mathbf{a}_3$	=	$-cx_3 \hat{\mathbf{z}}$	(2c) S I
$\mathbf{B}_5$	=	$\frac{1}{2} \mathbf{a}_1$	=	$\frac{1}{4}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{12}a \hat{\mathbf{y}} + \frac{1}{6}c \hat{\mathbf{z}}$	(3d) Ni I
$\mathbf{B}_6$	=	$\frac{1}{2} \mathbf{a}_2$	=	$\frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{6}c \hat{\mathbf{z}}$	(3d) Ni I
$\mathbf{B}_7$	=	$\frac{1}{2} \mathbf{a}_3$	=	$-\frac{1}{4}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{12}a \hat{\mathbf{y}} + \frac{1}{6}c \hat{\mathbf{z}}$	(3d) Ni I

References

- [1] R. Weihrich, S. F. Matar, V. Eyert, F. Rau, M. Zabel, M. Andratschke, I. Anusca, and T. Bernert, *Structure, ordering, and bonding of half antiperovskites: PbNi_{3/2}S and BiPd_{3/2}S*, Prog. Solid State Chem. **35**, 309–322 (2007), doi:10.1016/j.progsolidstchem.2007.01.011.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.