

Lu₂Co₃Si₅ Structure:


A3B2C5_mC40_15_ef_f_3ef-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/1Q2N>

https://aflow.org/prototype-encyclopedia/A3B2C5_mC40_15_ef_f_3ef-001

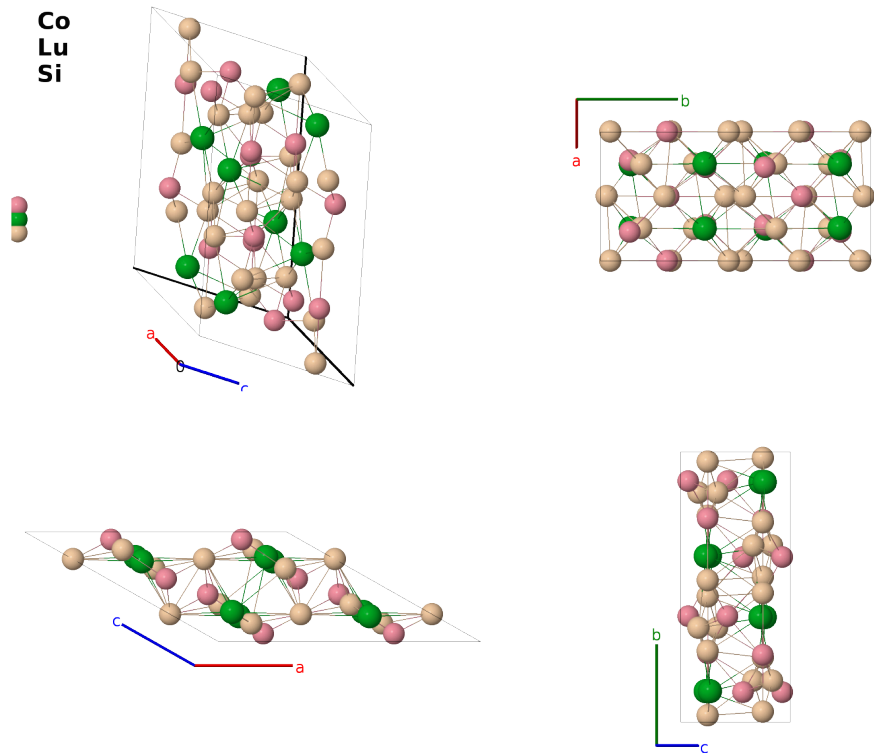


Prototype	Co ₃ Lu ₂ Si ₅
AFLOW prototype label	A3B2C5_mC40_15_ef_f_3ef-001
ICSD	76349
CCDC	1636956
Pearson symbol	mC40
Space group number	15
Space group symbol	<i>C</i> 2/ <i>c</i>
AFLOW prototype command	<code>aflow --proto=A3B2C5_mC40_15_ef_f_3ef-001</code> <code>--params=a,b/a,c/a,β,y₁,y₂,y₃,y₄,x₅,y₅,z₅,x₆,y₆,z₆,x₇,y₇,z₇</code>

Other compounds with this structure

Dy₂Co₃Si₅, Sc₂Co₃Si₅, Y₂Co₃Si₅

- This is a monoclinic distortion of the orthorhombic $\text{U}_2\text{Co}_3\text{Si}_5$ structure. (Chabot, 1985)

Base-centered Monoclinic primitive vectors

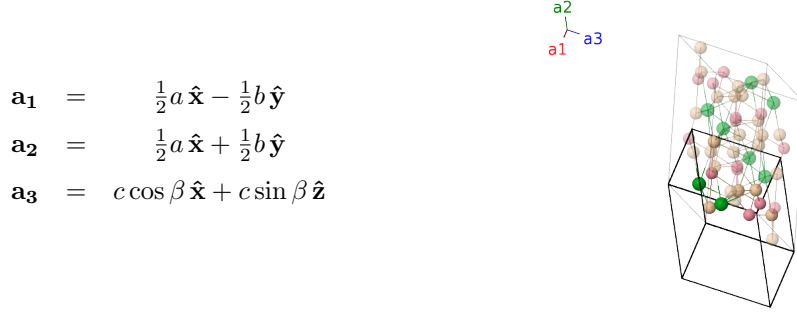

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= -y_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \cos \beta \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + \frac{1}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Co I
$\mathbf{B}_2$	$= y_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \cos \beta \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} + \frac{3}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Co I
$\mathbf{B}_3$	$= -y_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \cos \beta \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + \frac{1}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Si I
$\mathbf{B}_4$	$= y_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \cos \beta \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + \frac{3}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Si I
$\mathbf{B}_5$	$= -y_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \cos \beta \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + \frac{1}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Si II
$\mathbf{B}_6$	$= y_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \cos \beta \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + \frac{3}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Si II
$\mathbf{B}_7$	$= -y_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \cos \beta \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + \frac{1}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Si III
$\mathbf{B}_8$	$= y_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \cos \beta \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + \frac{3}{4}c \sin \beta \hat{\mathbf{z}}$	(4e)	Si III
$\mathbf{B}_9$	$= (x_5 - y_5) \mathbf{a}_1 + (x_5 + y_5) \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(8f)	Co II
$\mathbf{B}_{10}$	$= -(x_5 + y_5) \mathbf{a}_1 - (x_5 - y_5) \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_5 + c(z_5 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Co II
$\mathbf{B}_{11}$	$= -(x_5 - y_5) \mathbf{a}_1 - (x_5 + y_5) \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} - cz_5 \sin \beta \hat{\mathbf{z}}$	(8f)	Co II
$\mathbf{B}_{12}$	$= (x_5 + y_5) \mathbf{a}_1 + (x_5 - y_5) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_5 + c(z_5 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Co II
$\mathbf{B}_{13}$	$= (x_6 - y_6) \mathbf{a}_1 + (x_6 + y_6) \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}}$	(8f)	Lu I
$\mathbf{B}_{14}$	$= -(x_6 + y_6) \mathbf{a}_1 - (x_6 - y_6) \mathbf{a}_2 - (z_6 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_6 + c(z_6 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Lu I
$\mathbf{B}_{15}$	$= -(x_6 - y_6) \mathbf{a}_1 - (x_6 + y_6) \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$-(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} - cz_6 \sin \beta \hat{\mathbf{z}}$	(8f)	Lu I
$\mathbf{B}_{16}$	$= (x_6 + y_6) \mathbf{a}_1 + (x_6 - y_6) \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3$	$=$	$(ax_6 + c(z_6 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Lu I
$\mathbf{B}_{17}$	$= (x_7 - y_7) \mathbf{a}_1 + (x_7 + y_7) \mathbf{a}_2 + z_7 \mathbf{a}_3$	$=$	$(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \sin \beta \hat{\mathbf{z}}$	(8f)	Si IV
$\mathbf{B}_{18}$	$= -(x_7 + y_7) \mathbf{a}_1 - (x_7 - y_7) \mathbf{a}_2 - (z_7 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-(ax_7 + c(z_7 - \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} - c(z_7 - \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(8f)	Si IV
$\mathbf{B}_{19}$	$= -(x_7 - y_7) \mathbf{a}_1 - (x_7 + y_7) \mathbf{a}_2 - z_7 \mathbf{a}_3$	$=$	$-(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} - cz_7 \sin \beta \hat{\mathbf{z}}$	(8f)	Si IV

$$\mathbf{B}_{20} = \begin{pmatrix} (x_7 + y_7) \mathbf{a}_1 + (x_7 - y_7) \mathbf{a}_2 + \\ (z_7 + \frac{1}{2}) \mathbf{a}_3 \end{pmatrix} = \begin{pmatrix} (ax_7 + c(z_7 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} + \\ c(z_7 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} \quad (8f) \quad \text{Si IV}$$

References

- [1] B. Chabot and E. Parthé, *Dy₂Co₃Si₅, Lu₂Co₃Si₅, Y₂Co₃Si₅ and Sc₂Co₃Si₅, with a Monoclinic Structural Deformation Variant of the Orthorhombic U₂Co₃Si₅ Structure Type*, J. Less-Common Met. **106**, 53–59 (1985), doi:10.1016/0022-5088(85)90365-0.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.