

Pt₂Ge₃ Structure:


A3B2_oP20_62_3c_2c-002

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/GDA9>

https://aflow.org/prototype-encyclopedia/A3B2_oP20_62_3c_2c-002

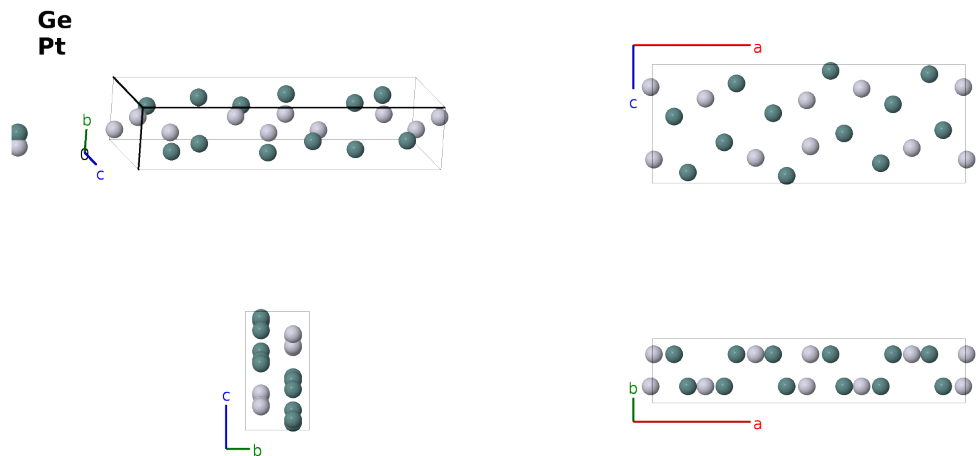

Prototype	Ge ₃ Pt ₂
AFLOW prototype label	A3B2_oP20_62_3c_2c-002
ICSD	42912
CCDC	1612525
Pearson symbol	oP20
Space group number	62
Space group symbol	<i>Pnma</i>
AFLOW prototype command	<code>aflow --proto=A3B2_oP20_62_3c_2c-002</code> <code>--params=a, b/a, c/a, x₁, z₁, x₂, z₂, x₃, z₃, x₄, z₄, x₅, z₅</code>

Other compounds with this structure

Pt₂Si₃


- This structure has the same AFLOW label, A3B2_oP20_62_3c_2c, as stibnite (Sb₂S₃, *D*5₈) and ottemannite (Sn₂S₃). The structures are generated by the same symmetry operations with different sets of parameters (`--params`) specified in their corresponding CIF files.

Simple Orthorhombic primitive vectors

$$\mathbf{a}_1 = a \hat{\mathbf{x}}$$

$$\mathbf{a}_2 = b \hat{\mathbf{y}}$$

$$\mathbf{a}_3 = c \hat{\mathbf{z}}$$

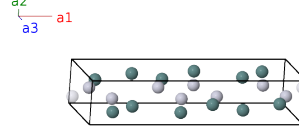

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(4c)	Ge I
$\mathbf{B}_2$	$= -\left(x_1 - \frac{1}{2}\right) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \left(z_1 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_1 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c\left(z_1 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Ge I
$\mathbf{B}_3$	$= -x_1 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_1 \hat{\mathbf{z}}$	(4c)	Ge I
$\mathbf{B}_4$	$= \left(x_1 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_1 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_1 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c\left(z_1 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Ge I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4c)	Ge II
$\mathbf{B}_6$	$= -\left(x_2 - \frac{1}{2}\right) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \left(z_2 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_2 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c\left(z_2 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Ge II
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4c)	Ge II
$\mathbf{B}_8$	$= \left(x_2 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_2 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_2 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c\left(z_2 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Ge II
$\mathbf{B}_9$	$= x_3 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(4c)	Ge III
$\mathbf{B}_{10}$	$= -\left(x_3 - \frac{1}{2}\right) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \left(z_3 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_3 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c\left(z_3 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Ge III
$\mathbf{B}_{11}$	$= -x_3 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(4c)	Ge III
$\mathbf{B}_{12}$	$= \left(x_3 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_3 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_3 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c\left(z_3 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Ge III
$\mathbf{B}_{13}$	$= x_4 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(4c)	Pt I
$\mathbf{B}_{14}$	$= -\left(x_4 - \frac{1}{2}\right) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \left(z_4 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_4 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c\left(z_4 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Pt I
$\mathbf{B}_{15}$	$= -x_4 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(4c)	Pt I
$\mathbf{B}_{16}$	$= \left(x_4 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_4 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_4 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c\left(z_4 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Pt I
$\mathbf{B}_{17}$	$= x_5 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(4c)	Pt II
$\mathbf{B}_{18}$	$= -\left(x_5 - \frac{1}{2}\right) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \left(z_5 + \frac{1}{2}\right) \mathbf{a}_3$	$=$	$-a\left(x_5 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c\left(z_5 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Pt II
$\mathbf{B}_{19}$	$= -x_5 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_5 \hat{\mathbf{z}}$	(4c)	Pt II
$\mathbf{B}_{20}$	$= \left(x_5 + \frac{1}{2}\right) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - \left(z_5 - \frac{1}{2}\right) \mathbf{a}_3$	$=$	$a\left(x_5 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c\left(z_5 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(4c)	Pt II

References

- [1] I. Engström and H.-U. Pfeifer, *The Crystal Structure of Pt_2Ge_3* , Acta Chem. Scand. **22**, 3137–3145 (1968), doi:10.3891/acta.chem.scand.22-3137.

Found in

- [1] A. Jain, S. Ping, G. Hautier, W. Chen, W. D. Richards, S. Dacek, S. Cholia, D. Gunter, D. Skinner, G. Ceder, and K. A. Persson, *Commentary: The Materials Project: A materials genome approach to accelerating materials innovation*, APL

Materials **1**, 011002 (2013), doi:10.1063/1.4812323.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.