

Haussmannite (Mn₃O₄) Structure: A3B4_tI28_141_ad_h-001


This structure previously used the label(s) **A3B4_tI28.141.ad.h**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/KP7A>


https://aflow.org/prototype-encyclopedia/A3B4_tI28_141_ad_h-001

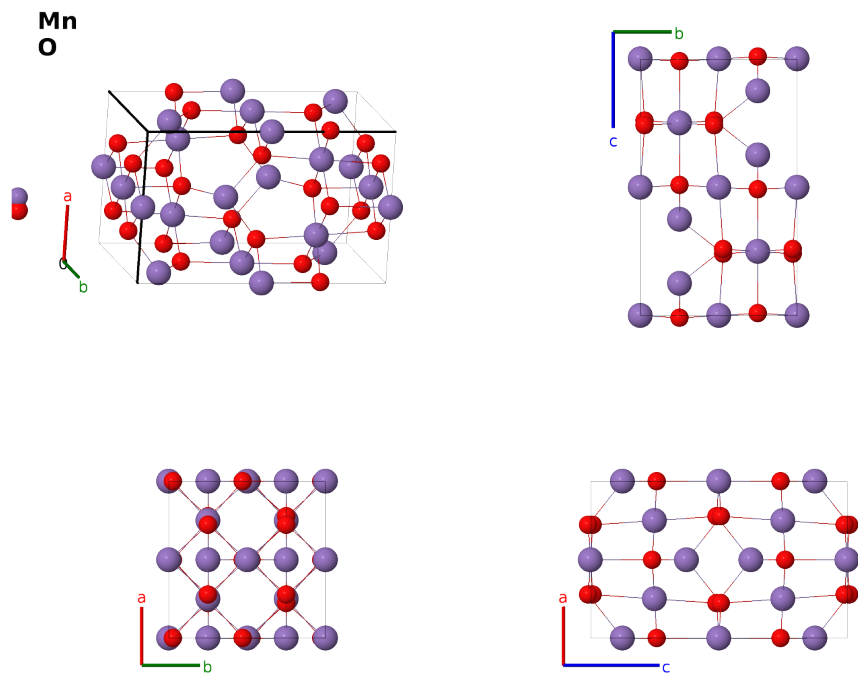

Prototype	Mn ₃ O ₄
AFLOW prototype label	A3B4_tI28_141_ad_h-001
Mineral name	haussmannite
ICSD	68174
CCDC	1630114
Pearson symbol	tI28
Space group number	141
Space group symbol	<i>I</i> 4 ₁ / <i>amd</i>
AFLOW prototype command	<code>aflow --proto=A3B4_tI28_141_ad_h-001</code> <code>--params=a, c/a, y₃, z₃</code>

Body-centered Tetragonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= -\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} - \frac{1}{2}c \hat{\mathbf{z}}\end{aligned}$$

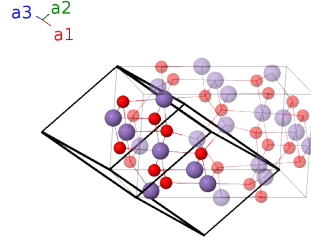

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{7}{8} \mathbf{a}_1 + \frac{1}{8} \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}a \hat{\mathbf{y}} + \frac{1}{8}c \hat{\mathbf{z}}$	(4a)	Mn I
$\mathbf{B}_2$	$= \frac{1}{8} \mathbf{a}_1 + \frac{7}{8} \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{4}a \hat{\mathbf{y}} + \frac{3}{8}c \hat{\mathbf{z}}$	(4a)	Mn I
$\mathbf{B}_3$	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2$	$=$	$\frac{1}{2}c \hat{\mathbf{z}}$	(8d)	Mn II
$\mathbf{B}_4$	$= \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}}$	(8d)	Mn II
$\mathbf{B}_5$	$= \frac{1}{2} \mathbf{a}_1$	$=$	$-\frac{1}{4}a \hat{\mathbf{x}} + \frac{1}{4}a \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(8d)	Mn II
$\mathbf{B}_6$	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{4}a \hat{\mathbf{x}} + \frac{1}{4}a \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(8d)	Mn II
$\mathbf{B}_7$	$= (y_3 + z_3) \mathbf{a}_1 + z_3 \mathbf{a}_2 + y_3 \mathbf{a}_3$	$=$	$ay_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(16h)	O I
$\mathbf{B}_8$	$= (-y_3 + z_3 + \frac{1}{2}) \mathbf{a}_1 + z_3 \mathbf{a}_2 - (y_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(y_3 - \frac{1}{2}) \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(16h)	O I
$\mathbf{B}_9$	$= z_3 \mathbf{a}_1 + (-y_3 + z_3 + \frac{1}{2}) \mathbf{a}_2 - y_3 \mathbf{a}_3$	$=$	$-a(y_3 - \frac{1}{4}) \hat{\mathbf{x}} - \frac{1}{4}a \hat{\mathbf{y}} + c(z_3 + \frac{1}{4}) \hat{\mathbf{z}}$	(16h)	O I
$\mathbf{B}_{10}$	$= z_3 \mathbf{a}_1 + (y_3 + z_3) \mathbf{a}_2 + (y_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$a(y_3 + \frac{1}{4}) \hat{\mathbf{x}} + \frac{1}{4}a \hat{\mathbf{y}} + c(z_3 - \frac{1}{4}) \hat{\mathbf{z}}$	(16h)	O I
$\mathbf{B}_{11}$	$= (y_3 - z_3 + \frac{1}{2}) \mathbf{a}_1 - z_3 \mathbf{a}_2 + (y_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$a(y_3 + \frac{1}{2}) \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(16h)	O I
$\mathbf{B}_{12}$	$= -(y_3 + z_3) \mathbf{a}_1 - z_3 \mathbf{a}_2 - y_3 \mathbf{a}_3$	$=$	$-ay_3 \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(16h)	O I
$\mathbf{B}_{13}$	$= -z_3 \mathbf{a}_1 + (y_3 - z_3 + \frac{1}{2}) \mathbf{a}_2 + y_3 \mathbf{a}_3$	$=$	$a(y_3 + \frac{1}{4}) \hat{\mathbf{x}} - \frac{1}{4}a \hat{\mathbf{y}} - c(z_3 - \frac{1}{4}) \hat{\mathbf{z}}$	(16h)	O I
$\mathbf{B}_{14}$	$= -z_3 \mathbf{a}_1 - (y_3 + z_3) \mathbf{a}_2 - (y_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(y_3 - \frac{1}{4}) \hat{\mathbf{x}} + \frac{1}{4}a \hat{\mathbf{y}} - c(z_3 + \frac{1}{4}) \hat{\mathbf{z}}$	(16h)	O I

References

- [1] D. Jarosch, *Crystal structure refinement and reflectance measurements of hausmannite, Mn_3O_4* , Mineralogy and Petrology **37**, 15–23 (1987), doi:10.1007/BF01163155.

Found in

- [1] P. Villars and L. Calvert, *Pearson's Handbook of Crystallographic Data for Intermetallic Phases* (ASM International, Materials Park, OH, 1991), 2nd edn.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1–828 (2017). doi: 10.1016/j.commatsci.2017.01.017