

R₂ Au₃Zn Structure:


A3B_oC32_64_def_d-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/GVGD>

https://aflow.org/prototype-encyclopedia/A3B_oC32_64_def_d-001

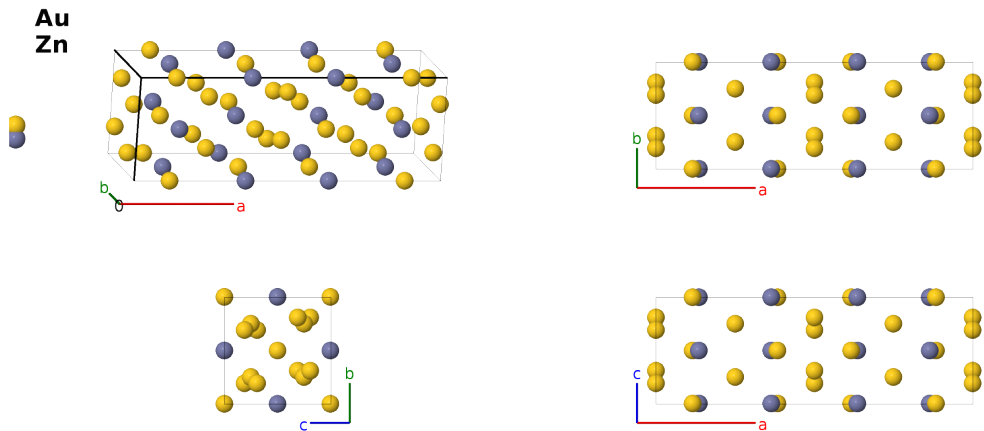


Prototype	Au ₃ Zn
AFLOW prototype label	A3B_oC32_64_def_d-001
ICSD	150693
CCDC	1667836
Pearson symbol	oC32
Space group number	64
Space group symbol	<i>Cmce</i>
AFLOW prototype command	<code>aflow --proto=A3B_oC32_64_def_d-001</code> <code>--params=a, b/a, c/a, x₁, x₂, y₃, y₄, z₄</code>

- Au₃Zn is known to exist in three forms, depending upon the exact composition and temperature (Hisatsune, 1998):
 - The tetragonal *R*₁ phase is stable below $\approx 475\text{K}$ with a composition very nearly stoichiometric.
 - The orthorhombic *R*₂ phase (this structure) is stable below $\approx 550\text{K}$ with a composition range somewhat wider than the *R*₁ phase.
 - The tetragonal *H* phase has the *D*0₂₃ structure and is stable at temperatures up to $\approx 700\text{K}$ over a considerably wider range of stoichiometries than either the *R*₁ or *R*₂ phases.
- (Iwaskai, 1962) gave structure of the *R*₂ phase in the *Abam* of space group #64. We used FINDSYM to transform this to the *Cmca* setting.

- (Iwaskai, 1962) gave the lattice constants in kX units. We used the conversion factor $1 \text{ kX} = 1.00202 \text{ \AA}$. (Wood, 1947)
- We use the orthorhombic lattice constants from (Wilkins, 1958) rather than the pseudo-tetragonal lattice constants of (Iwaskai, 1962).

Base-centered Orthorhombic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}}\end{aligned}$$

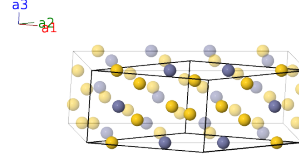

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + x_1 \mathbf{a}_2 =$		$ax_1 \hat{\mathbf{x}}$	(8d)	Au I
$\mathbf{B}_2$	$= -\left(x_1 - \frac{1}{2}\right) \mathbf{a}_1 - \left(x_1 - \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 =$		$-a\left(x_1 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$	(8d)	Au I
$\mathbf{B}_3$	$= -x_1 \mathbf{a}_1 - x_1 \mathbf{a}_2 =$		$-ax_1 \hat{\mathbf{x}}$	(8d)	Au I
$\mathbf{B}_4$	$= \left(x_1 + \frac{1}{2}\right) \mathbf{a}_1 + \left(x_1 + \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 =$		$a\left(x_1 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$	(8d)	Au I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 =$		$ax_2 \hat{\mathbf{x}}$	(8d)	Zn I
$\mathbf{B}_6$	$= -\left(x_2 - \frac{1}{2}\right) \mathbf{a}_1 - \left(x_2 - \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 =$		$-a\left(x_2 - \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$	(8d)	Zn I
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2 =$		$-ax_2 \hat{\mathbf{x}}$	(8d)	Zn I
$\mathbf{B}_8$	$= \left(x_2 + \frac{1}{2}\right) \mathbf{a}_1 + \left(x_2 + \frac{1}{2}\right) \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 =$		$a\left(x_2 + \frac{1}{2}\right) \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$	(8d)	Zn I
$\mathbf{B}_9$	$= -\left(y_3 - \frac{1}{4}\right) \mathbf{a}_1 + \left(y_3 + \frac{1}{4}\right) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3 =$		$\frac{1}{4}a \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(8e)	Au II
$\mathbf{B}_{10}$	$= \left(y_3 + \frac{1}{4}\right) \mathbf{a}_1 - \left(y_3 - \frac{1}{4}\right) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3 =$		$\frac{1}{4}a \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(8e)	Au II
$\mathbf{B}_{11}$	$= \left(y_3 + \frac{3}{4}\right) \mathbf{a}_1 - \left(y_3 - \frac{3}{4}\right) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3 =$		$\frac{3}{4}a \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(8e)	Au II
$\mathbf{B}_{12}$	$= -\left(y_3 - \frac{3}{4}\right) \mathbf{a}_1 + \left(y_3 + \frac{3}{4}\right) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3 =$		$\frac{3}{4}a \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(8e)	Au II
$\mathbf{B}_{13}$	$= -y_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3 =$		$by_4 \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(8f)	Au III
$\mathbf{B}_{14}$	$= \left(y_4 + \frac{1}{2}\right) \mathbf{a}_1 - \left(y_4 - \frac{1}{2}\right) \mathbf{a}_2 + \left(z_4 + \frac{1}{2}\right) \mathbf{a}_3 =$		$\frac{1}{2}a \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c\left(z_4 + \frac{1}{2}\right) \hat{\mathbf{z}}$	(8f)	Au III
$\mathbf{B}_{15}$	$= -\left(y_4 - \frac{1}{2}\right) \mathbf{a}_1 + \left(y_4 + \frac{1}{2}\right) \mathbf{a}_2 - \left(z_4 - \frac{1}{2}\right) \mathbf{a}_3 =$		$\frac{1}{2}a \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} - c\left(z_4 - \frac{1}{2}\right) \hat{\mathbf{z}}$	(8f)	Au III
$\mathbf{B}_{16}$	$= y_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3 =$		$-by_4 \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(8f)	Au III

References

- [1] H. Iwaskai, *Study on the Ordered Phases with Long Period in the Gold-Zinc Alloy System II. Structure Analysis of $\text{Au}_3\text{Zn}[R_1]$, $\text{Au}_3\text{Zn}[R_2]$ and Au_3+Zn* , J. Phys. Soc. Jpn. **17**, 1620–1633 (1962), doi:10.1143/JPSJ.17.1620.
- [2] E. A. Wood, *The Conversion Factor for kX Units to Angström Units*, J. Appl. Phys. **18**, 929–930 (1947), doi:10.1063/1.1697570.

Found in

- [1] K. Hisatsune, Y. Takuma, Y. Tanaka, K. Udoh, T. Morimura, and M. Hasaka, *Martensite transformation in Au_3Zn alloy*, Solid State Commun. **106**, 509–512 (1998), doi:10.1016/S0038-1098(98)00077-5.

First cited in

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.