


Cs₄Mg₃F₁₀ Structure: A4B10C3_oC68_64_2f_e2fg_af-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/B9LX>

https://aflow.org/prototype-encyclopedia/A4B10C3_oC68_64_2f_e2fg_af-001

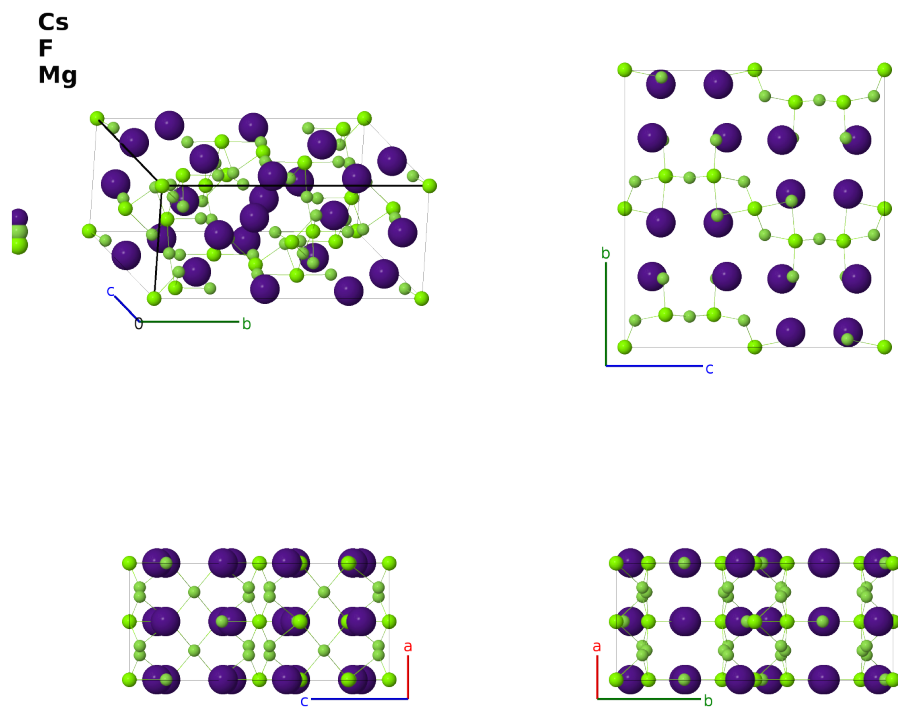

Prototype	Cs ₄ F ₁₀ Mg ₃
AFLOW prototype label	A4B10C3_oC68_64_2f_e2fg_af-001
ICSD	16084
CCDC	1596729
Pearson symbol	oC68
Space group number	64
Space group symbol	<i>Cmce</i>
AFLOW prototype command	<code>aflow --proto=A4B10C3_oC68_64_2f_e2fg_af-001</code> <code>--params=a,b/a,c/a,y₂,y₃,z₃,y₄,z₄,y₅,z₅,y₆,z₆,y₇,z₇,x₈,y₈,z₈</code>

Other compounds with this structure


Ba₄Ir₃F₁₀, Ba₄Mn₃O₁₀, Ba₄Ru₃O₁₀, Ba₄Sn₃O₁₀, Cs₄Fe₃F₁₀, Cs₄Ni₃F₁₀, Cs₄Zn₃F₁₀, Rb₄Mg₃H₁₀, Sr₄Mn₃O₁₀, Ba₄Ti₂PtO₁₀

Base-centered Orthorhombic primitive vectors

$$\mathbf{a}_1 = \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}b \hat{\mathbf{y}}$$

$$\mathbf{a}_2 = \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}b \hat{\mathbf{y}}$$

$$\mathbf{a}_3 = c \hat{\mathbf{z}}$$

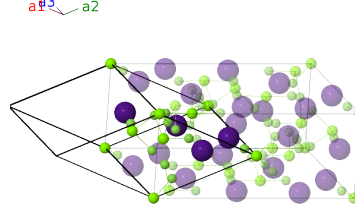

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	=	0	=	0	(4a) Mg I
$\mathbf{B}_2$	=	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4a) Mg I
$\mathbf{B}_3$	=	$-(y_2 - \frac{1}{4}) \mathbf{a}_1 + (y_2 + \frac{1}{4}) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	=	$\frac{1}{4}a \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(8e) F I
$\mathbf{B}_4$	=	$(y_2 + \frac{1}{4}) \mathbf{a}_1 - (y_2 - \frac{1}{4}) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	=	$\frac{1}{4}a \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(8e) F I
$\mathbf{B}_5$	=	$(y_2 + \frac{3}{4}) \mathbf{a}_1 - (y_2 - \frac{3}{4}) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	=	$\frac{3}{4}a \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(8e) F I
$\mathbf{B}_6$	=	$-(y_2 - \frac{3}{4}) \mathbf{a}_1 + (y_2 + \frac{3}{4}) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	=	$\frac{3}{4}a \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(8e) F I
$\mathbf{B}_7$	=	$-y_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$by_3 \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(8f) Cs I
$\mathbf{B}_8$	=	$(y_3 + \frac{1}{2}) \mathbf{a}_1 - (y_3 - \frac{1}{2}) \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(8f) Cs I
$\mathbf{B}_9$	=	$-(y_3 - \frac{1}{2}) \mathbf{a}_1 + (y_3 + \frac{1}{2}) \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(8f) Cs I
$\mathbf{B}_{10}$	=	$y_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 - z_3 \mathbf{a}_3$	=	$-by_3 \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(8f) Cs I
$\mathbf{B}_{11}$	=	$-y_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	=	$by_4 \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(8f) Cs II
$\mathbf{B}_{12}$	=	$(y_4 + \frac{1}{2}) \mathbf{a}_1 - (y_4 - \frac{1}{2}) \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(8f) Cs II
$\mathbf{B}_{13}$	=	$-(y_4 - \frac{1}{2}) \mathbf{a}_1 + (y_4 + \frac{1}{2}) \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \hat{\mathbf{z}}$	(8f) Cs II
$\mathbf{B}_{14}$	=	$y_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 - z_4 \mathbf{a}_3$	=	$-by_4 \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(8f) Cs II
$\mathbf{B}_{15}$	=	$-y_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	=	$by_5 \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(8f) F II
$\mathbf{B}_{16}$	=	$(y_5 + \frac{1}{2}) \mathbf{a}_1 - (y_5 - \frac{1}{2}) \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \hat{\mathbf{z}}$	(8f) F II
$\mathbf{B}_{17}$	=	$-(y_5 - \frac{1}{2}) \mathbf{a}_1 + (y_5 + \frac{1}{2}) \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	=	$\frac{1}{2}a \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \hat{\mathbf{z}}$	(8f) F II
$\mathbf{B}_{18}$	=	$y_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 - z_5 \mathbf{a}_3$	=	$-by_5 \hat{\mathbf{y}} - cz_5 \hat{\mathbf{z}}$	(8f) F II
$\mathbf{B}_{19}$	=	$-y_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	=	$by_6 \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}}$	(8f) F III

$$\begin{aligned}
\mathbf{B}_{20} &= \begin{pmatrix} y_6 + \frac{1}{2} \\ z_6 + \frac{1}{2} \end{pmatrix} \mathbf{a}_1 - \begin{pmatrix} y_6 - \frac{1}{2} \\ z_6 - \frac{1}{2} \end{pmatrix} \mathbf{a}_2 + \mathbf{a}_3 &= & \frac{1}{2}a \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} + c \left(z_6 + \frac{1}{2} \right) \hat{\mathbf{z}} & (8f) & \text{F III} \\
\mathbf{B}_{21} &= - \begin{pmatrix} y_6 - \frac{1}{2} \\ z_6 - \frac{1}{2} \end{pmatrix} \mathbf{a}_1 + \begin{pmatrix} y_6 + \frac{1}{2} \\ z_6 + \frac{1}{2} \end{pmatrix} \mathbf{a}_2 - \mathbf{a}_3 &= & \frac{1}{2}a \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} - c \left(z_6 - \frac{1}{2} \right) \hat{\mathbf{z}} & (8f) & \text{F III} \\
\mathbf{B}_{22} &= y_6 \mathbf{a}_1 - y_6 \mathbf{a}_2 - z_6 \mathbf{a}_3 &= & -by_6 \hat{\mathbf{y}} - cz_6 \hat{\mathbf{z}} & (8f) & \text{F III} \\
\mathbf{B}_{23} &= -y_7 \mathbf{a}_1 + y_7 \mathbf{a}_2 + z_7 \mathbf{a}_3 &= & by_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}} & (8f) & \text{Mg II} \\
\mathbf{B}_{24} &= \begin{pmatrix} y_7 + \frac{1}{2} \\ z_7 + \frac{1}{2} \end{pmatrix} \mathbf{a}_1 - \begin{pmatrix} y_7 - \frac{1}{2} \\ z_7 - \frac{1}{2} \end{pmatrix} \mathbf{a}_2 + \mathbf{a}_3 &= & \frac{1}{2}a \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} + c \left(z_7 + \frac{1}{2} \right) \hat{\mathbf{z}} & (8f) & \text{Mg II} \\
\mathbf{B}_{25} &= - \begin{pmatrix} y_7 - \frac{1}{2} \\ z_7 - \frac{1}{2} \end{pmatrix} \mathbf{a}_1 + \begin{pmatrix} y_7 + \frac{1}{2} \\ z_7 + \frac{1}{2} \end{pmatrix} \mathbf{a}_2 - \mathbf{a}_3 &= & \frac{1}{2}a \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} - c \left(z_7 - \frac{1}{2} \right) \hat{\mathbf{z}} & (8f) & \text{Mg II} \\
\mathbf{B}_{26} &= y_7 \mathbf{a}_1 - y_7 \mathbf{a}_2 - z_7 \mathbf{a}_3 &= & -by_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}} & (8f) & \text{Mg II} \\
\mathbf{B}_{27} &= (x_8 - y_8) \mathbf{a}_1 + (x_8 + y_8) \mathbf{a}_2 + z_8 \mathbf{a}_3 &= & ax_8 \hat{\mathbf{x}} + by_8 \hat{\mathbf{y}} + cz_8 \hat{\mathbf{z}} & (16g) & \text{F IV} \\
\mathbf{B}_{28} &= \begin{pmatrix} -x_8 + y_8 + \frac{1}{2} \\ x_8 + y_8 - \frac{1}{2} \end{pmatrix} \mathbf{a}_1 - \begin{pmatrix} x_8 + y_8 - \frac{1}{2} \\ x_8 + y_8 + \frac{1}{2} \end{pmatrix} \mathbf{a}_2 + \mathbf{a}_3 &= & -a \left(x_8 - \frac{1}{2} \right) \hat{\mathbf{x}} - by_8 \hat{\mathbf{y}} + c \left(z_8 + \frac{1}{2} \right) \hat{\mathbf{z}} & (16g) & \text{F IV} \\
\mathbf{B}_{29} &= \begin{pmatrix} -x_8 + y_8 - \frac{1}{2} \\ -x_8 + y_8 + \frac{1}{2} \end{pmatrix} \mathbf{a}_1 + \begin{pmatrix} x_8 + y_8 - \frac{1}{2} \\ x_8 + y_8 + \frac{1}{2} \end{pmatrix} \mathbf{a}_2 - \mathbf{a}_3 &= & -a \left(x_8 - \frac{1}{2} \right) \hat{\mathbf{x}} + by_8 \hat{\mathbf{y}} - c \left(z_8 - \frac{1}{2} \right) \hat{\mathbf{z}} & (16g) & \text{F IV} \\
\mathbf{B}_{30} &= (x_8 + y_8) \mathbf{a}_1 + (x_8 - y_8) \mathbf{a}_2 - z_8 \mathbf{a}_3 &= & ax_8 \hat{\mathbf{x}} - by_8 \hat{\mathbf{y}} - cz_8 \hat{\mathbf{z}} & (16g) & \text{F IV} \\
\mathbf{B}_{31} &= -(x_8 - y_8) \mathbf{a}_1 - (x_8 + y_8) \mathbf{a}_2 - z_8 \mathbf{a}_3 &= & -ax_8 \hat{\mathbf{x}} - by_8 \hat{\mathbf{y}} - cz_8 \hat{\mathbf{z}} & (16g) & \text{F IV} \\
\mathbf{B}_{32} &= \begin{pmatrix} x_8 - y_8 + \frac{1}{2} \\ x_8 + y_8 + \frac{1}{2} \end{pmatrix} \mathbf{a}_1 + \begin{pmatrix} x_8 + y_8 + \frac{1}{2} \\ x_8 - y_8 - \frac{1}{2} \end{pmatrix} \mathbf{a}_2 - \mathbf{a}_3 &= & a \left(x_8 + \frac{1}{2} \right) \hat{\mathbf{x}} + by_8 \hat{\mathbf{y}} - c \left(z_8 - \frac{1}{2} \right) \hat{\mathbf{z}} & (16g) & \text{F IV} \\
\mathbf{B}_{33} &= \begin{pmatrix} x_8 + y_8 + \frac{1}{2} \\ x_8 - y_8 + \frac{1}{2} \end{pmatrix} \mathbf{a}_1 + \begin{pmatrix} x_8 - y_8 + \frac{1}{2} \\ x_8 + y_8 + \frac{1}{2} \end{pmatrix} \mathbf{a}_2 + \mathbf{a}_3 &= & a \left(x_8 + \frac{1}{2} \right) \hat{\mathbf{x}} - by_8 \hat{\mathbf{y}} + c \left(z_8 + \frac{1}{2} \right) \hat{\mathbf{z}} & (16g) & \text{F IV} \\
\mathbf{B}_{34} &= -(x_8 + y_8) \mathbf{a}_1 - (x_8 - y_8) \mathbf{a}_2 + z_8 \mathbf{a}_3 &= & -ax_8 \hat{\mathbf{x}} + by_8 \hat{\mathbf{y}} + cz_8 \hat{\mathbf{z}} & (16g) & \text{F IV}
\end{aligned}$$

References

- [1] H. Steinfink and G. D. Burton, *The Crystal Structure of Cs₄Mg₃F₁₀*, Inorg. Chem. **8**, 1665–1668 (1969), doi:10.1021/ic50078a019.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.