

Tennantite ($\text{Cu}_{12}\text{As}_4\text{S}_{13}$) Structure: A4B24C13_cI82_217_c_deg_ag-001


This structure previously used the label(s) **A4B24C13_cI82_217_c_deg_ag**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/5PAV>

https://aflow.org/prototype-encyclopedia/A4B24C13_cI82_217_c_deg_ag-001

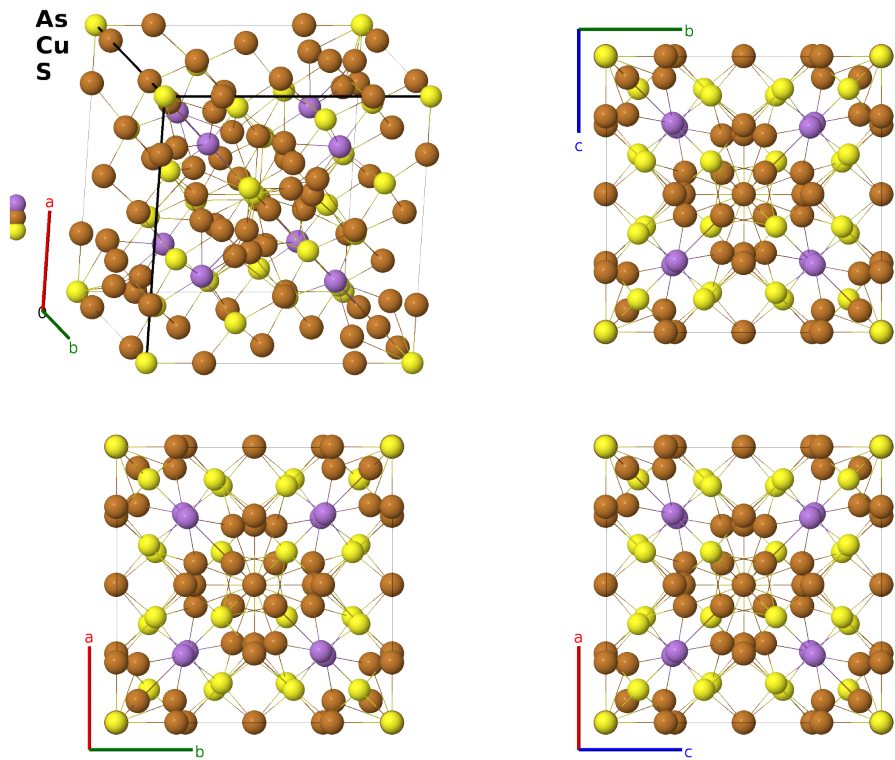

Prototype	$\text{AsCu}_{12}\text{S}_{13}$
AFLOW prototype label	A4B24C13_cI82_217_c_deg_ag-001
Mineral name	tennantite
ICSD	403458
CCDC	1910765
Pearson symbol	cI82
Space group number	217
Space group symbol	$I\bar{4}3m$
AFLOW prototype command	<code>aflow --proto=A4B24C13_cI82_217_c_deg_ag-001</code> <code>--params=$a, x_2, x_4, x_5, z_5, x_6, z_6$</code>

Other compounds with this structure

$\text{Cu}_{14}\text{Sb}_4\text{S}_{13}$ (tetrahedrite)


- The Cu-II (12e) site is only occupied 75.8% of the time, and the Cu-III site is occupied 12.1% of the time, so that these sites only contain twelve atoms between them.
- Searching (Downs, 2003) shows that natural samples often have antimony substituting for arsenic. The antimony structures (tetrahedrites) contain higher concentrations of copper.

Body-centered Cubic primitive vectors

$$\mathbf{a}_1 = -\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}a \hat{\mathbf{z}}$$

$$\mathbf{a}_2 = \frac{1}{2}a \hat{\mathbf{x}} - \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}a \hat{\mathbf{z}}$$

$$\mathbf{a}_3 = \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} - \frac{1}{2}a \hat{\mathbf{z}}$$

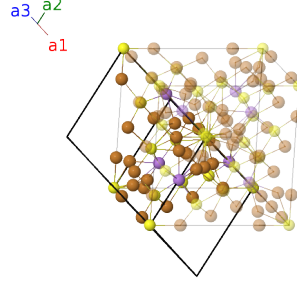

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	0	$=$	0	(2a)	S I
$\mathbf{B}_2$	$2x_2 \mathbf{a}_1 + 2x_2 \mathbf{a}_2 + 2x_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + ax_2 \hat{\mathbf{y}} + ax_2 \hat{\mathbf{z}}$	(8c)	As I
$\mathbf{B}_3$	$-2x_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} - ax_2 \hat{\mathbf{y}} + ax_2 \hat{\mathbf{z}}$	(8c)	As I
$\mathbf{B}_4$	$-2x_2 \mathbf{a}_2$	$=$	$-ax_2 \hat{\mathbf{x}} + ax_2 \hat{\mathbf{y}} - ax_2 \hat{\mathbf{z}}$	(8c)	As I
$\mathbf{B}_5$	$-2x_2 \mathbf{a}_1$	$=$	$ax_2 \hat{\mathbf{x}} - ax_2 \hat{\mathbf{y}} - ax_2 \hat{\mathbf{z}}$	(8c)	As I
$\mathbf{B}_6$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}}$	(12d)	Cu I
$\mathbf{B}_7$	$\frac{1}{2} \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{z}}$	(12d)	Cu I
$\mathbf{B}_8$	$\frac{3}{4} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}a \hat{\mathbf{y}} + \frac{1}{2}a \hat{\mathbf{z}}$	(12d)	Cu I
$\mathbf{B}_9$	$\frac{1}{4} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{4}a \hat{\mathbf{y}}$	(12d)	Cu I
$\mathbf{B}_{10}$	$\frac{1}{4} \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{4}a \hat{\mathbf{z}}$	(12d)	Cu I
$\mathbf{B}_{11}$	$\frac{3}{4} \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{4}a \hat{\mathbf{z}}$	(12d)	Cu I
$\mathbf{B}_{12}$	$x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}}$	(12e)	Cu II
$\mathbf{B}_{13}$	$-x_4 \mathbf{a}_2 - x_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}}$	(12e)	Cu II
$\mathbf{B}_{14}$	$x_4 \mathbf{a}_1 + x_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{y}}$	(12e)	Cu II
$\mathbf{B}_{15}$	$-x_4 \mathbf{a}_1 - x_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{y}}$	(12e)	Cu II
$\mathbf{B}_{16}$	$x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2$	$=$	$ax_4 \hat{\mathbf{z}}$	(12e)	Cu II
$\mathbf{B}_{17}$	$-x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2$	$=$	$-ax_4 \hat{\mathbf{z}}$	(12e)	Cu II
$\mathbf{B}_{18}$	$(x_5 + z_5) \mathbf{a}_1 + (x_5 + z_5) \mathbf{a}_2 + 2x_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} + ax_5 \hat{\mathbf{y}} + az_5 \hat{\mathbf{z}}$	(24g)	Cu III
$\mathbf{B}_{19}$	$-(x_5 - z_5) \mathbf{a}_1 - (x_5 - z_5) \mathbf{a}_2 - 2x_5 \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} - ax_5 \hat{\mathbf{y}} + az_5 \hat{\mathbf{z}}$	(24g)	Cu III
$\mathbf{B}_{20}$	$(x_5 - z_5) \mathbf{a}_1 - (x_5 + z_5) \mathbf{a}_2$	$=$	$-ax_5 \hat{\mathbf{x}} + ax_5 \hat{\mathbf{y}} - az_5 \hat{\mathbf{z}}$	(24g)	Cu III

$\mathbf{B}_{21}$	$=$	$-(x_5 + z_5) \mathbf{a}_1 + (x_5 - z_5) \mathbf{a}_2$	$=$	$ax_5 \hat{\mathbf{x}} - ax_5 \hat{\mathbf{y}} - az_5 \hat{\mathbf{z}}$	$(24g)$	Cu III
$\mathbf{B}_{22}$	$=$	$2x_5 \mathbf{a}_1 + (x_5 + z_5) \mathbf{a}_2 +$ $(x_5 + z_5) \mathbf{a}_3$	$=$	$az_5 \hat{\mathbf{x}} + ax_5 \hat{\mathbf{y}} + ax_5 \hat{\mathbf{z}}$	$(24g)$	Cu III
$\mathbf{B}_{23}$	$=$	$-2x_5 \mathbf{a}_1 - (x_5 - z_5) \mathbf{a}_2 -$ $(x_5 - z_5) \mathbf{a}_3$	$=$	$az_5 \hat{\mathbf{x}} - ax_5 \hat{\mathbf{y}} - ax_5 \hat{\mathbf{z}}$	$(24g)$	Cu III
$\mathbf{B}_{24}$	$=$	$(x_5 - z_5) \mathbf{a}_2 - (x_5 + z_5) \mathbf{a}_3$	$=$	$-az_5 \hat{\mathbf{x}} - ax_5 \hat{\mathbf{y}} + ax_5 \hat{\mathbf{z}}$	$(24g)$	Cu III
$\mathbf{B}_{25}$	$=$	$-(x_5 + z_5) \mathbf{a}_2 + (x_5 - z_5) \mathbf{a}_3$	$=$	$-az_5 \hat{\mathbf{x}} + ax_5 \hat{\mathbf{y}} - ax_5 \hat{\mathbf{z}}$	$(24g)$	Cu III
$\mathbf{B}_{26}$	$=$	$(x_5 + z_5) \mathbf{a}_1 + 2x_5 \mathbf{a}_2 +$ $(x_5 + z_5) \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} + az_5 \hat{\mathbf{y}} + ax_5 \hat{\mathbf{z}}$	$(24g)$	Cu III
$\mathbf{B}_{27}$	$=$	$-(x_5 - z_5) \mathbf{a}_1 - 2x_5 \mathbf{a}_2 -$ $(x_5 - z_5) \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} + az_5 \hat{\mathbf{y}} - ax_5 \hat{\mathbf{z}}$	$(24g)$	Cu III
$\mathbf{B}_{28}$	$=$	$-(x_5 + z_5) \mathbf{a}_1 + (x_5 - z_5) \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} - az_5 \hat{\mathbf{y}} - ax_5 \hat{\mathbf{z}}$	$(24g)$	Cu III
$\mathbf{B}_{29}$	$=$	$(x_5 - z_5) \mathbf{a}_1 - (x_5 + z_5) \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} - az_5 \hat{\mathbf{y}} + ax_5 \hat{\mathbf{z}}$	$(24g)$	Cu III
$\mathbf{B}_{30}$	$=$	$(x_6 + z_6) \mathbf{a}_1 + (x_6 + z_6) \mathbf{a}_2 +$ $2x_6 \mathbf{a}_3$	$=$	$ax_6 \hat{\mathbf{x}} + ax_6 \hat{\mathbf{y}} + az_6 \hat{\mathbf{z}}$	$(24g)$	S II
$\mathbf{B}_{31}$	$=$	$-(x_6 - z_6) \mathbf{a}_1 - (x_6 - z_6) \mathbf{a}_2 -$ $2x_6 \mathbf{a}_3$	$=$	$-ax_6 \hat{\mathbf{x}} - ax_6 \hat{\mathbf{y}} + az_6 \hat{\mathbf{z}}$	$(24g)$	S II
$\mathbf{B}_{32}$	$=$	$(x_6 - z_6) \mathbf{a}_1 - (x_6 + z_6) \mathbf{a}_2$	$=$	$-ax_6 \hat{\mathbf{x}} + ax_6 \hat{\mathbf{y}} - az_6 \hat{\mathbf{z}}$	$(24g)$	S II
$\mathbf{B}_{33}$	$=$	$-(x_6 + z_6) \mathbf{a}_1 + (x_6 - z_6) \mathbf{a}_2$	$=$	$ax_6 \hat{\mathbf{x}} - ax_6 \hat{\mathbf{y}} - az_6 \hat{\mathbf{z}}$	$(24g)$	S II
$\mathbf{B}_{34}$	$=$	$2x_6 \mathbf{a}_1 + (x_6 + z_6) \mathbf{a}_2 +$ $(x_6 + z_6) \mathbf{a}_3$	$=$	$az_6 \hat{\mathbf{x}} + ax_6 \hat{\mathbf{y}} + ax_6 \hat{\mathbf{z}}$	$(24g)$	S II
$\mathbf{B}_{35}$	$=$	$-2x_6 \mathbf{a}_1 - (x_6 - z_6) \mathbf{a}_2 -$ $(x_6 - z_6) \mathbf{a}_3$	$=$	$az_6 \hat{\mathbf{x}} - ax_6 \hat{\mathbf{y}} - ax_6 \hat{\mathbf{z}}$	$(24g)$	S II
$\mathbf{B}_{36}$	$=$	$(x_6 - z_6) \mathbf{a}_2 - (x_6 + z_6) \mathbf{a}_3$	$=$	$-az_6 \hat{\mathbf{x}} - ax_6 \hat{\mathbf{y}} + ax_6 \hat{\mathbf{z}}$	$(24g)$	S II
$\mathbf{B}_{37}$	$=$	$-(x_6 + z_6) \mathbf{a}_2 + (x_6 - z_6) \mathbf{a}_3$	$=$	$-az_6 \hat{\mathbf{x}} + ax_6 \hat{\mathbf{y}} - ax_6 \hat{\mathbf{z}}$	$(24g)$	S II
$\mathbf{B}_{38}$	$=$	$(x_6 + z_6) \mathbf{a}_1 + 2x_6 \mathbf{a}_2 +$ $(x_6 + z_6) \mathbf{a}_3$	$=$	$ax_6 \hat{\mathbf{x}} + az_6 \hat{\mathbf{y}} + ax_6 \hat{\mathbf{z}}$	$(24g)$	S II
$\mathbf{B}_{39}$	$=$	$-(x_6 - z_6) \mathbf{a}_1 - 2x_6 \mathbf{a}_2 -$ $(x_6 - z_6) \mathbf{a}_3$	$=$	$-ax_6 \hat{\mathbf{x}} + az_6 \hat{\mathbf{y}} - ax_6 \hat{\mathbf{z}}$	$(24g)$	S II
$\mathbf{B}_{40}$	$=$	$-(x_6 + z_6) \mathbf{a}_1 + (x_6 - z_6) \mathbf{a}_3$	$=$	$ax_6 \hat{\mathbf{x}} - az_6 \hat{\mathbf{y}} - ax_6 \hat{\mathbf{z}}$	$(24g)$	S II
$\mathbf{B}_{41}$	$=$	$(x_6 - z_6) \mathbf{a}_1 - (x_6 + z_6) \mathbf{a}_3$	$=$	$-ax_6 \hat{\mathbf{x}} - az_6 \hat{\mathbf{y}} + ax_6 \hat{\mathbf{z}}$	$(24g)$	S II

References

- [1] A. A. Yaroslavzev, A. V. Mironov, A. N. Kuznetsov, A. P. Dudka, and O. N. Khrykina, *Tennantite: multi-temperature crystal structure, phase transition and electronic structure of synthetic $\text{Cu}_{12}\text{As}_4\text{S}_{13}$* , Acta Crystallogr. Sect. B **75**, 634–642 (2019), doi:10.1107/S2052520619007595.
- [2] R. T. Downs and M. Hall-Wallace, *The American Mineralogist Crystal Structure Database*, Am. Mineral. **88**, 247–250 (2003).

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.