

α -Sm₃Ge₅ (High-temperature) Structure: A5B3_hP16_190_bch_g-001


This structure previously used the label(s) **A5B3_hP16_190_bdh_g**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/PJF4>

https://aflow.org/prototype-encyclopedia/A5B3_hP16_190_bch_g-001

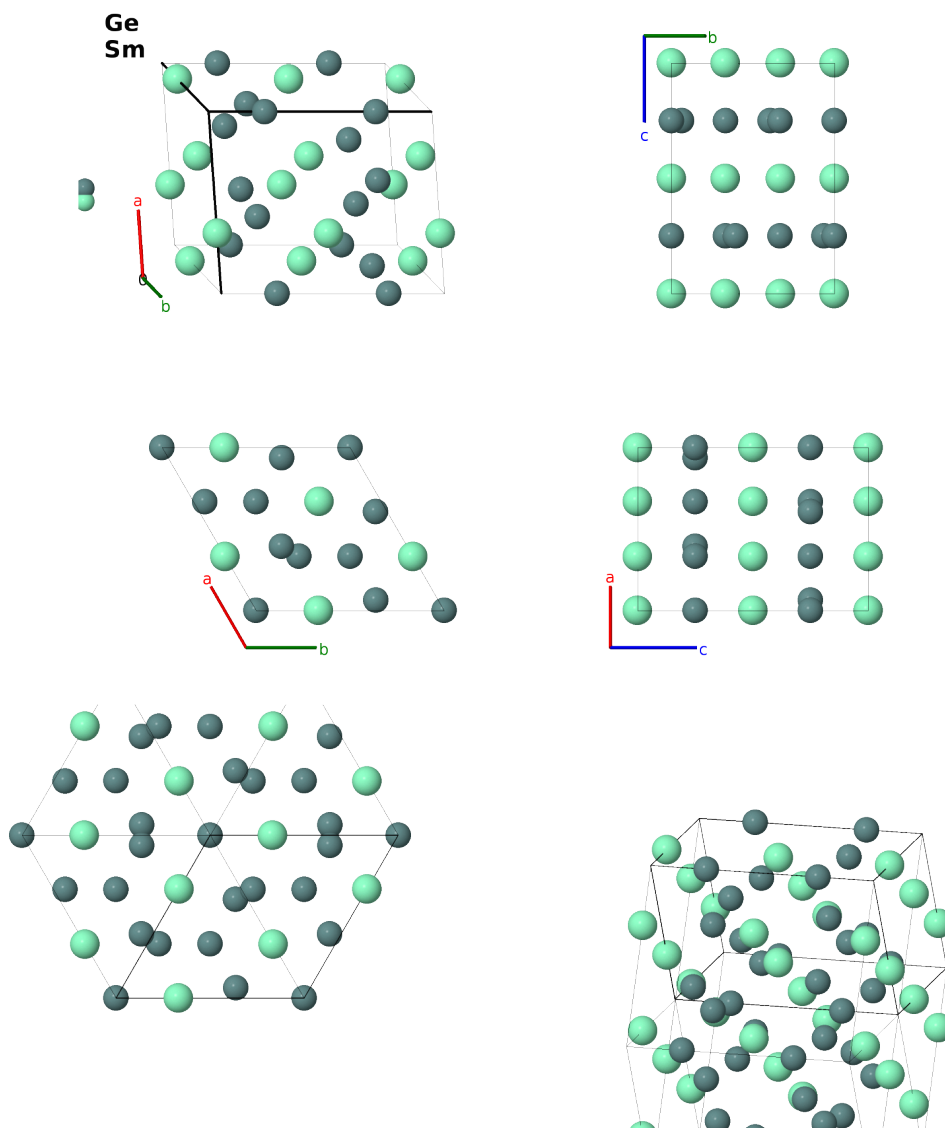


Prototype	Ge ₅ Sm ₃
AFLOW prototype label	A5B3_hP16_190_bch_g-001
ICSD	416581

CCDC	1730224
Pearson symbol	hP16
Space group number	190
Space group symbol	$P\bar{6}2c$
AFLOW prototype command	aflow --proto=A5B3_hP16_190_bch_g-001 --params= $a, c/a, x_3, x_4, y_4$

Hexagonal primitive vectors

$$\begin{aligned}
\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\
\mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\
\mathbf{a}_3 &= c \hat{\mathbf{z}}
\end{aligned}$$

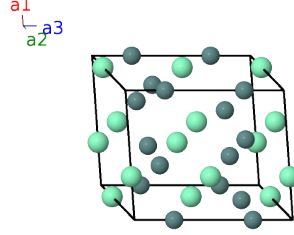

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{4}c \hat{\mathbf{z}}$	(2b)	Ge I
$\mathbf{B}_2$	$= \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{3}{4}c \hat{\mathbf{z}}$	(2b)	Ge I
$\mathbf{B}_3$	$= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(2c)	Ge II
$\mathbf{B}_4$	$= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(2c)	Ge II
$\mathbf{B}_5$	$= x_3 \mathbf{a}_1$	$=$	$\frac{1}{2}ax_3 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}}$	(6g)	Sm I
$\mathbf{B}_6$	$= x_3 \mathbf{a}_2$	$=$	$\frac{1}{2}ax_3 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}}$	(6g)	Sm I
$\mathbf{B}_7$	$= -x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2$	$=$	$-ax_3 \hat{\mathbf{x}}$	(6g)	Sm I
$\mathbf{B}_8$	$= x_3 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}ax_3 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(6g)	Sm I
$\mathbf{B}_9$	$= x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}ax_3 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(6g)	Sm I
$\mathbf{B}_{10}$	$= -x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + \frac{1}{2}c \hat{\mathbf{z}}$	(6g)	Sm I
$\mathbf{B}_{11}$	$= x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_4 + y_4) \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a(x_4 - y_4) \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6h)	Ge III
$\mathbf{B}_{12}$	$= -y_4 \mathbf{a}_1 + (x_4 - y_4) \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_4 - 2y_4) \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6h)	Ge III
$\mathbf{B}_{13}$	$= -(x_4 - y_4) \mathbf{a}_1 - x_4 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$-\frac{1}{2}a(2x_4 - y_4) \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ay_4 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6h)	Ge III
$\mathbf{B}_{14}$	$= y_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_4 + y_4) \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a(x_4 - y_4) \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6h)	Ge III
$\mathbf{B}_{15}$	$= (x_4 - y_4) \mathbf{a}_1 - y_4 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}a(x_4 - 2y_4) \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6h)	Ge III
$\mathbf{B}_{16}$	$= -x_4 \mathbf{a}_1 - (x_4 - y_4) \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-\frac{1}{2}a(2x_4 - y_4) \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ay_4 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6h)	Ge III

References

- [1] P. H. Tobash, D. Lins, S. Bobev, N. Hur, J. D. Thompson, and J. L. Sarrao, *Vacancy Ordering in SmGe_{2-x} and GdGe_{2-x} ($x = 0.33$): Structure and Properties of Two Sm_3Ge_5 Polymorphs and of Gd_3Ge_5* , Inorg. Chem. **45**, 7286–7294 (2006), doi:10.1021/ic060913f.

Found in

- [1] P. Villars and K. Cenzual, *Pearson's Crystal Data – Crystal Structure Database for Inorganic Compounds* (2013). ASM International.

First cited in

D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043