

Mavlyanovite (Mn_5Si_3 , D_{8_8}) Structure: A5B3_hP16_193_dg_g-001


This structure previously used the label(s) **A5B3_hP16_193_dg-g**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/AQ0J>

https://aflow.org/prototype-encyclopedia/A5B3_hP16_193_dg_g-001

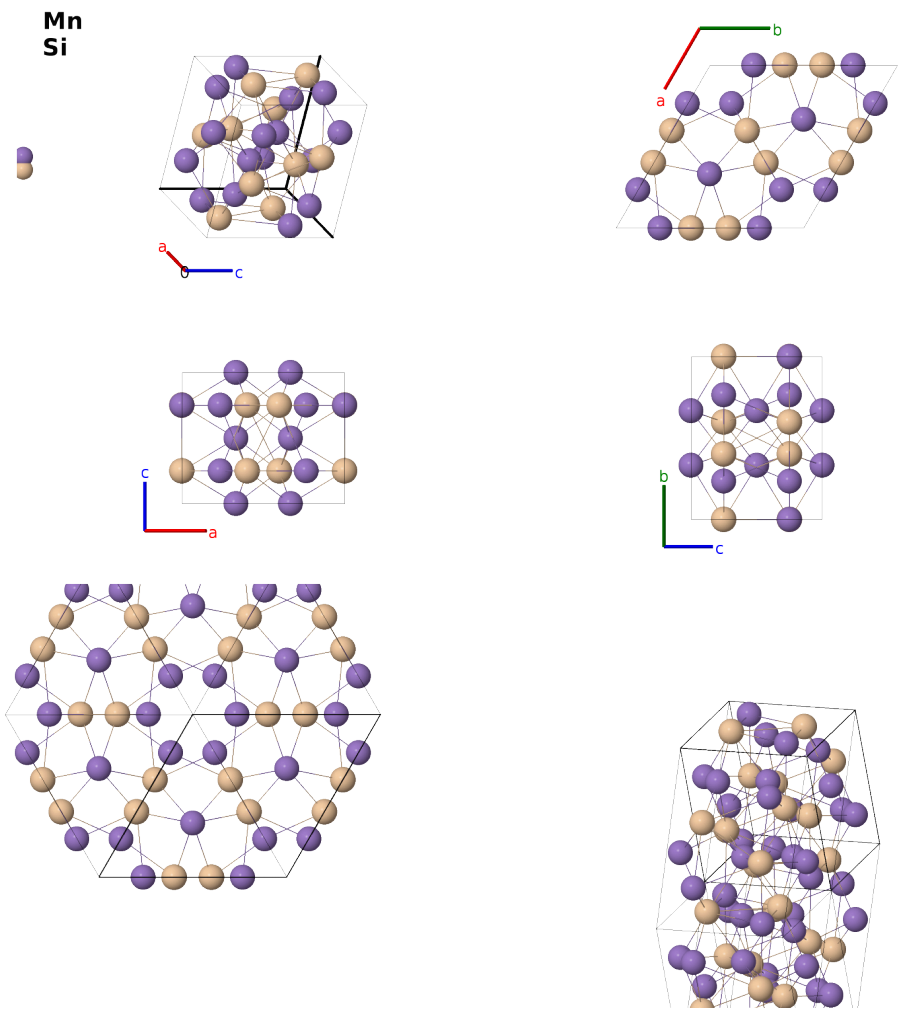


Prototype	Mn_5Si_3
AFLOW prototype label	A5B3_hP16_193_dg_g-001
<i>Strukturbericht</i> designation	D_{8_8}
Mineral name	mavlyanovite
ICSD	24359

CCDC	1600399
Pearson symbol	hP16
Space group number	193
Space group symbol	$P6_3/mcm$
AFLOW prototype command	aflow --proto=A5B3_hP16_193_dg_g-001 --params= $a, c/a, x_2, x_3$

Other compounds with this structure

Ce₅Ge₃, Ce₅Pb₃, Ce₅Sb₃, Dy₅Ge₃, Dy₅Sb₃, Er₅Si₃, Fe₅Si₃ (HT), Gd₅Ge₃, Gd₅Sb₃, Hf₅Ga₃, Hf₅Ge₃, Hf₅Si₃, Hf₅Sn₃, Ho₅Sb₃, Ho₅Sn₃, La₅Ge₃, La₅Pb₃, La₅Sb₃, Lu₅Si₃, Mg₅Hg₃, Mn₅Ge₃, Mn₅Si₃, Mo₅Si₃, Nb₅Ge₃, Nb₅Si₃, Nd₅Sb₃, Nd₅Sn₃, Pr₅Sb₃, Sc₅Ga₃, Sc₅Ge₃, Sc₅Pb₃, Sc₅Si₃, Sc₅Sn₃, Ta₅Si₃, Tb₅Sb₃, Ti₅Ga₃, Ti₅Ge₃, Ti₅P₃, Ti₅Si₃, Ti₅Sn₃, U₅Ge₃, V₅Ga₃, V₅Ge₃, V₅Si₃, W₅Si₃, Y₅Ga₃, Y₅Ge₃, Y₅Pb₃, Y₅Si₃, Y₅Sn₃, Yb₅Sb₃, Zr₅Al₃, Zr₅Ga₃, Zr₅Ge₃, Zr₅Pb₃, Zr₅Pt₃, Zr₅Sb₃, Zr₅Si₃, Zr₅Sn₃, Cr_{5-x-y}Fe_xNb_ySi₃, Mn_{5-x}Fe_xSi₃, Ti₅Ga_{1.5}Ge_{1.5}

Hexagonal primitive vectors
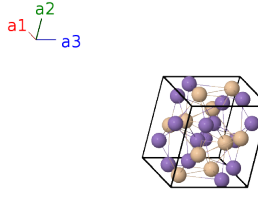
$$\begin{aligned}
 \mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\
 \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\
 \mathbf{a}_3 &= c \hat{\mathbf{z}}
 \end{aligned}$$


Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}}$	(4d)	Mn I
$\mathbf{B}_2$	$= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4d)	Mn I
$\mathbf{B}_3$	$= \frac{2}{3} \mathbf{a}_1 + \frac{1}{3} \mathbf{a}_2$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a \hat{\mathbf{y}}$	(4d)	Mn I
$\mathbf{B}_4$	$= \frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(4d)	Mn I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}ax_2 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_2 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6g)	Mn II
$\mathbf{B}_6$	$= x_2 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}ax_2 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_2 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6g)	Mn II
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6g)	Mn II
$\mathbf{B}_8$	$= -x_2 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_3$	$=$	$-\frac{1}{2}ax_2 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_2 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6g)	Mn II
$\mathbf{B}_9$	$= -x_2 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-\frac{1}{2}ax_2 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_2 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6g)	Mn II
$\mathbf{B}_{10}$	$= x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6g)	Mn II
$\mathbf{B}_{11}$	$= x_3 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}ax_3 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6g)	Si I
$\mathbf{B}_{12}$	$= x_3 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$\frac{1}{2}ax_3 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6g)	Si I
$\mathbf{B}_{13}$	$= -x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 + \frac{1}{4} \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + \frac{1}{4}c \hat{\mathbf{z}}$	(6g)	Si I
$\mathbf{B}_{14}$	$= -x_3 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_3$	$=$	$-\frac{1}{2}ax_3 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6g)	Si I
$\mathbf{B}_{15}$	$= -x_3 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$-\frac{1}{2}ax_3 \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6g)	Si I
$\mathbf{B}_{16}$	$= x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + \frac{3}{4} \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + \frac{3}{4}c \hat{\mathbf{z}}$	(6g)	Si I

References

- [1] B. Aronson, *A Note on the Compositions and Crystal Structures of MnB_2 , Mn_3Si , Mn_5Si_3 , and $FeSi_2$* , Acta Chem. Scand. **14**, 1414–1418 (1960), doi:10.3891/acta.chem.scand.14-1414.

Found in

- [1] P. Villars and K. Cenzual, *Pearson's Crystal Data – Crystal Structure Database for Inorganic Compounds* (2013). ASM International.

First cited in

D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043