$VOSO_4$ Structure: A5BC_oP28_62_3cd_c_c-001

This structure previously used the label(s) `A5BC_oP28_62_3cd_c_c`. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

---

https://aflow.org/prototype-encyclopedia/3N5K

https://aflow.org/prototype-encyclopedia/A5BC_oP28_62_3cd_c_c-001

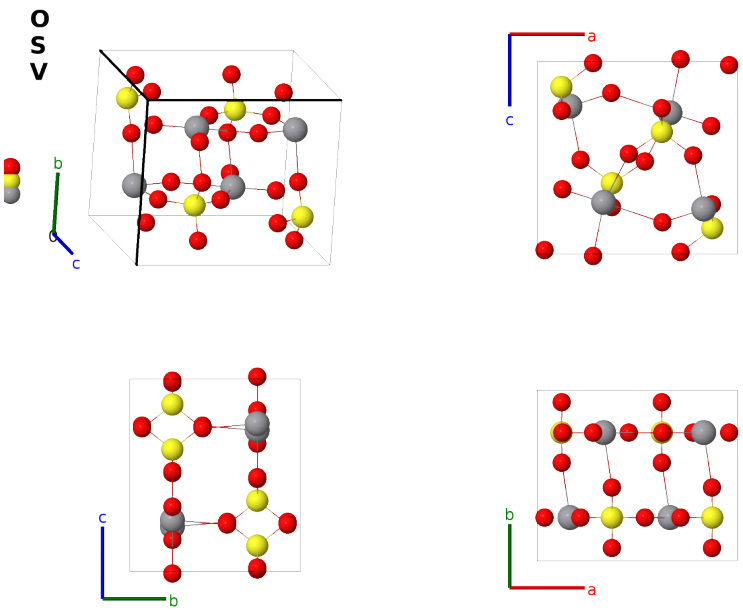

Prototype	O_5SV
AFLOW prototype label	A5BC_oP28_62_3cd_c_c-001
ICSD	24101
CCDC	1600151
Pearson symbol	oP28
Space group number	62
Space group symbol	*Pnma*
AFLOW prototype command	`aflow --proto=A5BC_oP28_62_3cd_c_c-001 --params=`$a, b/a, c/a, x_1, z_1, x_2, z_2, x_3, z_3, x_4, z_4, x_5, z_5, x_6, y_6, z_6$

- This structure consists of distorted SO_4 tetrahedra linked to distorted VO_6 tetrahedra.

Simple Orthorhombic primitive vectors

$$\mathbf{a_1} = a\,\hat{\mathbf{x}}$$
$$\mathbf{a_2} = b\,\hat{\mathbf{y}}$$
$$\mathbf{a_3} = c\,\hat{\mathbf{z}}$$

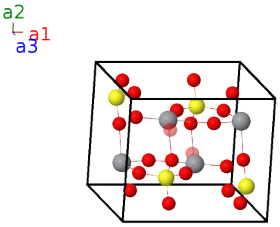

Basis vectors

		Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B_1}$	=	$x_1\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 + z_1\,\mathbf{a}_3$	=	$ax_1\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} + cz_1\,\hat{\mathbf{z}}$	(4c)	O I
$\mathbf{B_2}$	=	$-\left(x_1 - \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 + \left(z_1 + \frac{1}{2}\right)\,\mathbf{a}_3$	=	$-a\left(x_1 - \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} + c\left(z_1 + \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	O I
$\mathbf{B_3}$	=	$-x_1\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 - z_1\,\mathbf{a}_3$	=	$-ax_1\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} - cz_1\,\hat{\mathbf{z}}$	(4c)	O I
$\mathbf{B_4}$	=	$\left(x_1 + \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 - \left(z_1 - \frac{1}{2}\right)\,\mathbf{a}_3$	=	$a\left(x_1 + \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} - c\left(z_1 - \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	O I
$\mathbf{B_5}$	=	$x_2\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 + z_2\,\mathbf{a}_3$	=	$ax_2\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} + cz_2\,\hat{\mathbf{z}}$	(4c)	O II
$\mathbf{B_6}$	=	$-\left(x_2 - \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 + \left(z_2 + \frac{1}{2}\right)\,\mathbf{a}_3$	=	$-a\left(x_2 - \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} + c\left(z_2 + \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	O II
$\mathbf{B_7}$	=	$-x_2\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 - z_2\,\mathbf{a}_3$	=	$-ax_2\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} - cz_2\,\hat{\mathbf{z}}$	(4c)	O II
$\mathbf{B_8}$	=	$\left(x_2 + \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 - \left(z_2 - \frac{1}{2}\right)\,\mathbf{a}_3$	=	$a\left(x_2 + \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} - c\left(z_2 - \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	O II
$\mathbf{B_9}$	=	$x_3\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 + z_3\,\mathbf{a}_3$	=	$ax_3\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} + cz_3\,\hat{\mathbf{z}}$	(4c)	O III
$\mathbf{B_{10}}$	=	$-\left(x_3 - \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 + \left(z_3 + \frac{1}{2}\right)\,\mathbf{a}_3$	=	$-a\left(x_3 - \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} + c\left(z_3 + \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	O III
$\mathbf{B_{11}}$	=	$-x_3\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 - z_3\,\mathbf{a}_3$	=	$-ax_3\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} - cz_3\,\hat{\mathbf{z}}$	(4c)	O III
$\mathbf{B_{12}}$	=	$\left(x_3 + \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 - \left(z_3 - \frac{1}{2}\right)\,\mathbf{a}_3$	=	$a\left(x_3 + \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} - c\left(z_3 - \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	O III
$\mathbf{B_{13}}$	=	$x_4\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 + z_4\,\mathbf{a}_3$	=	$ax_4\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} + cz_4\,\hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B_{14}}$	=	$-\left(x_4 - \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 + \left(z_4 + \frac{1}{2}\right)\,\mathbf{a}_3$	=	$-a\left(x_4 - \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} + c\left(z_4 + \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B_{15}}$	=	$-x_4\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 - z_4\,\mathbf{a}_3$	=	$-ax_4\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} - cz_4\,\hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B_{16}}$	=	$\left(x_4 + \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 - \left(z_4 - \frac{1}{2}\right)\,\mathbf{a}_3$	=	$a\left(x_4 + \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} - c\left(z_4 - \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	S I
$\mathbf{B_{17}}$	=	$x_5\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 + z_5\,\mathbf{a}_3$	=	$ax_5\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} + cz_5\,\hat{\mathbf{z}}$	(4c)	V I
$\mathbf{B_{18}}$	=	$-\left(x_5 - \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 + \left(z_5 + \frac{1}{2}\right)\,\mathbf{a}_3$	=	$-a\left(x_5 - \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} + c\left(z_5 + \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	V I
$\mathbf{B_{19}}$	=	$-x_5\,\mathbf{a}_1 + \frac{3}{4}\,\mathbf{a}_2 - z_5\,\mathbf{a}_3$	=	$-ax_5\,\hat{\mathbf{x}} + \frac{3}{4}b\,\hat{\mathbf{y}} - cz_5\,\hat{\mathbf{z}}$	(4c)	V I
$\mathbf{B_{20}}$	=	$\left(x_5 + \frac{1}{2}\right)\,\mathbf{a}_1 + \frac{1}{4}\,\mathbf{a}_2 - \left(z_5 - \frac{1}{2}\right)\,\mathbf{a}_3$	=	$a\left(x_5 + \frac{1}{2}\right)\,\hat{\mathbf{x}} + \frac{1}{4}b\,\hat{\mathbf{y}} - c\left(z_5 - \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(4c)	V I
$\mathbf{B_{21}}$	=	$x_6\,\mathbf{a}_1 + y_6\,\mathbf{a}_2 + z_6\,\mathbf{a}_3$	=	$ax_6\,\hat{\mathbf{x}} + by_6\,\hat{\mathbf{y}} + cz_6\,\hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B_{22}}$	=	$-\left(x_6 - \frac{1}{2}\right)\,\mathbf{a}_1 - y_6\,\mathbf{a}_2 + \left(z_6 + \frac{1}{2}\right)\,\mathbf{a}_3$	=	$-a\left(x_6 - \frac{1}{2}\right)\,\hat{\mathbf{x}} - by_6\,\hat{\mathbf{y}} + c\left(z_6 + \frac{1}{2}\right)\,\hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B_{23}}$	=	$-x_6\,\mathbf{a}_1 + \left(y_6 + \frac{1}{2}\right)\,\mathbf{a}_2 - z_6\,\mathbf{a}_3$	=	$-ax_6\,\hat{\mathbf{x}} + b\left(y_6 + \frac{1}{2}\right)\,\hat{\mathbf{y}} - cz_6\,\hat{\mathbf{z}}$	(8d)	O IV

$\mathbf{B_{24}}$	=	$\left(x_6+\frac{1}{2}\right)\mathbf{a}_1-\left(y_6-\frac{1}{2}\right)\mathbf{a}_2-\left(z_6-\frac{1}{2}\right)\mathbf{a}_3$	=	$a\left(x_6+\frac{1}{2}\right)\hat{\mathbf{x}}-b\left(y_6-\frac{1}{2}\right)\hat{\mathbf{y}}-c\left(z_6-\frac{1}{2}\right)\hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B_{25}}$	=	$-x_6\,\mathbf{a}_1-y_6\,\mathbf{a}_2-z_6\,\mathbf{a}_3$	=	$-ax_6\,\hat{\mathbf{x}}-by_6\,\hat{\mathbf{y}}-cz_6\,\hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B_{26}}$	=	$\left(x_6+\frac{1}{2}\right)\mathbf{a}_1+y_6\,\mathbf{a}_2-\left(z_6-\frac{1}{2}\right)\mathbf{a}_3$	=	$a\left(x_6+\frac{1}{2}\right)\hat{\mathbf{x}}+by_6\,\hat{\mathbf{y}}-c\left(z_6-\frac{1}{2}\right)\hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B_{27}}$	=	$x_6\,\mathbf{a}_1-\left(y_6-\frac{1}{2}\right)\mathbf{a}_2+z_6\,\mathbf{a}_3$	=	$ax_6\,\hat{\mathbf{x}}-b\left(y_6-\frac{1}{2}\right)\hat{\mathbf{y}}+cz_6\,\hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B_{28}}$	=	$-\left(x_6-\frac{1}{2}\right)\mathbf{a}_1+\left(y_6+\frac{1}{2}\right)\mathbf{a}_2+\left(z_6+\frac{1}{2}\right)\mathbf{a}_3$	=	$-a\left(x_6-\frac{1}{2}\right)\hat{\mathbf{x}}+b\left(y_6+\frac{1}{2}\right)\hat{\mathbf{y}}+c\left(z_6+\frac{1}{2}\right)\hat{\mathbf{z}}$	(8d)	O IV

References

[1] P. Kierkegaard, J. M. Longo, and B.-O. Marinder, *Note on the Crystal Structure of $VOSO_4$*, Acta Chem. Scand. **19**, 763–764 (1965), doi:10.3891/acta.chem.scand.19-0763.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.