

CaB₆ (*D*2₁) Structure: A6B_cP7_221_e_b-001


This structure previously used the label(s) **A6B_cP7_221_f_a**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/GKJM>

https://aflow.org/prototype-encyclopedia/A6B_cP7_221_e_b-001

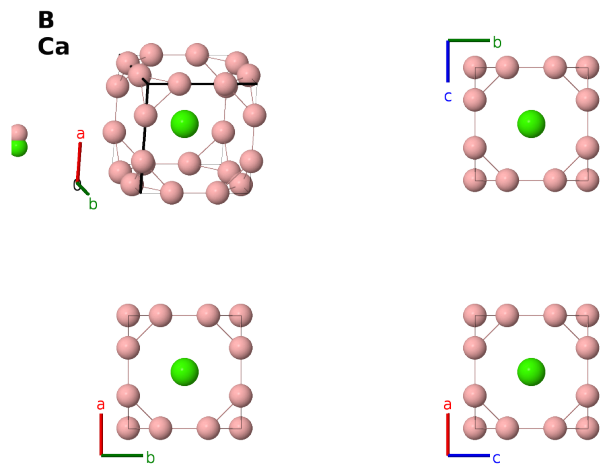

Prototype	B ₆ Ca
AFLOW prototype label	A6B_cP7_221_e_b-001
Strukturbericht designation	<i>D</i> 2 ₁
ICSD	26753
CCDC	1602139
Pearson symbol	cP7
Space group number	221
Space group symbol	<i>Pm</i> $\bar{3}$ <i>m</i>
AFLOW prototype command	<code>aflow --proto=A6B_cP7_221_e_b-001 --params=<i>a</i>, <i>x</i>₂</code>

Other compounds with this structure

BaB₆, CeB₆, DyB₆, ErB₆, EuB₆, GdB₆, HoB₆, LaB₆, LuB₆, NaB₆, NdB₆, PrB₆, PuB₆, ScB₆, SiB₆, SmB₆, SrB₆, TbB₆, ThB₆, TmB₆, YB₆, YbB₆, (Ca, Sm)B₆, (Ce, La)B₆


- The internal parameter is chosen to match the intraoctahedral boron-boron distance of 1.755 Å found in (Yahia, 1990). The ICSD entry is from (Pauling, 1934).

Simple Cubic primitive vectors

$$\mathbf{a}_1 = a \hat{\mathbf{x}}$$

$$\mathbf{a}_2 = a \hat{\mathbf{y}}$$

$$\mathbf{a}_3 = a \hat{\mathbf{z}}$$



Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}a \hat{\mathbf{z}}$	(1b)	Ca I
$\mathbf{B}_2$	$= x_2 \mathbf{a}_1$	$=$	$ax_2 \hat{\mathbf{x}}$	(6e)	B I
$\mathbf{B}_3$	$= -x_2 \mathbf{a}_1$	$=$	$-ax_2 \hat{\mathbf{x}}$	(6e)	B I
$\mathbf{B}_4$	$= x_2 \mathbf{a}_2$	$=$	$ax_2 \hat{\mathbf{y}}$	(6e)	B I
$\mathbf{B}_5$	$= -x_2 \mathbf{a}_2$	$=$	$-ax_2 \hat{\mathbf{y}}$	(6e)	B I
$\mathbf{B}_6$	$= x_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{z}}$	(6e)	B I
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{z}}$	(6e)	B I

References

- [1] Z. Yahia, S. Turrell, G. Turrell, and J. P. Mercurio, *Infrared and Raman spectra of hexaborides: force-field calculations, and isotopic effects*, J. Mol. Struct. **224**, 303–312 (1990), doi:10.1016/0022-2860(90)87025-S.
- [2] L. Pauling and S. Weinbaum, *The Structure of Calcium Boride, CaB_6* , Z. Krystallogr. **87**, 181–182 (1934), doi:10.1524/zkri.1934.87.1.181.

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017