

Possible δ -Y₂Si₂O₇ Structure: A7B2C2_oP44_62_3c2d_2c_d-001


This structure previously used the label(s) **A7B2C2_oP44_62_3c2d_2c_d**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/Y82X>

https://aflow.org/prototype-encyclopedia/A7B2C2_oP44_62_3c2d_2c_d-001

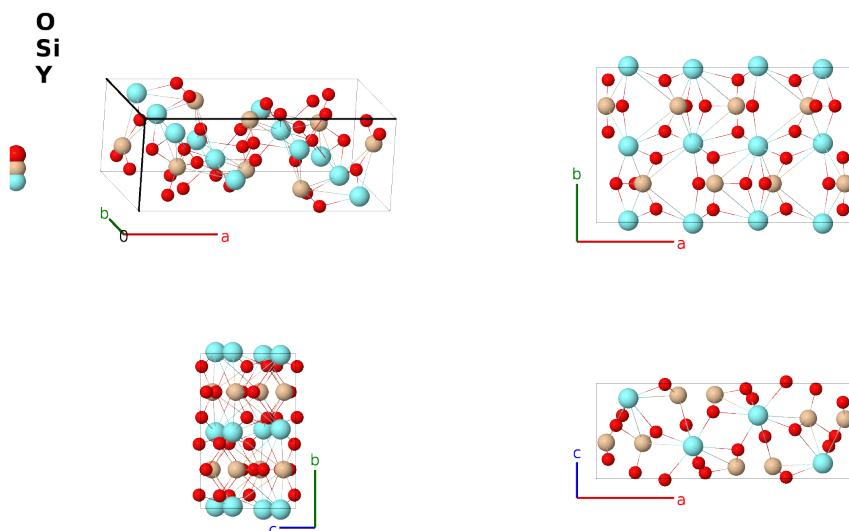

Prototype	O ₇ Si ₂ Y ₂
AFLOW prototype label	A7B2C2_oP44_62_3c2d_2c_d-001
ICSD	33721
CCDC	1606463
Pearson symbol	oP44
Space group number	62
Space group symbol	<i>Pnma</i>
AFLOW prototype command	<pre>aflow --proto=A7B2C2_oP44_62_3c2d_2c_d-001 --params=a,b/a,c/a,x₁,z₁,x₂,z₂,x₃,z₃,x₄,z₄,x₅,z₅,x₆,y₆,z₆,x₇,y₇,z₇,x₈,y₈,z₈</pre>

Other compounds with this structure


δ -Ho₂O₇Si₂, δ -Dy₂O₇Si₂, δ -Y₂O₇Si₂, Li₂S₂O₇

- (Diaz, 1990) found that some structures of RE₂O₇Si₂ (RE = Ho, Dy, Gd, Y) were in the centro-symmetric orthorhombic *Pnma* #62 space group, in which case this would be the prototype of δ -RE₂O₇Si₂ (Becerro, 2004).

- (Smolin, 1970) found δ -Gd₂O₇Si₂ to be in the non-centro-symmetric $Pna2_1$ #33 space group.
- (Becerro, 2004) found only one yttrium site in the δ -structure, supporting (Diaz, 1990).
- In addition if we allow a small amount of uncertainty (0.2Å) in the atomic positions in the $Pna2_1$ structure findsym places this structure in the $Pnma$ group.
- Nevertheless we have found no work explicitly stating that the structure of (Smolin, 1970) is in error, and indeed (Christensen, 1994) found δ -Y₂O₇Si₂ in space group $Pna2_1$. Given this ambiguity, we list Y₂O₇Si₂ only as a possible prototype for the δ -phase pyrosilicates.

Simple Orthorhombic primitive vectors

$$\begin{aligned} \mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \hat{\mathbf{z}} \end{aligned}$$

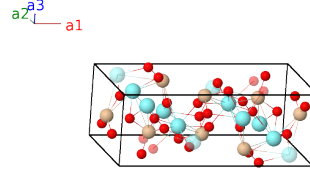

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_1 \hat{\mathbf{z}}$	(4c)	O I
$\mathbf{B}_2$	$= -(x_1 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_1 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	O I
$\mathbf{B}_3$	$= -x_1 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_1 \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_1 \hat{\mathbf{z}}$	(4c)	O I
$\mathbf{B}_4$	$= (x_1 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_1 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_1 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_1 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	O I
$\mathbf{B}_5$	$= x_2 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(4c)	O II
$\mathbf{B}_6$	$= -(x_2 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	O II
$\mathbf{B}_7$	$= -x_2 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(4c)	O II
$\mathbf{B}_8$	$= (x_2 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_2 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_2 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	O II
$\mathbf{B}_9$	$= x_3 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_3 \hat{\mathbf{z}}$	(4c)	O III
$\mathbf{B}_{10}$	$= -(x_3 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	O III
$\mathbf{B}_{11}$	$= -x_3 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_3 \hat{\mathbf{z}}$	(4c)	O III
$\mathbf{B}_{12}$	$= (x_3 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_3 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_3 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	O III
$\mathbf{B}_{13}$	$= x_4 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_4 \hat{\mathbf{z}}$	(4c)	Si I
$\mathbf{B}_{14}$	$= -(x_4 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_4 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Si I
$\mathbf{B}_{15}$	$= -x_4 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_4 \hat{\mathbf{z}}$	(4c)	Si I
$\mathbf{B}_{16}$	$= (x_4 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_4 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_4 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} - c(z_4 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Si I
$\mathbf{B}_{17}$	$= x_5 \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 + z_5 \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{x}} + \frac{1}{4}b \hat{\mathbf{y}} + cz_5 \hat{\mathbf{z}}$	(4c)	Si II
$\mathbf{B}_{18}$	$= -(x_5 - \frac{1}{2}) \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_5 - \frac{1}{2}) \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Si II
$\mathbf{B}_{19}$	$= -x_5 \mathbf{a}_1 + \frac{3}{4} \mathbf{a}_2 - z_5 \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{x}} + \frac{3}{4}b \hat{\mathbf{y}} - cz_5 \hat{\mathbf{z}}$	(4c)	Si II

$\mathbf{B}_{20} =$	$(x_5 + \frac{1}{2}) \mathbf{a}_1 + \frac{1}{4} \mathbf{a}_2 - (z_5 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_5 + \frac{1}{2}) \hat{\mathbf{x}} + \frac{1}{4}b\hat{\mathbf{y}} - c(z_5 - \frac{1}{2}) \hat{\mathbf{z}}$	(4c)	Si II
$\mathbf{B}_{21} =$	$x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$ax_6 \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B}_{22} =$	$-(x_6 - \frac{1}{2}) \mathbf{a}_1 - y_6 \mathbf{a}_2 +$ $(z_6 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_6 - \frac{1}{2}) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B}_{23} =$	$-x_6 \mathbf{a}_1 + (y_6 + \frac{1}{2}) \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$-ax_6 \hat{\mathbf{x}} + b(y_6 + \frac{1}{2}) \hat{\mathbf{y}} - cz_6 \hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B}_{24} =$	$(x_6 + \frac{1}{2}) \mathbf{a}_1 - (y_6 - \frac{1}{2}) \mathbf{a}_2 -$ $(z_6 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_6 + \frac{1}{2}) \hat{\mathbf{x}} - b(y_6 - \frac{1}{2}) \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B}_{25} =$	$-x_6 \mathbf{a}_1 - y_6 \mathbf{a}_2 - z_6 \mathbf{a}_3$	$=$	$-ax_6 \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} - cz_6 \hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B}_{26} =$	$(x_6 + \frac{1}{2}) \mathbf{a}_1 + y_6 \mathbf{a}_2 - (z_6 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_6 + \frac{1}{2}) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} - c(z_6 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B}_{27} =$	$x_6 \mathbf{a}_1 - (y_6 - \frac{1}{2}) \mathbf{a}_2 + z_6 \mathbf{a}_3$	$=$	$ax_6 \hat{\mathbf{x}} - b(y_6 - \frac{1}{2}) \hat{\mathbf{y}} + cz_6 \hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B}_{28} =$	$-(x_6 - \frac{1}{2}) \mathbf{a}_1 + (y_6 + \frac{1}{2}) \mathbf{a}_2 +$ $(z_6 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_6 - \frac{1}{2}) \hat{\mathbf{x}} + b(y_6 + \frac{1}{2}) \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	O IV
$\mathbf{B}_{29} =$	$x_7 \mathbf{a}_1 + y_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$	$=$	$ax_7 \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(8d)	O V
$\mathbf{B}_{30} =$	$-(x_7 - \frac{1}{2}) \mathbf{a}_1 - y_7 \mathbf{a}_2 +$ $(z_7 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_7 - \frac{1}{2}) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	O V
$\mathbf{B}_{31} =$	$-x_7 \mathbf{a}_1 + (y_7 + \frac{1}{2}) \mathbf{a}_2 - z_7 \mathbf{a}_3$	$=$	$-ax_7 \hat{\mathbf{x}} + b(y_7 + \frac{1}{2}) \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$	(8d)	O V
$\mathbf{B}_{32} =$	$(x_7 + \frac{1}{2}) \mathbf{a}_1 - (y_7 - \frac{1}{2}) \mathbf{a}_2 -$ $(z_7 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_7 + \frac{1}{2}) \hat{\mathbf{x}} - b(y_7 - \frac{1}{2}) \hat{\mathbf{y}} - c(z_7 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	O V
$\mathbf{B}_{33} =$	$-x_7 \mathbf{a}_1 - y_7 \mathbf{a}_2 - z_7 \mathbf{a}_3$	$=$	$-ax_7 \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} - cz_7 \hat{\mathbf{z}}$	(8d)	O V
$\mathbf{B}_{34} =$	$(x_7 + \frac{1}{2}) \mathbf{a}_1 + y_7 \mathbf{a}_2 - (z_7 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_7 + \frac{1}{2}) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} - c(z_7 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	O V
$\mathbf{B}_{35} =$	$x_7 \mathbf{a}_1 - (y_7 - \frac{1}{2}) \mathbf{a}_2 + z_7 \mathbf{a}_3$	$=$	$ax_7 \hat{\mathbf{x}} - b(y_7 - \frac{1}{2}) \hat{\mathbf{y}} + cz_7 \hat{\mathbf{z}}$	(8d)	O V
$\mathbf{B}_{36} =$	$-(x_7 - \frac{1}{2}) \mathbf{a}_1 + (y_7 + \frac{1}{2}) \mathbf{a}_2 +$ $(z_7 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_7 - \frac{1}{2}) \hat{\mathbf{x}} + b(y_7 + \frac{1}{2}) \hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	O V
$\mathbf{B}_{37} =$	$x_8 \mathbf{a}_1 + y_8 \mathbf{a}_2 + z_8 \mathbf{a}_3$	$=$	$ax_8 \hat{\mathbf{x}} + by_8 \hat{\mathbf{y}} + cz_8 \hat{\mathbf{z}}$	(8d)	Y I
$\mathbf{B}_{38} =$	$-(x_8 - \frac{1}{2}) \mathbf{a}_1 - y_8 \mathbf{a}_2 +$ $(z_8 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_8 - \frac{1}{2}) \hat{\mathbf{x}} - by_8 \hat{\mathbf{y}} + c(z_8 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Y I
$\mathbf{B}_{39} =$	$-x_8 \mathbf{a}_1 + (y_8 + \frac{1}{2}) \mathbf{a}_2 - z_8 \mathbf{a}_3$	$=$	$-ax_8 \hat{\mathbf{x}} + b(y_8 + \frac{1}{2}) \hat{\mathbf{y}} - cz_8 \hat{\mathbf{z}}$	(8d)	Y I
$\mathbf{B}_{40} =$	$(x_8 + \frac{1}{2}) \mathbf{a}_1 - (y_8 - \frac{1}{2}) \mathbf{a}_2 -$ $(z_8 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_8 + \frac{1}{2}) \hat{\mathbf{x}} - b(y_8 - \frac{1}{2}) \hat{\mathbf{y}} - c(z_8 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Y I
$\mathbf{B}_{41} =$	$-x_8 \mathbf{a}_1 - y_8 \mathbf{a}_2 - z_8 \mathbf{a}_3$	$=$	$-ax_8 \hat{\mathbf{x}} - by_8 \hat{\mathbf{y}} - cz_8 \hat{\mathbf{z}}$	(8d)	Y I
$\mathbf{B}_{42} =$	$(x_8 + \frac{1}{2}) \mathbf{a}_1 + y_8 \mathbf{a}_2 - (z_8 - \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_8 + \frac{1}{2}) \hat{\mathbf{x}} + by_8 \hat{\mathbf{y}} - c(z_8 - \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Y I
$\mathbf{B}_{43} =$	$x_8 \mathbf{a}_1 - (y_8 - \frac{1}{2}) \mathbf{a}_2 + z_8 \mathbf{a}_3$	$=$	$ax_8 \hat{\mathbf{x}} - b(y_8 - \frac{1}{2}) \hat{\mathbf{y}} + cz_8 \hat{\mathbf{z}}$	(8d)	Y I
$\mathbf{B}_{44} =$	$-(x_8 - \frac{1}{2}) \mathbf{a}_1 + (y_8 + \frac{1}{2}) \mathbf{a}_2 +$ $(z_8 + \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_8 - \frac{1}{2}) \hat{\mathbf{x}} + b(y_8 + \frac{1}{2}) \hat{\mathbf{y}} + c(z_8 + \frac{1}{2}) \hat{\mathbf{z}}$	(8d)	Y I

References

- [1] H. W. Dias, F. P. Glasser, R. P. Gunwardane, and R. A. Howie, *The crystal structure of δ -yttrium pyrosilicate, δ -Y₂Si₂O₇*, Z. Kristallogr. **191**, 117–124 (1990), doi:10.1524/zkri.1990.191.14.117.

Found in

- [1] A. I. Becerro and A. Escudero, *Revision of the crystallographic data of polymorphic Y₂Si₂O₇ and Y₂SiO₅ compounds*, Phase Transitions **77**, 1093–1102 (2004), doi:10.1080/01411590412331282814.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.