

Dy₅Pd₂ Structure:


A7B2_cF144_227_2ef_e-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/WYVV>

https://aflow.org/prototype-encyclopedia/A7B2_cF144_227_2ef_e-001

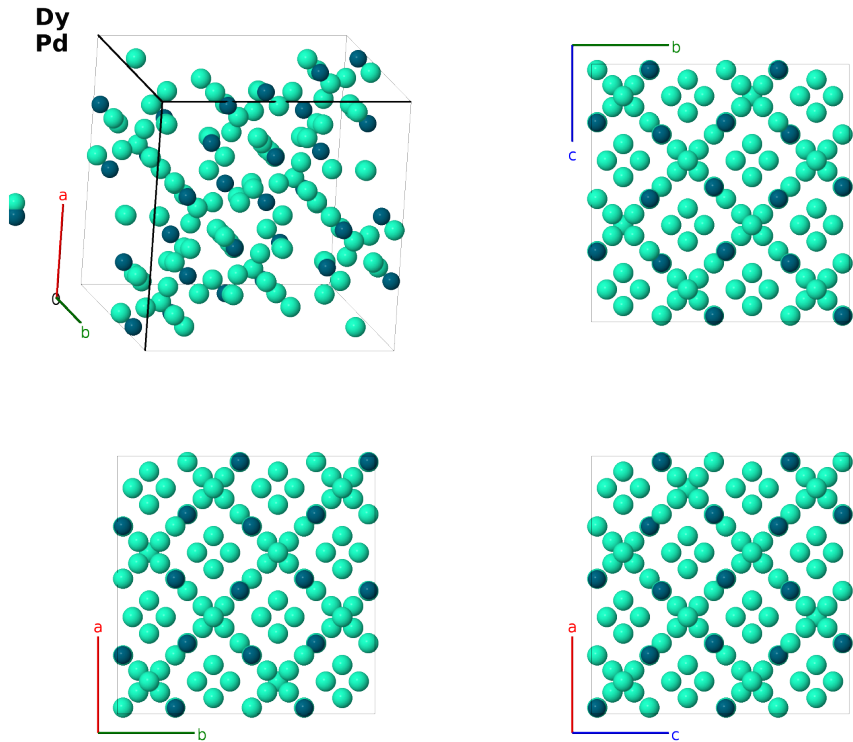

Prototype	Dy ₅ Pd ₂
AFLOW prototype label	A7B2_cF144_227_2ef_e-001
ICSD	103347
CCDC	1661292
Pearson symbol	cF144
Space group number	227
Space group symbol	$Fd\bar{3}m$
AFLOW prototype command	<pre>aflow --proto=A7B2_cF144_227_2ef_e-001 --params=a, x₁, x₂, x₃, x₄</pre>


Other compounds with this structure

Er₅Pd₂, Ho₅Pd₂, Lu₅Pd₂, Tb₅Pd₂, Tm₅Pd₂, Y₅Pd₂

- There is considerable disorder in this structure, with all of the (32e) sites having vacancies:
 - The Dy-I site is 50% occupied.
 - The Dy-II site is 12.5% occupied
 - The Pd site is 87.5% occupied.
- This gives a composition of $\text{Dy}_{2.43}\text{Pd}$.

Face-centered Cubic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}a \hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}}\end{aligned}$$

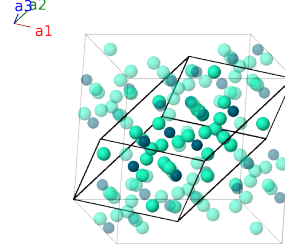

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= x_1 \mathbf{a}_1 + x_1 \mathbf{a}_2 + x_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} + ax_1 \hat{\mathbf{y}} + ax_1 \hat{\mathbf{z}}$	(32e)	Dy I
$\mathbf{B}_2$	$= x_1 \mathbf{a}_1 + x_1 \mathbf{a}_2 - (3x_1 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_1 - \frac{1}{4}) \hat{\mathbf{x}} - a(x_1 - \frac{1}{4}) \hat{\mathbf{y}} + ax_1 \hat{\mathbf{z}}$	(32e)	Dy I
$\mathbf{B}_3$	$= x_1 \mathbf{a}_1 - (3x_1 - \frac{1}{2}) \mathbf{a}_2 + x_1 \mathbf{a}_3$	$=$	$-a(x_1 - \frac{1}{4}) \hat{\mathbf{x}} + ax_1 \hat{\mathbf{y}} - a(x_1 - \frac{1}{4}) \hat{\mathbf{z}}$	(32e)	Dy I
$\mathbf{B}_4$	$= -(3x_1 - \frac{1}{2}) \mathbf{a}_1 + x_1 \mathbf{a}_2 + x_1 \mathbf{a}_3$	$=$	$ax_1 \hat{\mathbf{x}} - a(x_1 - \frac{1}{4}) \hat{\mathbf{y}} - a(x_1 - \frac{1}{4}) \hat{\mathbf{z}}$	(32e)	Dy I
$\mathbf{B}_5$	$= -x_1 \mathbf{a}_1 - x_1 \mathbf{a}_2 + (3x_1 + \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_1 + \frac{1}{4}) \hat{\mathbf{x}} + a(x_1 + \frac{1}{4}) \hat{\mathbf{y}} - ax_1 \hat{\mathbf{z}}$	(32e)	Dy I
$\mathbf{B}_6$	$= -x_1 \mathbf{a}_1 - x_1 \mathbf{a}_2 - x_1 \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} - ax_1 \hat{\mathbf{y}} - ax_1 \hat{\mathbf{z}}$	(32e)	Dy I
$\mathbf{B}_7$	$= -x_1 \mathbf{a}_1 + (3x_1 + \frac{1}{2}) \mathbf{a}_2 - x_1 \mathbf{a}_3$	$=$	$a(x_1 + \frac{1}{4}) \hat{\mathbf{x}} - ax_1 \hat{\mathbf{y}} + a(x_1 + \frac{1}{4}) \hat{\mathbf{z}}$	(32e)	Dy I
$\mathbf{B}_8$	$= (3x_1 + \frac{1}{2}) \mathbf{a}_1 - x_1 \mathbf{a}_2 - x_1 \mathbf{a}_3$	$=$	$-ax_1 \hat{\mathbf{x}} + a(x_1 + \frac{1}{4}) \hat{\mathbf{y}} + a(x_1 + \frac{1}{4}) \hat{\mathbf{z}}$	(32e)	Dy I
$\mathbf{B}_9$	$= x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + x_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} + ax_2 \hat{\mathbf{y}} + ax_2 \hat{\mathbf{z}}$	(32e)	Dy II
$\mathbf{B}_{10}$	$= x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 - (3x_2 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{4}) \hat{\mathbf{x}} - a(x_2 - \frac{1}{4}) \hat{\mathbf{y}} + ax_2 \hat{\mathbf{z}}$	(32e)	Dy II
$\mathbf{B}_{11}$	$= x_2 \mathbf{a}_1 - (3x_2 - \frac{1}{2}) \mathbf{a}_2 + x_2 \mathbf{a}_3$	$=$	$-a(x_2 - \frac{1}{4}) \hat{\mathbf{x}} + ax_2 \hat{\mathbf{y}} - a(x_2 - \frac{1}{4}) \hat{\mathbf{z}}$	(32e)	Dy II
$\mathbf{B}_{12}$	$= -(3x_2 - \frac{1}{2}) \mathbf{a}_1 + x_2 \mathbf{a}_2 + x_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{x}} - a(x_2 - \frac{1}{4}) \hat{\mathbf{y}} - a(x_2 - \frac{1}{4}) \hat{\mathbf{z}}$	(32e)	Dy II
$\mathbf{B}_{13}$	$= -x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2 + (3x_2 + \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_2 + \frac{1}{4}) \hat{\mathbf{x}} + a(x_2 + \frac{1}{4}) \hat{\mathbf{y}} - ax_2 \hat{\mathbf{z}}$	(32e)	Dy II
$\mathbf{B}_{14}$	$= -x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2 - x_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} - ax_2 \hat{\mathbf{y}} - ax_2 \hat{\mathbf{z}}$	(32e)	Dy II
$\mathbf{B}_{15}$	$= -x_2 \mathbf{a}_1 + (3x_2 + \frac{1}{2}) \mathbf{a}_2 - x_2 \mathbf{a}_3$	$=$	$a(x_2 + \frac{1}{4}) \hat{\mathbf{x}} - ax_2 \hat{\mathbf{y}} + a(x_2 + \frac{1}{4}) \hat{\mathbf{z}}$	(32e)	Dy II
$\mathbf{B}_{16}$	$= (3x_2 + \frac{1}{2}) \mathbf{a}_1 - x_2 \mathbf{a}_2 - x_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{x}} + a(x_2 + \frac{1}{4}) \hat{\mathbf{y}} + a(x_2 + \frac{1}{4}) \hat{\mathbf{z}}$	(32e)	Dy II
$\mathbf{B}_{17}$	$= x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}} + ax_3 \hat{\mathbf{z}}$	(32e)	Pd I
$\mathbf{B}_{18}$	$= x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 - (3x_3 - \frac{1}{2}) \mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{4}) \hat{\mathbf{x}} - a(x_3 - \frac{1}{4}) \hat{\mathbf{y}} + ax_3 \hat{\mathbf{z}}$	(32e)	Pd I
$\mathbf{B}_{19}$	$= x_3 \mathbf{a}_1 - (3x_3 - \frac{1}{2}) \mathbf{a}_2 + x_3 \mathbf{a}_3$	$=$	$-a(x_3 - \frac{1}{4}) \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}} - a(x_3 - \frac{1}{4}) \hat{\mathbf{z}}$	(32e)	Pd I
$\mathbf{B}_{20}$	$= -(3x_3 - \frac{1}{2}) \mathbf{a}_1 + x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} - a(x_3 - \frac{1}{4}) \hat{\mathbf{y}} - a(x_3 - \frac{1}{4}) \hat{\mathbf{z}}$	(32e)	Pd I
$\mathbf{B}_{21}$	$= -x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 + (3x_3 + \frac{1}{2}) \mathbf{a}_3$	$=$	$a(x_3 + \frac{1}{4}) \hat{\mathbf{x}} + a(x_3 + \frac{1}{4}) \hat{\mathbf{y}} - ax_3 \hat{\mathbf{z}}$	(32e)	Pd I
$\mathbf{B}_{22}$	$= -x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 - x_3 \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}} - ax_3 \hat{\mathbf{z}}$	(32e)	Pd I

$$\begin{aligned}
\mathbf{B}_{23} &= -x_3 \mathbf{a}_1 + \left(3x_3 + \frac{1}{2}\right) \mathbf{a}_2 - x_3 \mathbf{a}_3 &= a \left(x_3 + \frac{1}{4}\right) \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}} + a \left(x_3 + \frac{1}{4}\right) \hat{\mathbf{z}} &(32e) &\text{Pd I} \\
\mathbf{B}_{24} &= \left(3x_3 + \frac{1}{2}\right) \mathbf{a}_1 - x_3 \mathbf{a}_2 - x_3 \mathbf{a}_3 &= -ax_3 \hat{\mathbf{x}} + a \left(x_3 + \frac{1}{4}\right) \hat{\mathbf{y}} + a \left(x_3 + \frac{1}{4}\right) \hat{\mathbf{z}} &(32e) &\text{Pd I} \\
\mathbf{B}_{25} &= -\left(x_4 - \frac{1}{4}\right) \mathbf{a}_1 + x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3 &= ax_4 \hat{\mathbf{x}} + \frac{1}{8}a \hat{\mathbf{y}} + \frac{1}{8}a \hat{\mathbf{z}} &(48f) &\text{Dy III} \\
\mathbf{B}_{26} &= x_4 \mathbf{a}_1 - \left(x_4 - \frac{1}{4}\right) \mathbf{a}_2 - \left(x_4 - \frac{1}{4}\right) \mathbf{a}_3 &= -a \left(x_4 - \frac{1}{4}\right) \hat{\mathbf{x}} + \frac{1}{8}a \hat{\mathbf{y}} + \frac{1}{8}a \hat{\mathbf{z}} &(48f) &\text{Dy III} \\
\mathbf{B}_{27} &= x_4 \mathbf{a}_1 - \left(x_4 - \frac{1}{4}\right) \mathbf{a}_2 + x_4 \mathbf{a}_3 &= \frac{1}{8}a \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}} + \frac{1}{8}a \hat{\mathbf{z}} &(48f) &\text{Dy III} \\
\mathbf{B}_{28} &= -\left(x_4 - \frac{1}{4}\right) \mathbf{a}_1 + x_4 \mathbf{a}_2 - &= \frac{1}{8}a \hat{\mathbf{x}} - a \left(x_4 - \frac{1}{4}\right) \hat{\mathbf{y}} + \frac{1}{8}a \hat{\mathbf{z}} &(48f) &\text{Dy III} \\
&\quad \left(x_4 - \frac{1}{4}\right) \mathbf{a}_3 \\
\mathbf{B}_{29} &= x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 - \left(x_4 - \frac{1}{4}\right) \mathbf{a}_3 &= \frac{1}{8}a \hat{\mathbf{x}} + \frac{1}{8}a \hat{\mathbf{y}} + ax_4 \hat{\mathbf{z}} &(48f) &\text{Dy III} \\
\mathbf{B}_{30} &= -\left(x_4 - \frac{1}{4}\right) \mathbf{a}_1 - \left(x_4 - \frac{1}{4}\right) \mathbf{a}_2 + &= \frac{1}{8}a \hat{\mathbf{x}} + \frac{1}{8}a \hat{\mathbf{y}} - a \left(x_4 - \frac{1}{4}\right) \hat{\mathbf{z}} &(48f) &\text{Dy III} \\
&\quad x_4 \mathbf{a}_3 \\
\mathbf{B}_{31} &= \left(x_4 + \frac{3}{4}\right) \mathbf{a}_1 - x_4 \mathbf{a}_2 + \left(x_4 + \frac{3}{4}\right) \mathbf{a}_3 &= \frac{3}{8}a \hat{\mathbf{x}} + a \left(x_4 + \frac{3}{4}\right) \hat{\mathbf{y}} + \frac{3}{8}a \hat{\mathbf{z}} &(48f) &\text{Dy III} \\
\mathbf{B}_{32} &= -x_4 \mathbf{a}_1 + \left(x_4 + \frac{3}{4}\right) \mathbf{a}_2 - x_4 \mathbf{a}_3 &= \frac{3}{8}a \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}} + \frac{3}{8}a \hat{\mathbf{z}} &(48f) &\text{Dy III} \\
\mathbf{B}_{33} &= -x_4 \mathbf{a}_1 + \left(x_4 + \frac{3}{4}\right) \mathbf{a}_2 + &= a \left(x_4 + \frac{3}{4}\right) \hat{\mathbf{x}} + \frac{3}{8}a \hat{\mathbf{y}} + \frac{3}{8}a \hat{\mathbf{z}} &(48f) &\text{Dy III} \\
&\quad \left(x_4 + \frac{3}{4}\right) \mathbf{a}_3 \\
\mathbf{B}_{34} &= \left(x_4 + \frac{3}{4}\right) \mathbf{a}_1 - x_4 \mathbf{a}_2 - x_4 \mathbf{a}_3 &= -ax_4 \hat{\mathbf{x}} + \frac{3}{8}a \hat{\mathbf{y}} + \frac{3}{8}a \hat{\mathbf{z}} &(48f) &\text{Dy III} \\
\mathbf{B}_{35} &= -x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 + \left(x_4 + \frac{3}{4}\right) \mathbf{a}_3 &= \frac{3}{8}a \hat{\mathbf{x}} + \frac{3}{8}a \hat{\mathbf{y}} - ax_4 \hat{\mathbf{z}} &(48f) &\text{Dy III} \\
\mathbf{B}_{36} &= \left(x_4 + \frac{3}{4}\right) \mathbf{a}_1 + \left(x_4 + \frac{3}{4}\right) \mathbf{a}_2 - x_4 \mathbf{a}_3 &= \frac{3}{8}a \hat{\mathbf{x}} + \frac{3}{8}a \hat{\mathbf{y}} + a \left(x_4 + \frac{3}{4}\right) \hat{\mathbf{z}} &(48f) &\text{Dy III}
\end{aligned}$$

References

- [1] M. L. Fornasini and Palenzona, *Crystal structure of the so-called $R.E._5\text{Pd}_2$ compounds*, J. Less-Common Met. **38**, 77–82 (1974), doi:10.1016/0022-5088(74)90205-7.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.