

Er₂Co₇ Structure:

A7B2_hR18_166_a2cdh_2c-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/VGKE>

https://aflow.org/prototype-encyclopedia/A7B2_hR18_166_a2cdh_2c-001

Prototype	Co ₇ Er ₂
AFLOW prototype label	A7B2_hR18_166_a2cdh_2c-001
ICSD	102366
CCDC	1660349
Pearson symbol	hR18
Space group number	166
Space group symbol	$R\bar{3}m$
AFLOW prototype command	<code>aflow --proto=A7B2_hR18_166_a2cdh_2c-001</code> <code>--params=a,c/a,x₂,x₃,x₄,x₅,x₇,z₇</code>


Other compounds with this structure

Dy₂Co₇, Er₂Ni₇, Gd₂Co₇, Gd₂Ni₇, Ho₂Co₇, La₂Ni₇, Lu₂Co₇, Tb₂Co₇, Th₂Fe₇, Th₂Ni₇, Tm₂Co₇, Y₂Co₇, Y₂Ni₇

- The ICSD lists Gd₂Co₇ as the prototype, but (Ostertag, 1967) only gives atomic coordinates for Er₂Co₇, so we will use that instead.
- Hexagonal settings of this structure can be obtained with the option `--hex`.






Rhombohedral primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + \frac{1}{3}c\hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{\sqrt{3}}a\hat{\mathbf{y}} + \frac{1}{3}c\hat{\mathbf{z}} \\ \mathbf{a}_3 &= -\frac{1}{2}a\hat{\mathbf{x}} - \frac{\sqrt{3}}{6}a\hat{\mathbf{y}} + \frac{1}{3}c\hat{\mathbf{z}}\end{aligned}$$

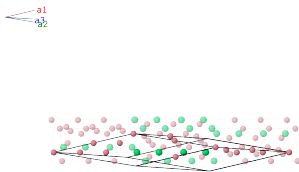

Basis vectors

Co
Er

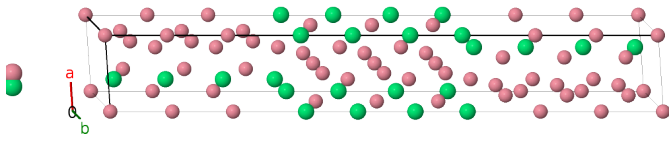

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	=	0	=	0	(1a) Co I
$\mathbf{B}_2$	=	$x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + x_2 \mathbf{a}_3$	=	$cx_2 \hat{\mathbf{z}}$	(2c) Co II
$\mathbf{B}_3$	=	$-x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2 - x_2 \mathbf{a}_3$	=	$-cx_2 \hat{\mathbf{z}}$	(2c) Co II
$\mathbf{B}_4$	=	$x_3 \mathbf{a}_1 + x_3 \mathbf{a}_2 + x_3 \mathbf{a}_3$	=	$cx_3 \hat{\mathbf{z}}$	(2c) Co III
$\mathbf{B}_5$	=	$-x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2 - x_3 \mathbf{a}_3$	=	$-cx_3 \hat{\mathbf{z}}$	(2c) Co III
$\mathbf{B}_6$	=	$x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3$	=	$cx_4 \hat{\mathbf{z}}$	(2c) Er I
$\mathbf{B}_7$	=	$-x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - x_4 \mathbf{a}_3$	=	$-cx_4 \hat{\mathbf{z}}$	(2c) Er I
$\mathbf{B}_8$	=	$x_5 \mathbf{a}_1 + x_5 \mathbf{a}_2 + x_5 \mathbf{a}_3$	=	$cx_5 \hat{\mathbf{z}}$	(2c) Er II
$\mathbf{B}_9$	=	$-x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2 - x_5 \mathbf{a}_3$	=	$-cx_5 \hat{\mathbf{z}}$	(2c) Er II
$\mathbf{B}_{10}$	=	$\frac{1}{2} \mathbf{a}_1$	=	$\frac{1}{4} a \hat{\mathbf{x}} - \frac{\sqrt{3}}{12} a \hat{\mathbf{y}} + \frac{1}{6} c \hat{\mathbf{z}}$	(3d) Co IV
$\mathbf{B}_{11}$	=	$\frac{1}{2} \mathbf{a}_2$	=	$\frac{\sqrt{3}}{6} a \hat{\mathbf{y}} + \frac{1}{6} c \hat{\mathbf{z}}$	(3d) Co IV
$\mathbf{B}_{12}$	=	$\frac{1}{2} \mathbf{a}_3$	=	$-\frac{1}{4} a \hat{\mathbf{x}} - \frac{\sqrt{3}}{12} a \hat{\mathbf{y}} + \frac{1}{6} c \hat{\mathbf{z}}$	(3d) Co IV
$\mathbf{B}_{13}$	=	$x_7 \mathbf{a}_1 + x_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$	=	$\frac{1}{2} a (x_7 - z_7) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a (x_7 - z_7) \hat{\mathbf{y}} + \frac{1}{3} c (2x_7 + z_7) \hat{\mathbf{z}}$	(6h) Co V
$\mathbf{B}_{14}$	=	$z_7 \mathbf{a}_1 + x_7 \mathbf{a}_2 + x_7 \mathbf{a}_3$	=	$-\frac{1}{2} a (x_7 - z_7) \hat{\mathbf{x}} + \frac{\sqrt{3}}{6} a (x_7 - z_7) \hat{\mathbf{y}} + \frac{1}{3} c (2x_7 + z_7) \hat{\mathbf{z}}$	(6h) Co V
$\mathbf{B}_{15}$	=	$x_7 \mathbf{a}_1 + z_7 \mathbf{a}_2 + x_7 \mathbf{a}_3$	=	$-\frac{1}{\sqrt{3}} a (x_7 - z_7) \hat{\mathbf{y}} + \frac{1}{3} c (2x_7 + z_7) \hat{\mathbf{z}}$	(6h) Co V
$\mathbf{B}_{16}$	=	$-z_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 - x_7 \mathbf{a}_3$	=	$\frac{1}{2} a (x_7 - z_7) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a (x_7 - z_7) \hat{\mathbf{y}} - \frac{1}{3} c (2x_7 + z_7) \hat{\mathbf{z}}$	(6h) Co V
$\mathbf{B}_{17}$	=	$-x_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 - z_7 \mathbf{a}_3$	=	$-\frac{1}{2} a (x_7 - z_7) \hat{\mathbf{x}} - \frac{\sqrt{3}}{6} a (x_7 - z_7) \hat{\mathbf{y}} - \frac{1}{3} c (2x_7 + z_7) \hat{\mathbf{z}}$	(6h) Co V
$\mathbf{B}_{18}$	=	$-x_7 \mathbf{a}_1 - z_7 \mathbf{a}_2 - x_7 \mathbf{a}_3$	=	$\frac{1}{\sqrt{3}} a (x_7 - z_7) \hat{\mathbf{y}} - \frac{1}{3} c (2x_7 + z_7) \hat{\mathbf{z}}$	(6h) Co V

References

- [1] W. Ostertag, *The crystal structure of Er_2Co_7 and other rare earth-cobalt compounds R_2Co_7 ($\text{R} = \text{Gd}, \text{Tb}, \text{Dy}, \text{Ho}, \text{Tm}, \text{Lu}, \text{Y}$)*, J. Less-Common Met. **13**, 385–390 (1967), doi:10.1016/0022-5088(67)90032-X.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.