

Cs₇O Structure: A7B_hP24_187_ah2j2kn_j-001







This structure previously used the label(s) **A7B_hP24_187_ai2j2kn_j**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/BZC9>

https://aflow.org/prototype-encyclopedia/A7B_hP24_187_ah2j2kn_j-001

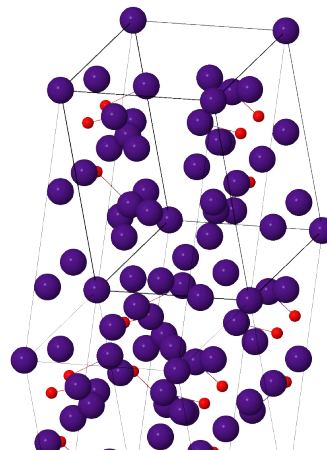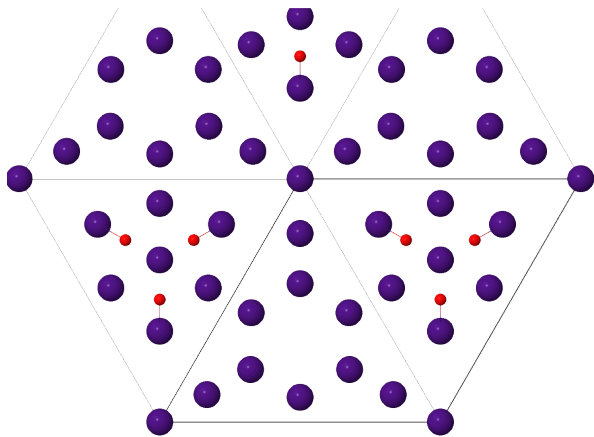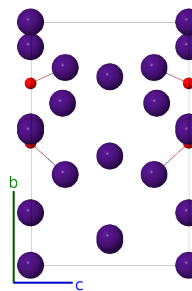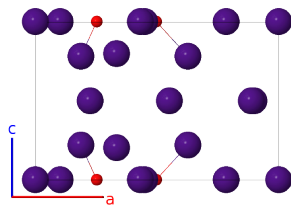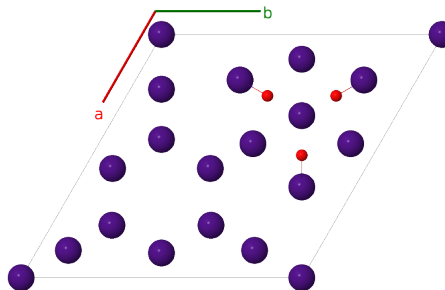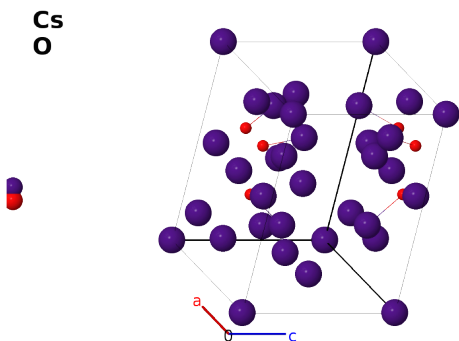


Prototype	Cs ₇ O
AFLOW prototype label	A7B_hP24_187_ah2j2kn_j-001
ICSD	111
CCDC	1590731
Pearson symbol	hP24
Space group number	187
Space group symbol	$P\bar{6}m2$
AFLOW prototype command	aflow --proto=A7B_hP24_187_ah2j2kn_j-001 --params=a, c/a, z ₂ , x ₃ , x ₄ , x ₅ , x ₆ , x ₇ , x ₈ , z ₈

- This structure is composed of Cs₁₁O₃ molecules, similar to the building blocks of the Cs₁₁O₃ structure, interlaced with cesium atoms which have approximately the same spacing as in bcc-Cs.
- Lattice constant data was given at −150°C, while the atomic positions were given at −175°C.

Hexagonal primitive vectors

$$\begin{aligned}
\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{x}} - \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\
\mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}a \hat{\mathbf{y}} \\
\mathbf{a}_3 &= c \hat{\mathbf{z}}
\end{aligned}$$

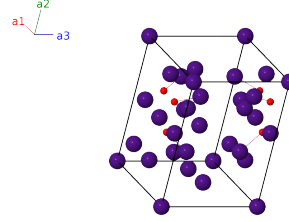

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	(1a) Cs I
$\mathbf{B}_2$	$=$	$\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 + z_2 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} + cz_2 \hat{\mathbf{z}}$	(2h) Cs II
$\mathbf{B}_3$	$=$	$\frac{1}{3} \mathbf{a}_1 + \frac{2}{3} \mathbf{a}_2 - z_2 \mathbf{a}_3$	$=$	$\frac{1}{2}a \hat{\mathbf{x}} + \frac{\sqrt{3}}{6}a \hat{\mathbf{y}} - cz_2 \hat{\mathbf{z}}$	(2h) Cs II
$\mathbf{B}_4$	$=$	$x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2$	$=$	$-\sqrt{3}ax_3 \hat{\mathbf{y}}$	(3j) Cs III
$\mathbf{B}_5$	$=$	$x_3 \mathbf{a}_1 + 2x_3 \mathbf{a}_2$	$=$	$\frac{3}{2}ax_3 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}}$	(3j) Cs III
$\mathbf{B}_6$	$=$	$-2x_3 \mathbf{a}_1 - x_3 \mathbf{a}_2$	$=$	$-\frac{3}{2}ax_3 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_3 \hat{\mathbf{y}}$	(3j) Cs III
$\mathbf{B}_7$	$=$	$x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2$	$=$	$-\sqrt{3}ax_4 \hat{\mathbf{y}}$	(3j) Cs IV
$\mathbf{B}_8$	$=$	$x_4 \mathbf{a}_1 + 2x_4 \mathbf{a}_2$	$=$	$\frac{3}{2}ax_4 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}}$	(3j) Cs IV
$\mathbf{B}_9$	$=$	$-2x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2$	$=$	$-\frac{3}{2}ax_4 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_4 \hat{\mathbf{y}}$	(3j) Cs IV
$\mathbf{B}_{10}$	$=$	$x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2$	$=$	$-\sqrt{3}ax_5 \hat{\mathbf{y}}$	(3j) O I
$\mathbf{B}_{11}$	$=$	$x_5 \mathbf{a}_1 + 2x_5 \mathbf{a}_2$	$=$	$\frac{3}{2}ax_5 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_5 \hat{\mathbf{y}}$	(3j) O I
$\mathbf{B}_{12}$	$=$	$-2x_5 \mathbf{a}_1 - x_5 \mathbf{a}_2$	$=$	$-\frac{3}{2}ax_5 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_5 \hat{\mathbf{y}}$	(3j) O I
$\mathbf{B}_{13}$	$=$	$x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-\sqrt{3}ax_6 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(3k) Cs V
$\mathbf{B}_{14}$	$=$	$x_6 \mathbf{a}_1 + 2x_6 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{3}{2}ax_6 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_6 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(3k) Cs V
$\mathbf{B}_{15}$	$=$	$-2x_6 \mathbf{a}_1 - x_6 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-\frac{3}{2}ax_6 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_6 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}}$	(3k) Cs V

$$\begin{aligned}
\mathbf{B}_{16} &= x_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 &= -\sqrt{3}ax_7 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} &(3k) &\text{Cs VI} \\
\mathbf{B}_{17} &= x_7 \mathbf{a}_1 + 2x_7 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 &= \frac{3}{2}ax_7 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_7 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} &(3k) &\text{Cs VI} \\
\mathbf{B}_{18} &= -2x_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3 &= -\frac{3}{2}ax_7 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_7 \hat{\mathbf{y}} + \frac{1}{2}c \hat{\mathbf{z}} &(3k) &\text{Cs VI} \\
\mathbf{B}_{19} &= x_8 \mathbf{a}_1 - x_8 \mathbf{a}_2 + z_8 \mathbf{a}_3 &= -\sqrt{3}ax_8 \hat{\mathbf{y}} + cz_8 \hat{\mathbf{z}} &(6n) &\text{Cs VII} \\
\mathbf{B}_{20} &= x_8 \mathbf{a}_1 + 2x_8 \mathbf{a}_2 + z_8 \mathbf{a}_3 &= \frac{3}{2}ax_8 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_8 \hat{\mathbf{y}} + cz_8 \hat{\mathbf{z}} &(6n) &\text{Cs VII} \\
\mathbf{B}_{21} &= -2x_8 \mathbf{a}_1 - x_8 \mathbf{a}_2 + z_8 \mathbf{a}_3 &= -\frac{3}{2}ax_8 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_8 \hat{\mathbf{y}} + cz_8 \hat{\mathbf{z}} &(6n) &\text{Cs VII} \\
\mathbf{B}_{22} &= x_8 \mathbf{a}_1 - x_8 \mathbf{a}_2 - z_8 \mathbf{a}_3 &= -\sqrt{3}ax_8 \hat{\mathbf{y}} - cz_8 \hat{\mathbf{z}} &(6n) &\text{Cs VII} \\
\mathbf{B}_{23} &= x_8 \mathbf{a}_1 + 2x_8 \mathbf{a}_2 - z_8 \mathbf{a}_3 &= \frac{3}{2}ax_8 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_8 \hat{\mathbf{y}} - cz_8 \hat{\mathbf{z}} &(6n) &\text{Cs VII} \\
\mathbf{B}_{24} &= -2x_8 \mathbf{a}_1 - x_8 \mathbf{a}_2 - z_8 \mathbf{a}_3 &= -\frac{3}{2}ax_8 \hat{\mathbf{x}} + \frac{\sqrt{3}}{2}ax_8 \hat{\mathbf{y}} - cz_8 \hat{\mathbf{z}} &(6n) &\text{Cs VII}
\end{aligned}$$

References

- [1] A. Simon, *Über Alkalimetall-Suboxide. VII. Das metallreichste Cäsiumoxid—Cs₇O*, Z. Anorganische und Allgemeine Chemie **422**, 208–218 (1976), doi:10.1002/zaac.19764220303.

Found in

- [1] T. B. Massalski, H. Okamoto, P. R. Subramanian, and L. Kacprzak, eds., *Binary Alloy Phase Diagrams*, vol. 2 (ASM International, Materials Park, Ohio, USA, 1990), 2nd edn. Cd-Ce to Hf-Rb.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.