

Ce₈Pd₂₄Sb Structure:


A8B24C_cP33_221_g_efh_a-001

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/CLMU>

https://aflow.org/prototype-encyclopedia/A8B24C_cP33_221_g_efh_a-001

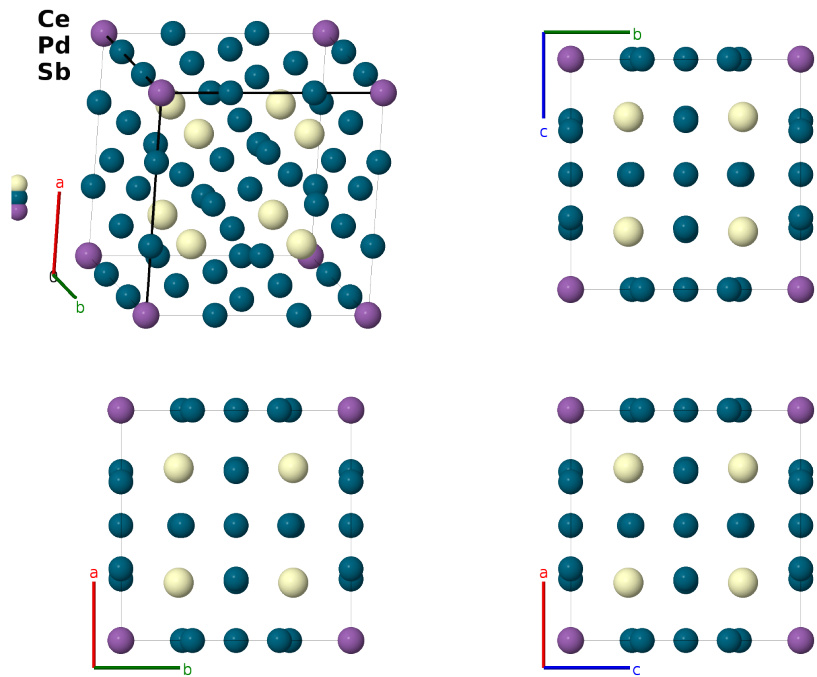

Prototype	Ce ₈ Pd ₂₄ Sb
AFLOW prototype label	A8B24C_cP33_221_g_efh_a-001
ICSD	83378
CCDC	1643425
Pearson symbol	cP33
Space group number	221
Space group symbol	$Pm\bar{3}m$
AFLOW prototype command	<code>aflow --proto=A8B24C_cP33_221_g_efh_a-001</code> <code>--params=a, x₂, x₃, x₄, x₅</code>


- CePd₃ forms in the $L1_2$ Cu₃Au Structure. Adding antimony at some octahedral sites gives this structure. Alternatively, this can be viewed as a cubic perovskite ($E2_1$) structure with 7/8 of the B atoms removed in an ordered manner.

Simple Cubic primitive vectors

$$\mathbf{a}_1 = a \hat{\mathbf{x}}$$

$$\mathbf{a}_2 = a \hat{\mathbf{y}}$$

$$\mathbf{a}_3 = a \hat{\mathbf{z}}$$

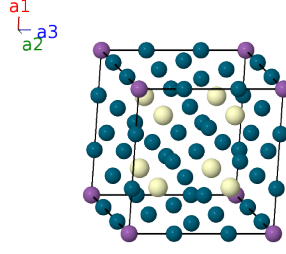

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$=$	0	$=$	0	(1a) Sb I
$\mathbf{B}_2$	$=$	$x_2 \mathbf{a}_1$	$=$	$ax_2 \hat{\mathbf{x}}$	(6e) Pd I
$\mathbf{B}_3$	$=$	$-x_2 \mathbf{a}_1$	$=$	$-ax_2 \hat{\mathbf{x}}$	(6e) Pd I
$\mathbf{B}_4$	$=$	$x_2 \mathbf{a}_2$	$=$	$ax_2 \hat{\mathbf{y}}$	(6e) Pd I
$\mathbf{B}_5$	$=$	$-x_2 \mathbf{a}_2$	$=$	$-ax_2 \hat{\mathbf{y}}$	(6e) Pd I
$\mathbf{B}_6$	$=$	$x_2 \mathbf{a}_3$	$=$	$ax_2 \hat{\mathbf{z}}$	(6e) Pd I
$\mathbf{B}_7$	$=$	$-x_2 \mathbf{a}_3$	$=$	$-ax_2 \hat{\mathbf{z}}$	(6e) Pd I
$\mathbf{B}_8$	$=$	$x_3 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$ax_3 \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(6f) Pd II
$\mathbf{B}_9$	$=$	$-x_3 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-ax_3 \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(6f) Pd II
$\mathbf{B}_{10}$	$=$	$\frac{1}{2} \mathbf{a}_1 + x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + ax_3 \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(6f) Pd II
$\mathbf{B}_{11}$	$=$	$\frac{1}{2} \mathbf{a}_1 - x_3 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} - ax_3 \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(6f) Pd II
$\mathbf{B}_{12}$	$=$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 + x_3 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} + ax_3 \hat{\mathbf{z}}$	(6f) Pd II
$\mathbf{B}_{13}$	$=$	$\frac{1}{2} \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2 - x_3 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}} - ax_3 \hat{\mathbf{z}}$	(6f) Pd II
$\mathbf{B}_{14}$	$=$	$x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}} + ax_4 \hat{\mathbf{z}}$	(8g) Ce I
$\mathbf{B}_{15}$	$=$	$-x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}} + ax_4 \hat{\mathbf{z}}$	(8g) Ce I
$\mathbf{B}_{16}$	$=$	$-x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 - x_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}} - ax_4 \hat{\mathbf{z}}$	(8g) Ce I
$\mathbf{B}_{17}$	$=$	$x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - x_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}} - ax_4 \hat{\mathbf{z}}$	(8g) Ce I
$\mathbf{B}_{18}$	$=$	$x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 - x_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}} - ax_4 \hat{\mathbf{z}}$	(8g) Ce I
$\mathbf{B}_{19}$	$=$	$-x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 - x_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}} - ax_4 \hat{\mathbf{z}}$	(8g) Ce I
$\mathbf{B}_{20}$	$=$	$x_4 \mathbf{a}_1 - x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3$	$=$	$ax_4 \hat{\mathbf{x}} - ax_4 \hat{\mathbf{y}} + ax_4 \hat{\mathbf{z}}$	(8g) Ce I
$\mathbf{B}_{21}$	$=$	$-x_4 \mathbf{a}_1 + x_4 \mathbf{a}_2 + x_4 \mathbf{a}_3$	$=$	$-ax_4 \hat{\mathbf{x}} + ax_4 \hat{\mathbf{y}} + ax_4 \hat{\mathbf{z}}$	(8g) Ce I
$\mathbf{B}_{22}$	$=$	$x_5 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2$	$=$	$ax_5 \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}}$	(12h) Pd III
$\mathbf{B}_{23}$	$=$	$-x_5 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_2$	$=$	$-ax_5 \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{y}}$	(12h) Pd III
$\mathbf{B}_{24}$	$=$	$x_5 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$ax_5 \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(12h) Pd III
$\mathbf{B}_{25}$	$=$	$-x_5 \mathbf{a}_2 + \frac{1}{2} \mathbf{a}_3$	$=$	$-ax_5 \hat{\mathbf{y}} + \frac{1}{2} a \hat{\mathbf{z}}$	(12h) Pd III
$\mathbf{B}_{26}$	$=$	$\frac{1}{2} \mathbf{a}_1 + x_5 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + ax_5 \hat{\mathbf{z}}$	(12h) Pd III
$\mathbf{B}_{27}$	$=$	$\frac{1}{2} \mathbf{a}_1 - x_5 \mathbf{a}_3$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} - ax_5 \hat{\mathbf{z}}$	(12h) Pd III
$\mathbf{B}_{28}$	$=$	$\frac{1}{2} \mathbf{a}_1 + x_5 \mathbf{a}_2$	$=$	$\frac{1}{2} a \hat{\mathbf{x}} + ax_5 \hat{\mathbf{y}}$	(12h) Pd III

$$\begin{array}{llllll}
\mathbf{B}_{29} & = & \frac{1}{2} \mathbf{a}_1 - x_5 \mathbf{a}_2 & = & \frac{1}{2} a \hat{\mathbf{x}} - ax_5 \hat{\mathbf{y}} & (12h) \quad \text{Pd III} \\
\mathbf{B}_{30} & = & x_5 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3 & = & ax_5 \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{z}} & (12h) \quad \text{Pd III} \\
\mathbf{B}_{31} & = & -x_5 \mathbf{a}_1 + \frac{1}{2} \mathbf{a}_3 & = & -ax_5 \hat{\mathbf{x}} + \frac{1}{2} a \hat{\mathbf{z}} & (12h) \quad \text{Pd III} \\
\mathbf{B}_{32} & = & \frac{1}{2} \mathbf{a}_2 - x_5 \mathbf{a}_3 & = & \frac{1}{2} a \hat{\mathbf{y}} - ax_5 \hat{\mathbf{z}} & (12h) \quad \text{Pd III} \\
\mathbf{B}_{33} & = & \frac{1}{2} \mathbf{a}_2 + x_5 \mathbf{a}_3 & = & \frac{1}{2} a \hat{\mathbf{y}} + ax_5 \hat{\mathbf{z}} & (12h) \quad \text{Pd III}
\end{array}$$

References

- [1] R. A. Gordon and F. J. DiSalvo, *Crystal Structure and Magnetic Susceptibility of $Ce_8Pd_{24}Sb$* , Z. Naturforsch. B **51**, 52–56 (1996), doi:10.1515/znb-1996-0112.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.