

Fe₈N (D_{2g}) Structure: A8B_tI18_139_deh_a-001


This structure previously used the label(s) **A8B-tI18_139_deh.a**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/6VR8>

https://aflow.org/prototype-encyclopedia/A8B_tI18_139_deh_a-001

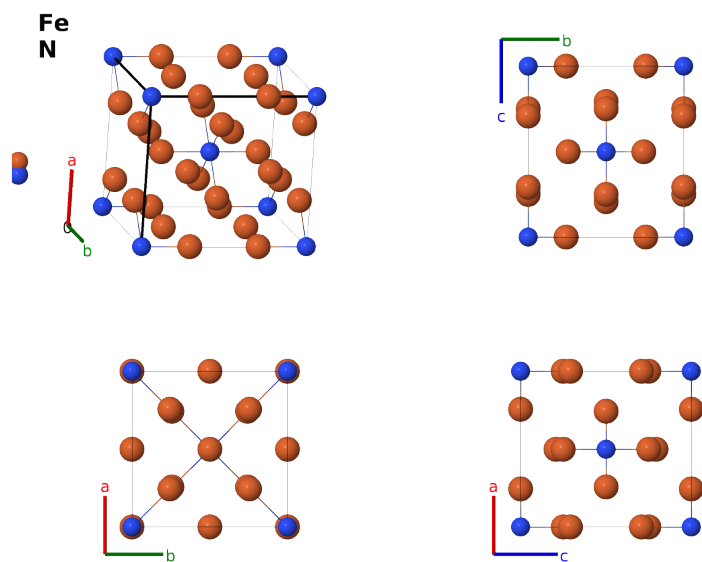


Prototype	Fe ₈ N
AFLOW prototype label	A8B_tI18_139_deh_a-001
<i>Strukturbericht</i> designation	D_{2g}
ICSD	654562
CCDC	1765762
Pearson symbol	tI18
Space group number	139
Space group symbol	$I4/mmm$
AFLOW prototype command	<code>aflow --proto=A8B_tI18_139_deh_a-001 --params=a,c/a,z₃,x₄</code>

- (Jack, 1951) and others refer to this structure as α'' -Fe₁₆N₂.

- (Yamashita, 2012) determined the structure by examining crystals containing various amounts of α'' -Fe₁₆N₂ and α -Fe (bcc iron). We use their data from the sample that was 90% α'' -Fe₁₆N₂. Their measurements were confirmed by first principles calculations and are in agreement with the first principles calculations of (Sims, 2012).
- The ICSD entry is from (Jack, 1951).

Body-centered Tetragonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= -\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} - \frac{1}{2}c\hat{\mathbf{z}}\end{aligned}$$

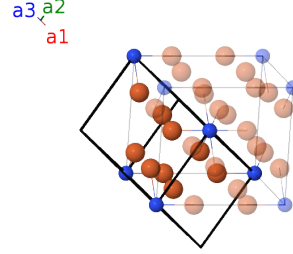

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	0	$=$	0	(2a)	N I
$\mathbf{B}_2$	$\frac{3}{4}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{4}c\hat{\mathbf{z}}$	(4d)	Fe I
$\mathbf{B}_3$	$\frac{1}{4}\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{4}c\hat{\mathbf{z}}$	(4d)	Fe I
$\mathbf{B}_4$	$z_3\mathbf{a}_1 + z_3\mathbf{a}_2$	$=$	$cz_3\hat{\mathbf{z}}$	(4e)	Fe II
$\mathbf{B}_5$	$-z_3\mathbf{a}_1 - z_3\mathbf{a}_2$	$=$	$-cz_3\hat{\mathbf{z}}$	(4e)	Fe II
$\mathbf{B}_6$	$x_4\mathbf{a}_1 + x_4\mathbf{a}_2 + 2x_4\mathbf{a}_3$	$=$	$ax_4\hat{\mathbf{x}} + ax_4\hat{\mathbf{y}}$	(8h)	Fe III
$\mathbf{B}_7$	$-x_4\mathbf{a}_1 - x_4\mathbf{a}_2 - 2x_4\mathbf{a}_3$	$=$	$-ax_4\hat{\mathbf{x}} - ax_4\hat{\mathbf{y}}$	(8h)	Fe III
$\mathbf{B}_8$	$x_4\mathbf{a}_1 - x_4\mathbf{a}_2$	$=$	$-ax_4\hat{\mathbf{x}} + ax_4\hat{\mathbf{y}}$	(8h)	Fe III
$\mathbf{B}_9$	$-x_4\mathbf{a}_1 + x_4\mathbf{a}_2$	$=$	$ax_4\hat{\mathbf{x}} - ax_4\hat{\mathbf{y}}$	(8h)	Fe III

References

- [1] S. Yamashita, Y. Masubuchi, Y. Nakazawa, T. Okayama, M. Tsuchiya, and S. Kikkawa, *Crystal structure and magnetic properties of “ α'' -Fe₁₆N₂” containing residual α -Fe prepared by low-temperature ammonia nitridation*, J. Solid State Chem. **194**, 76–79 (2012), doi:10.1016/j.jssc.2012.07.025.
- [2] K. H. Jack, *The occurrence and the crystal structure of α'' -iron nitride; a new type of interstitial alloy formed during the tempering of nitrogen-martensite*, Proc. R. Soc. A Math. Phys. Eng. Sci. **208**, 216–217 (1951), doi:10.1098/rspa.1951.0155.
- [3] H. Sims, W. H. Butler, M. Richter, K. Koepf, E. Şaşıoğlu, C. Friedrich, and S. Blügel, *Theoretical investigation into the possibility of very large moments in Fe₁₆N₂*, Phys. Rev. B **86**, 174422 (2012), doi:10.1103/PhysRevB.86.174422.

First cited in

D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.