

# Model of Ferrite Structure (cF128): A9B16C7\_cF128\_225\_acd\_2f\_be-001


This structure previously used the label(s) **A9B16C7\_cF128\_225\_acd\_2f\_be**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Osos, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/FENM>

[https://aflow.org/prototype-encyclopedia/A9B16C7\\_cF128\\_225\\_acd\\_2f\\_be-001](https://aflow.org/prototype-encyclopedia/A9B16C7_cF128_225_acd_2f_be-001)

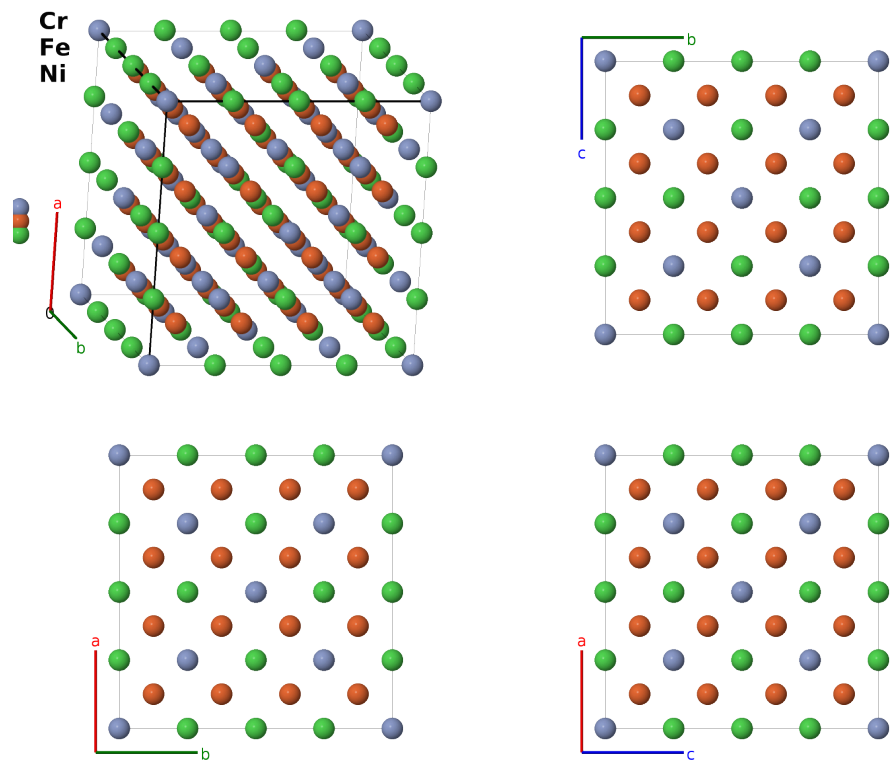

|                         |                                                                                                                                    |
|-------------------------|------------------------------------------------------------------------------------------------------------------------------------|
| Prototype               | Cr <sub>9</sub> Fe <sub>16</sub> Ni <sub>7</sub>                                                                                   |
| AFLOW prototype label   | A9B16C7_cF128_225_acd_2f_be-001                                                                                                    |
| Pearson symbol          | cF128                                                                                                                              |
| Space group number      | 225                                                                                                                                |
| Space group symbol      | $Fm\bar{3}m$                                                                                                                       |
| AFLOW prototype command | <code>aflow --proto=A9B16C7_cF128_225_acd_2f_be-001</code><br><code>--params=a, x<sub>5</sub>, x<sub>6</sub>, x<sub>7</sub></code> |


- Ferritic steels are alloys of iron and other metals with an averaged body-centered cubic structure. This model represents one approximation for a ferritic steel. It is not meant to represent a real steel, and the selection of atom types for each Wyckoff position is arbitrary.

- If we set  $x_5 = 1/4$ ,  $x_6 = 1/8$ , and  $x_7 = 3/8$  and replace the nickel atoms by chromium, this structure reverts to CsCl ( $B2$ ) with  $a_{B2} = 1/4a$ .
- If we replace both the nickel and chromium atoms by iron the structure becomes a body-centered cubic lattice ( $A2$ ) again with  $a_{A2} = 1/4a$ .

---

### Face-centered Cubic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}a\hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}}\end{aligned}$$

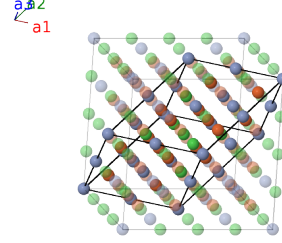


---

### Basis vectors

|                   | Lattice<br>coordinates |                                                                               | Cartesian<br>coordinates | Wyckoff<br>position                                                                          | Atom<br>type |
|-------------------|------------------------|-------------------------------------------------------------------------------|--------------------------|----------------------------------------------------------------------------------------------|--------------|
| $\mathbf{B}_1$    | $=$                    | $0$                                                                           | $=$                      | $0$                                                                                          | Cr I         |
| $\mathbf{B}_2$    | $=$                    | $\frac{1}{2}\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$ | $=$                      | $\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}a\hat{\mathbf{z}}$ | (4b) Ni I    |
| $\mathbf{B}_3$    | $=$                    | $\frac{1}{4}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + \frac{1}{4}\mathbf{a}_3$ | $=$                      | $\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{y}} + \frac{1}{4}a\hat{\mathbf{z}}$ | (8c) Cr II   |
| $\mathbf{B}_4$    | $=$                    | $\frac{3}{4}\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2 + \frac{3}{4}\mathbf{a}_3$ | $=$                      | $\frac{3}{4}a\hat{\mathbf{x}} + \frac{3}{4}a\hat{\mathbf{y}} + \frac{3}{4}a\hat{\mathbf{z}}$ | (8c) Cr II   |
| $\mathbf{B}_5$    | $=$                    | $\frac{1}{2}\mathbf{a}_1$                                                     | $=$                      | $\frac{1}{4}a\hat{\mathbf{y}} + \frac{1}{4}a\hat{\mathbf{z}}$                                | (24d) Cr III |
| $\mathbf{B}_6$    | $=$                    | $\frac{1}{2}\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$                           | $=$                      | $\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{y}} + \frac{1}{4}a\hat{\mathbf{z}}$ | (24d) Cr III |
| $\mathbf{B}_7$    | $=$                    | $\frac{1}{2}\mathbf{a}_2$                                                     | $=$                      | $\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{z}}$                                | (24d) Cr III |
| $\mathbf{B}_8$    | $=$                    | $\frac{1}{2}\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_3$                           | $=$                      | $\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{4}a\hat{\mathbf{z}}$ | (24d) Cr III |
| $\mathbf{B}_9$    | $=$                    | $\frac{1}{2}\mathbf{a}_3$                                                     | $=$                      | $\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{y}}$                                | (24d) Cr III |
| $\mathbf{B}_{10}$ | $=$                    | $\frac{1}{2}\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_2$                           | $=$                      | $\frac{1}{4}a\hat{\mathbf{x}} + \frac{1}{4}a\hat{\mathbf{y}} + \frac{1}{2}a\hat{\mathbf{z}}$ | (24d) Cr III |
| $\mathbf{B}_{11}$ | $=$                    | $-x_5\mathbf{a}_1 + x_5\mathbf{a}_2 + x_5\mathbf{a}_3$                        | $=$                      | $ax_5\hat{\mathbf{x}}$                                                                       | (24e) Ni II  |
| $\mathbf{B}_{12}$ | $=$                    | $x_5\mathbf{a}_1 - x_5\mathbf{a}_2 - x_5\mathbf{a}_3$                         | $=$                      | $-ax_5\hat{\mathbf{x}}$                                                                      | (24e) Ni II  |
| $\mathbf{B}_{13}$ | $=$                    | $x_5\mathbf{a}_1 - x_5\mathbf{a}_2 + x_5\mathbf{a}_3$                         | $=$                      | $ax_5\hat{\mathbf{y}}$                                                                       | (24e) Ni II  |
| $\mathbf{B}_{14}$ | $=$                    | $-x_5\mathbf{a}_1 + x_5\mathbf{a}_2 - x_5\mathbf{a}_3$                        | $=$                      | $-ax_5\hat{\mathbf{y}}$                                                                      | (24e) Ni II  |
| $\mathbf{B}_{15}$ | $=$                    | $x_5\mathbf{a}_1 + x_5\mathbf{a}_2 - x_5\mathbf{a}_3$                         | $=$                      | $ax_5\hat{\mathbf{z}}$                                                                       | (24e) Ni II  |
| $\mathbf{B}_{16}$ | $=$                    | $-x_5\mathbf{a}_1 - x_5\mathbf{a}_2 + x_5\mathbf{a}_3$                        | $=$                      | $-ax_5\hat{\mathbf{z}}$                                                                      | (24e) Ni II  |
| $\mathbf{B}_{17}$ | $=$                    | $x_6\mathbf{a}_1 + x_6\mathbf{a}_2 + x_6\mathbf{a}_3$                         | $=$                      | $ax_6\hat{\mathbf{x}} + ax_6\hat{\mathbf{y}} + ax_6\hat{\mathbf{z}}$                         | (32f) Fe I   |
| $\mathbf{B}_{18}$ | $=$                    | $x_6\mathbf{a}_1 + x_6\mathbf{a}_2 - 3x_6\mathbf{a}_3$                        | $=$                      | $-ax_6\hat{\mathbf{x}} - ax_6\hat{\mathbf{y}} + ax_6\hat{\mathbf{z}}$                        | (32f) Fe I   |
| $\mathbf{B}_{19}$ | $=$                    | $x_6\mathbf{a}_1 - 3x_6\mathbf{a}_2 + x_6\mathbf{a}_3$                        | $=$                      | $-ax_6\hat{\mathbf{x}} + ax_6\hat{\mathbf{y}} - ax_6\hat{\mathbf{z}}$                        | (32f) Fe I   |
| $\mathbf{B}_{20}$ | $=$                    | $-3x_6\mathbf{a}_1 + x_6\mathbf{a}_2 + x_6\mathbf{a}_3$                       | $=$                      | $ax_6\hat{\mathbf{x}} - ax_6\hat{\mathbf{y}} - ax_6\hat{\mathbf{z}}$                         | (32f) Fe I   |
| $\mathbf{B}_{21}$ | $=$                    | $-x_6\mathbf{a}_1 - x_6\mathbf{a}_2 + 3x_6\mathbf{a}_3$                       | $=$                      | $ax_6\hat{\mathbf{x}} + ax_6\hat{\mathbf{y}} - ax_6\hat{\mathbf{z}}$                         | (32f) Fe I   |
| $\mathbf{B}_{22}$ | $=$                    | $-x_6\mathbf{a}_1 - x_6\mathbf{a}_2 - x_6\mathbf{a}_3$                        | $=$                      | $-ax_6\hat{\mathbf{x}} - ax_6\hat{\mathbf{y}} - ax_6\hat{\mathbf{z}}$                        | (32f) Fe I   |
| $\mathbf{B}_{23}$ | $=$                    | $-x_6\mathbf{a}_1 + 3x_6\mathbf{a}_2 - x_6\mathbf{a}_3$                       | $=$                      | $ax_6\hat{\mathbf{x}} - ax_6\hat{\mathbf{y}} + ax_6\hat{\mathbf{z}}$                         | (32f) Fe I   |
| $\mathbf{B}_{24}$ | $=$                    | $3x_6\mathbf{a}_1 - x_6\mathbf{a}_2 - x_6\mathbf{a}_3$                        | $=$                      | $-ax_6\hat{\mathbf{x}} + ax_6\hat{\mathbf{y}} + ax_6\hat{\mathbf{z}}$                        | (32f) Fe I   |

|                   |     |                                                            |     |                                                                          |       |       |
|-------------------|-----|------------------------------------------------------------|-----|--------------------------------------------------------------------------|-------|-------|
| $\mathbf{B}_{25}$ | $=$ | $x_7 \mathbf{a}_1 + x_7 \mathbf{a}_2 + x_7 \mathbf{a}_3$   | $=$ | $ax_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} + ax_7 \hat{\mathbf{z}}$  | (32f) | Fe II |
| $\mathbf{B}_{26}$ | $=$ | $x_7 \mathbf{a}_1 + x_7 \mathbf{a}_2 - 3x_7 \mathbf{a}_3$  | $=$ | $-ax_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} + ax_7 \hat{\mathbf{z}}$ | (32f) | Fe II |
| $\mathbf{B}_{27}$ | $=$ | $x_7 \mathbf{a}_1 - 3x_7 \mathbf{a}_2 + x_7 \mathbf{a}_3$  | $=$ | $-ax_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} - ax_7 \hat{\mathbf{z}}$ | (32f) | Fe II |
| $\mathbf{B}_{28}$ | $=$ | $-3x_7 \mathbf{a}_1 + x_7 \mathbf{a}_2 + x_7 \mathbf{a}_3$ | $=$ | $ax_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} - ax_7 \hat{\mathbf{z}}$  | (32f) | Fe II |
| $\mathbf{B}_{29}$ | $=$ | $-x_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 + 3x_7 \mathbf{a}_3$ | $=$ | $ax_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} - ax_7 \hat{\mathbf{z}}$  | (32f) | Fe II |
| $\mathbf{B}_{30}$ | $=$ | $-x_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 - x_7 \mathbf{a}_3$  | $=$ | $-ax_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} - ax_7 \hat{\mathbf{z}}$ | (32f) | Fe II |
| $\mathbf{B}_{31}$ | $=$ | $-x_7 \mathbf{a}_1 + 3x_7 \mathbf{a}_2 - x_7 \mathbf{a}_3$ | $=$ | $ax_7 \hat{\mathbf{x}} - ax_7 \hat{\mathbf{y}} + ax_7 \hat{\mathbf{z}}$  | (32f) | Fe II |
| $\mathbf{B}_{32}$ | $=$ | $3x_7 \mathbf{a}_1 - x_7 \mathbf{a}_2 - x_7 \mathbf{a}_3$  | $=$ | $-ax_7 \hat{\mathbf{x}} + ax_7 \hat{\mathbf{y}} + ax_7 \hat{\mathbf{z}}$ | (32f) | Fe II |

## References

- [1] M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW library of crystallographic prototypes: part 1*, Comput. Mater. Sci. **136**, S1–S828 (2017), doi:10.1016/j.commatsci.2017.01.017.

## First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017