

Rh₂Ga₉ Structure: A9B2_mP22_7_9a_2a-001


This structure previously used the label(s) **A9B2_mP22_7_9a_2a**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/2DRY>

https://aflow.org/prototype-encyclopedia/A9B2_mP22_7_9a_2a-001

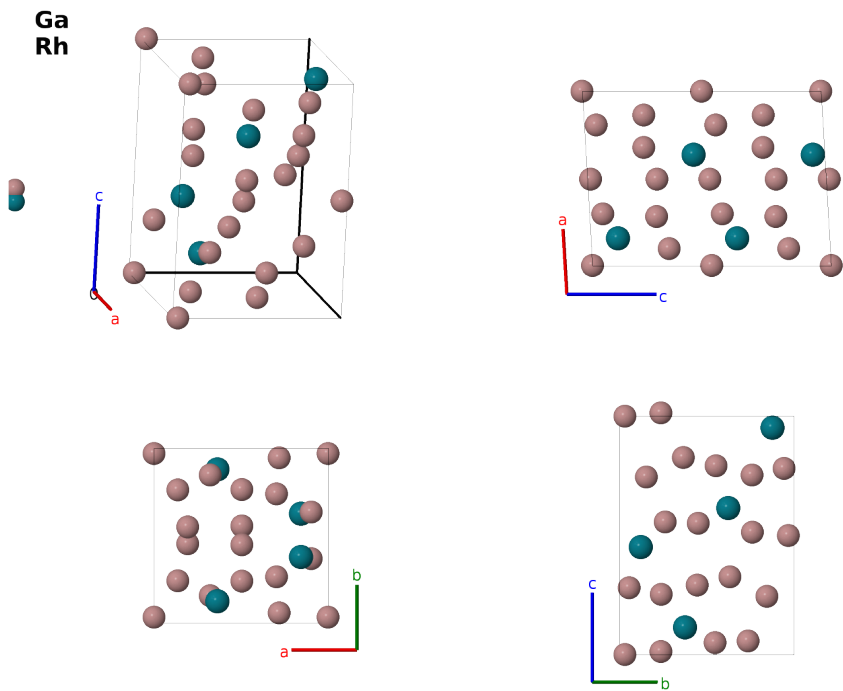


Prototype	Ga ₉ Rh ₂
AFLOW prototype label	A9B2_mP22_7_9a_2a-001
ICSD	414305
CCDC	1776436
Pearson symbol	mP22
Space group number	7
Space group symbol	<i>Pc</i>
AFLOW prototype command	<code>aflow --proto=A9B2_mP22_7_9a_2a-001</code> <code>--params=a,b/a,c/a,β,x₁,y₁,z₁,x₂,y₂,z₂,x₃,y₃,z₃,x₄,y₄,z₄,x₅,y₅,z₅,x₆,y₆,z₆,x₇,y₇,z₇,x₈,y₈,z₈,x₉,y₉,z₉,x₁₀,y₁₀,z₁₀,x₁₁,y₁₁,z₁₁</code>

Other compounds with this structure

Ir_2Ga_9

Simple Monoclinic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= a \hat{\mathbf{x}} \\ \mathbf{a}_2 &= b \hat{\mathbf{y}} \\ \mathbf{a}_3 &= c \cos \beta \hat{\mathbf{x}} + c \sin \beta \hat{\mathbf{z}}\end{aligned}$$

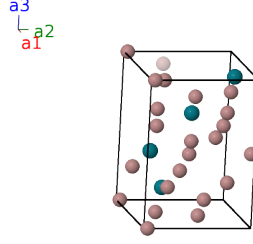

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$x_1 \mathbf{a}_1 + y_1 \mathbf{a}_2 + z_1 \mathbf{a}_3$	=	$(ax_1 + cz_1 \cos \beta) \hat{\mathbf{x}} + by_1 \hat{\mathbf{y}} + cz_1 \sin \beta \hat{\mathbf{z}}$	(2a)	Ga I
$\mathbf{B}_2$	$x_1 \mathbf{a}_1 - y_1 \mathbf{a}_2 + (z_1 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_1 + c(z_1 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_1 \hat{\mathbf{y}} + c(z_1 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(2a)	Ga I
$\mathbf{B}_3$	$x_2 \mathbf{a}_1 + y_2 \mathbf{a}_2 + z_2 \mathbf{a}_3$	=	$(ax_2 + cz_2 \cos \beta) \hat{\mathbf{x}} + by_2 \hat{\mathbf{y}} + cz_2 \sin \beta \hat{\mathbf{z}}$	(2a)	Ga II
$\mathbf{B}_4$	$x_2 \mathbf{a}_1 - y_2 \mathbf{a}_2 + (z_2 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_2 + c(z_2 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_2 \hat{\mathbf{y}} + c(z_2 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(2a)	Ga II
$\mathbf{B}_5$	$x_3 \mathbf{a}_1 + y_3 \mathbf{a}_2 + z_3 \mathbf{a}_3$	=	$(ax_3 + cz_3 \cos \beta) \hat{\mathbf{x}} + by_3 \hat{\mathbf{y}} + cz_3 \sin \beta \hat{\mathbf{z}}$	(2a)	Ga III
$\mathbf{B}_6$	$x_3 \mathbf{a}_1 - y_3 \mathbf{a}_2 + (z_3 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_3 + c(z_3 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_3 \hat{\mathbf{y}} + c(z_3 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(2a)	Ga III
$\mathbf{B}_7$	$x_4 \mathbf{a}_1 + y_4 \mathbf{a}_2 + z_4 \mathbf{a}_3$	=	$(ax_4 + cz_4 \cos \beta) \hat{\mathbf{x}} + by_4 \hat{\mathbf{y}} + cz_4 \sin \beta \hat{\mathbf{z}}$	(2a)	Ga IV
$\mathbf{B}_8$	$x_4 \mathbf{a}_1 - y_4 \mathbf{a}_2 + (z_4 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_4 + c(z_4 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_4 \hat{\mathbf{y}} + c(z_4 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(2a)	Ga IV
$\mathbf{B}_9$	$x_5 \mathbf{a}_1 + y_5 \mathbf{a}_2 + z_5 \mathbf{a}_3$	=	$(ax_5 + cz_5 \cos \beta) \hat{\mathbf{x}} + by_5 \hat{\mathbf{y}} + cz_5 \sin \beta \hat{\mathbf{z}}$	(2a)	Ga V
$\mathbf{B}_{10}$	$x_5 \mathbf{a}_1 - y_5 \mathbf{a}_2 + (z_5 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_5 + c(z_5 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_5 \hat{\mathbf{y}} + c(z_5 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(2a)	Ga V
$\mathbf{B}_{11}$	$x_6 \mathbf{a}_1 + y_6 \mathbf{a}_2 + z_6 \mathbf{a}_3$	=	$(ax_6 + cz_6 \cos \beta) \hat{\mathbf{x}} + by_6 \hat{\mathbf{y}} + cz_6 \sin \beta \hat{\mathbf{z}}$	(2a)	Ga VI
$\mathbf{B}_{12}$	$x_6 \mathbf{a}_1 - y_6 \mathbf{a}_2 + (z_6 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_6 + c(z_6 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_6 \hat{\mathbf{y}} + c(z_6 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(2a)	Ga VI
$\mathbf{B}_{13}$	$x_7 \mathbf{a}_1 + y_7 \mathbf{a}_2 + z_7 \mathbf{a}_3$	=	$(ax_7 + cz_7 \cos \beta) \hat{\mathbf{x}} + by_7 \hat{\mathbf{y}} + cz_7 \sin \beta \hat{\mathbf{z}}$	(2a)	Ga VII
$\mathbf{B}_{14}$	$x_7 \mathbf{a}_1 - y_7 \mathbf{a}_2 + (z_7 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_7 + c(z_7 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_7 \hat{\mathbf{y}} + c(z_7 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(2a)	Ga VII
$\mathbf{B}_{15}$	$x_8 \mathbf{a}_1 + y_8 \mathbf{a}_2 + z_8 \mathbf{a}_3$	=	$(ax_8 + cz_8 \cos \beta) \hat{\mathbf{x}} + by_8 \hat{\mathbf{y}} + cz_8 \sin \beta \hat{\mathbf{z}}$	(2a)	Ga VIII
$\mathbf{B}_{16}$	$x_8 \mathbf{a}_1 - y_8 \mathbf{a}_2 + (z_8 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_8 + c(z_8 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_8 \hat{\mathbf{y}} + c(z_8 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(2a)	Ga VIII
$\mathbf{B}_{17}$	$x_9 \mathbf{a}_1 + y_9 \mathbf{a}_2 + z_9 \mathbf{a}_3$	=	$(ax_9 + cz_9 \cos \beta) \hat{\mathbf{x}} + by_9 \hat{\mathbf{y}} + cz_9 \sin \beta \hat{\mathbf{z}}$	(2a)	Ga IX
$\mathbf{B}_{18}$	$x_9 \mathbf{a}_1 - y_9 \mathbf{a}_2 + (z_9 + \frac{1}{2}) \mathbf{a}_3$	=	$(ax_9 + c(z_9 + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_9 \hat{\mathbf{y}} + c(z_9 + \frac{1}{2}) \sin \beta \hat{\mathbf{z}}$	(2a)	Ga IX
$\mathbf{B}_{19}$	$x_{10} \mathbf{a}_1 + y_{10} \mathbf{a}_2 + z_{10} \mathbf{a}_3$	=	$(ax_{10} + cz_{10} \cos \beta) \hat{\mathbf{x}} + by_{10} \hat{\mathbf{y}} + cz_{10} \sin \beta \hat{\mathbf{z}}$	(2a)	Rh I

$$\begin{aligned}
\mathbf{B}_{20} &= x_{10} \mathbf{a}_1 - y_{10} \mathbf{a}_2 + \left(z_{10} + \frac{1}{2}\right) \mathbf{a}_3 &= \begin{pmatrix} (ax_{10} + c(z_{10} + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_{10} \hat{\mathbf{y}} + \\ c(z_{10} + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} &(2a) &\text{Rh I} \\
\mathbf{B}_{21} &= x_{11} \mathbf{a}_1 + y_{11} \mathbf{a}_2 + z_{11} \mathbf{a}_3 &= (ax_{11} + cz_{11} \cos \beta) \hat{\mathbf{x}} + by_{11} \hat{\mathbf{y}} + cz_{11} \sin \beta \hat{\mathbf{z}} &(2a) &\text{Rh II} \\
\mathbf{B}_{22} &= x_{11} \mathbf{a}_1 - y_{11} \mathbf{a}_2 + \left(z_{11} + \frac{1}{2}\right) \mathbf{a}_3 &= \begin{pmatrix} (ax_{11} + c(z_{11} + \frac{1}{2}) \cos \beta) \hat{\mathbf{x}} - by_{11} \hat{\mathbf{y}} + \\ c(z_{11} + \frac{1}{2}) \sin \beta \hat{\mathbf{z}} \end{pmatrix} &(2a) &\text{Rh II}
\end{aligned}$$

References

- [1] M. Boström, H. Rosner, Y. Prots, U. Burkhardt, and Y. Grin, *The Co_2Al_9 Structure Type Revisited*, Z. Anorganische und Allgemeine Chemie **631**, 534–541 (2005), doi:10.1002/zaac.200400418.

Found in

- [1] P. Villars and K. Cenzual, *Pearson's Crystal Data – Crystal Structure Database for Inorganic Compounds* (2013). ASM International.

First cited in

- D. Hicks, M. J. Mehl, E. Gossett, C. Toher, O. Levy, R. M. Hanson, G. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 2*, Comput. Mater. Sci. **161**, S1 (2019). doi: 10.1016/j.commatsci.2018.10.043