

BaZnSb₂ Structure:


AB2C_tI16_139_e_ce_d-003

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/00JM>

https://aflow.org/prototype-encyclopedia/AB2C_tI16_139_e_ce_d-003

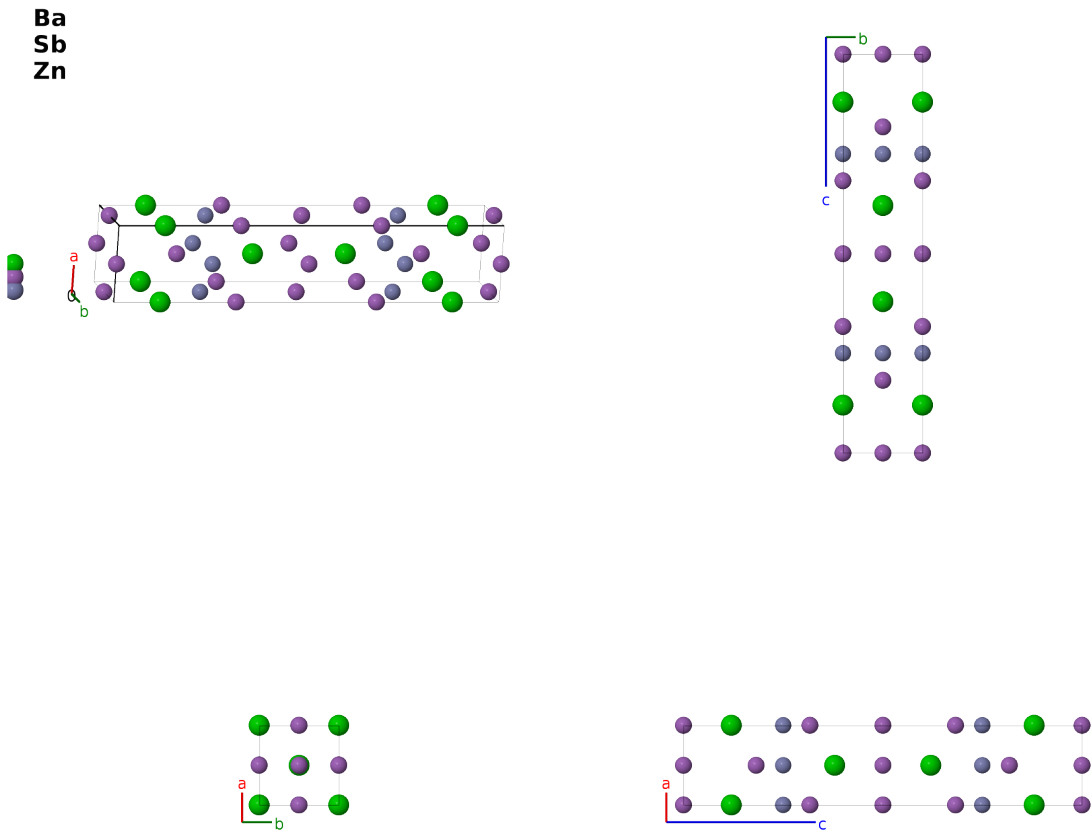

Prototype	BaSb ₂ Zn
AFLOW prototype label	AB2C_tI16_139_e_ce_d-003
ICSD	52694
CCDC	1617425
Pearson symbol	tI16
Space group number	139

Space group symbol $I4/mmm$

AFLOW prototype command `aflow --proto=AB2C_tI16_139_e_ce_d-003`
`--params=a, c/a, z3, z4`


Other compounds with this structure

BaCdBi₂, BaCdSb₂, BaMnSb₂, BaZnBi₂, SrCdBi₂, SrZnBi₂

- Many authorities designate SrZnBi₂ as the prototype for this structure.

Body-centered Tetragonal primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= -\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{\mathbf{x}} - \frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{2}c\hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{2}a\hat{\mathbf{y}} - \frac{1}{2}c\hat{\mathbf{z}}\end{aligned}$$

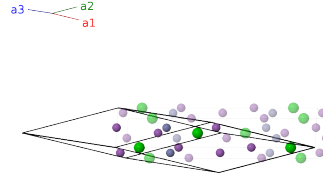

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	$= \frac{1}{2}\mathbf{a}_1 + \frac{1}{2}\mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{y}}$	(4c)	Sb I
$\mathbf{B}_2$	$= \frac{1}{2}\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{x}}$	(4c)	Sb I
$\mathbf{B}_3$	$= \frac{3}{4}\mathbf{a}_1 + \frac{1}{4}\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{y}} + \frac{1}{4}c\hat{\mathbf{z}}$	(4d)	Zn I
$\mathbf{B}_4$	$= \frac{1}{4}\mathbf{a}_1 + \frac{3}{4}\mathbf{a}_2 + \frac{1}{2}\mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{\mathbf{x}} + \frac{1}{4}c\hat{\mathbf{z}}$	(4d)	Zn I
$\mathbf{B}_5$	$= z_3\mathbf{a}_1 + z_3\mathbf{a}_2$	$=$	$cz_3\hat{\mathbf{z}}$	(4e)	Ba I
$\mathbf{B}_6$	$= -z_3\mathbf{a}_1 - z_3\mathbf{a}_2$	$=$	$-cz_3\hat{\mathbf{z}}$	(4e)	Ba I
$\mathbf{B}_7$	$= z_4\mathbf{a}_1 + z_4\mathbf{a}_2$	$=$	$cz_4\hat{\mathbf{z}}$	(4e)	Sb II
$\mathbf{B}_8$	$= -z_4\mathbf{a}_1 - z_4\mathbf{a}_2$	$=$	$-cz_4\hat{\mathbf{z}}$	(4e)	Sb II

References

- [1] E. Brechtel, G. Cordier, and H. Schäfer, *Neue ternäre erdalkali-übergangselement-pnictide*, J. Less-Common Met. **79**, 131–138 (1981), doi:10.1016/0022-5088(81)90057-6.

Found in

- [1] C. Yi, S. Yang, M. Yang, L. Wang, Y. Matsushita, S. Miao, Y. Jiao, J. Cheng, Y. Li, K. Yamaura, Y. Shi, and J. Luo, *Large negative magnetoresistance of a nearly Dirac material: Layered antimonide EuMnSb₂*, Phys. Rev. B **96**, 205103 (2017), doi:10.1103/PhysRevB.96.205103.

First cited in

H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettel, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.