

Ti₂C Structure:

AB2_cF48_227_c_e-001


This structure previously used the label(s) **AB2_cF48_227_c_e**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/PR5K>

https://aflow.org/prototype-encyclopedia/AB2_cF48_227_c_e-001

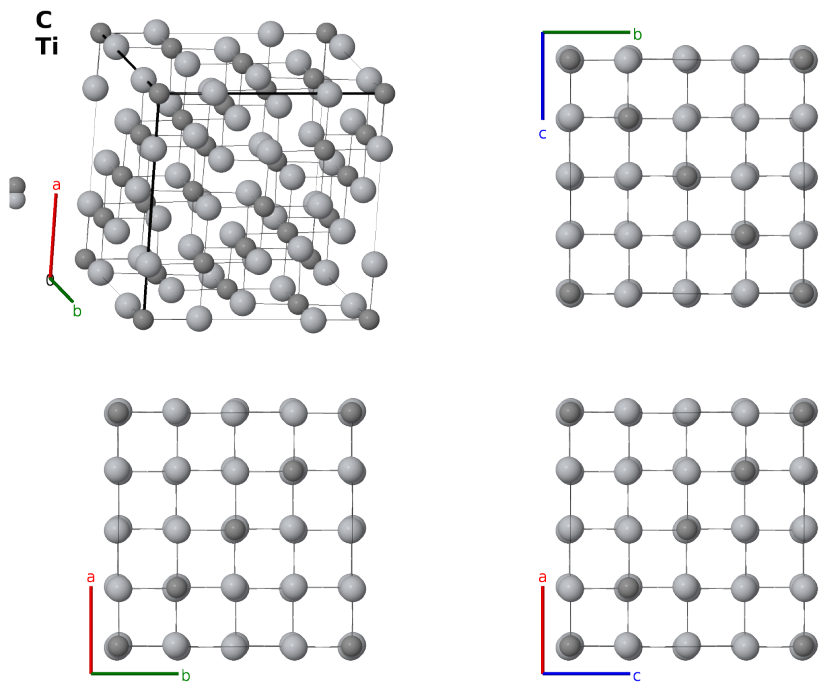

Prototype	CTi ₂
AFLOW prototype label	AB2_cF48_227_c_e-001
ICSD	77473
CCDC	1637900
Pearson symbol	cF48
Space group number	227
Space group symbol	$Fd\bar{3}m$
AFLOW prototype command	<code>aflow --proto=AB2_cF48_227_c_e-001</code> <code>--params=a, x₂</code>


Other compounds with this structure

Ca₃₃Ge, MnBr₂, SnS₂, TiS₂

- Some sources consider the real prototype of this system to be Ca_{33}Ge , with the (32e) sites occupied by calcium atoms and the (16c) sites randomly occupied by calcium and germanium atoms.

Face-centered Cubic primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a \hat{\mathbf{y}} + \frac{1}{2}a \hat{\mathbf{z}} \\ \mathbf{a}_2 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{z}} \\ \mathbf{a}_3 &= \frac{1}{2}a \hat{\mathbf{x}} + \frac{1}{2}a \hat{\mathbf{y}}\end{aligned}$$

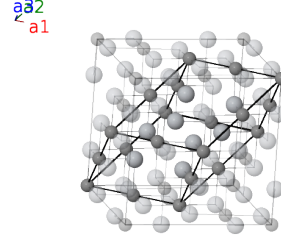

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	=	0	=	0	(16c) C I
$\mathbf{B}_2$	=	$\frac{1}{2} \mathbf{a}_3$	=	$\frac{1}{4}a \hat{\mathbf{x}} + \frac{1}{4}a \hat{\mathbf{y}}$	(16c) C I
$\mathbf{B}_3$	=	$\frac{1}{2} \mathbf{a}_2$	=	$\frac{1}{4}a \hat{\mathbf{x}} + \frac{1}{4}a \hat{\mathbf{z}}$	(16c) C I
$\mathbf{B}_4$	=	$\frac{1}{2} \mathbf{a}_1$	=	$\frac{1}{4}a \hat{\mathbf{y}} + \frac{1}{4}a \hat{\mathbf{z}}$	(16c) C I
$\mathbf{B}_5$	=	$x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 + x_2 \mathbf{a}_3$	=	$ax_2 \hat{\mathbf{x}} + ax_2 \hat{\mathbf{y}} + ax_2 \hat{\mathbf{z}}$	(32e) Ti I
$\mathbf{B}_6$	=	$x_2 \mathbf{a}_1 + x_2 \mathbf{a}_2 - (3x_2 - \frac{1}{2}) \mathbf{a}_3$	=	$-a(x_2 - \frac{1}{4}) \hat{\mathbf{x}} - a(x_2 - \frac{1}{4}) \hat{\mathbf{y}} + ax_2 \hat{\mathbf{z}}$	(32e) Ti I
$\mathbf{B}_7$	=	$x_2 \mathbf{a}_1 - (3x_2 - \frac{1}{2}) \mathbf{a}_2 + x_2 \mathbf{a}_3$	=	$-a(x_2 - \frac{1}{4}) \hat{\mathbf{x}} + ax_2 \hat{\mathbf{y}} - a(x_2 - \frac{1}{4}) \hat{\mathbf{z}}$	(32e) Ti I
$\mathbf{B}_8$	=	$-(3x_2 - \frac{1}{2}) \mathbf{a}_1 + x_2 \mathbf{a}_2 + x_2 \mathbf{a}_3$	=	$ax_2 \hat{\mathbf{x}} - a(x_2 - \frac{1}{4}) \hat{\mathbf{y}} - a(x_2 - \frac{1}{4}) \hat{\mathbf{z}}$	(32e) Ti I
$\mathbf{B}_9$	=	$-x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2 + (3x_2 + \frac{1}{2}) \mathbf{a}_3$	=	$a(x_2 + \frac{1}{4}) \hat{\mathbf{x}} + a(x_2 + \frac{1}{4}) \hat{\mathbf{y}} - ax_2 \hat{\mathbf{z}}$	(32e) Ti I
$\mathbf{B}_{10}$	=	$-x_2 \mathbf{a}_1 - x_2 \mathbf{a}_2 - x_2 \mathbf{a}_3$	=	$-ax_2 \hat{\mathbf{x}} - ax_2 \hat{\mathbf{y}} - ax_2 \hat{\mathbf{z}}$	(32e) Ti I
$\mathbf{B}_{11}$	=	$-x_2 \mathbf{a}_1 + (3x_2 + \frac{1}{2}) \mathbf{a}_2 - x_2 \mathbf{a}_3$	=	$a(x_2 + \frac{1}{4}) \hat{\mathbf{x}} - ax_2 \hat{\mathbf{y}} + a(x_2 + \frac{1}{4}) \hat{\mathbf{z}}$	(32e) Ti I
$\mathbf{B}_{12}$	=	$(3x_2 + \frac{1}{2}) \mathbf{a}_1 - x_2 \mathbf{a}_2 - x_2 \mathbf{a}_3$	=	$-ax_2 \hat{\mathbf{x}} + a(x_2 + \frac{1}{4}) \hat{\mathbf{y}} + a(x_2 + \frac{1}{4}) \hat{\mathbf{z}}$	(32e) Ti I

References

- [1] H. Goretzei, *Neutron Diffraction Studies on Titanium-Carbon and Zirconium-Carbon Alloys*, Phys. Stat. Solidi B **20**, K141–K143 (1967), doi:10.1002/pssb.19670200260.

Found in

- [1] P. Villars and L. Calvert, *Pearson's Handbook of Crystallographic Data for Intermetallic Phases* (ASM International, Materials Park, OH, 1991), 2nd edn.

First cited in

- M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017