

ω Phase (CdI_2 , $C6$) Structure: AB2_hP3_164_a_d-001


This structure previously used the label(s) **AB2_hP3_164_a_d**. Calls to these addresses will be redirected here.

Cite this page as:

- H. Eckert, S. Divilov, M. J. Mehl, D. Hicks, A. C. Zettl, M. Esters, X. Campilongo, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 4*, Comput. Mater. Sci. **240**, 112988 (2024), doi: 10.1016/j.commatsci.2024.112988.
- D. Hicks, M. J. Mehl, M. Esters, C. Oses, O. Levy, G. L. W. Hart, C. Toher, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 3*, Comput. Mater. Sci. **199**, 110450 (2021), doi: 10.1016/j.commatsci.2021.110450.

<https://aflow.org/prototype-encyclopedia/32EZ>

https://aflow.org/prototype-encyclopedia/AB2_hP3_164_a_d-001

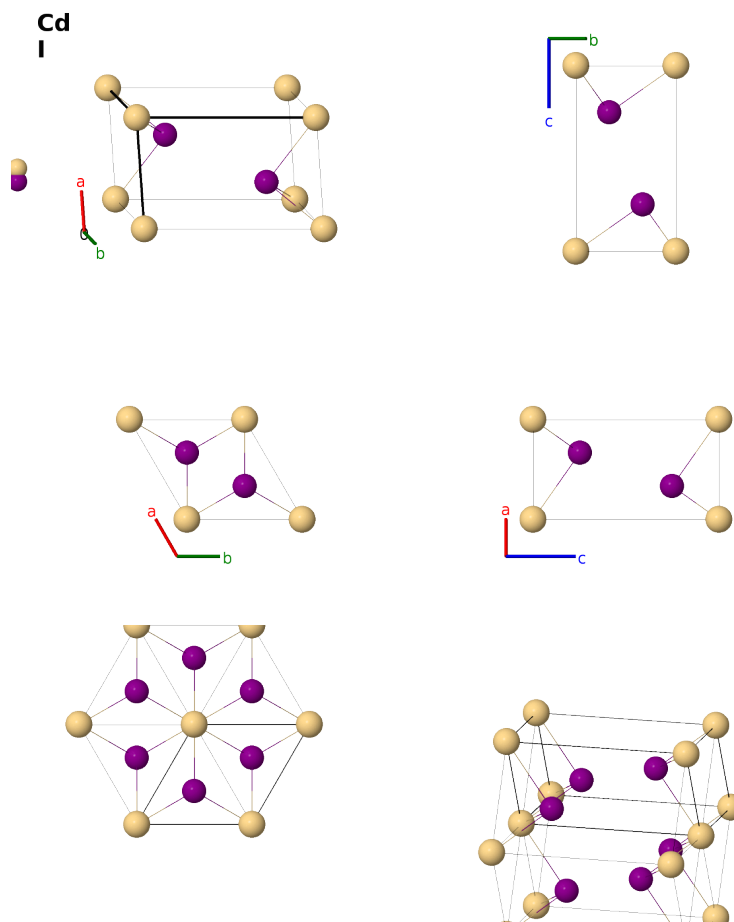

Prototype	CdI_2
AFLOW prototype label	AB2_hP3_164_a_d-001
<i>Strukturbericht</i> designation	$C6$
ICSD	53983
CCDC	1618603
Pearson symbol	hP3
Space group number	164

Space group symbol $P\bar{3}m1$

AFLOW prototype command `aflow --proto=AB2_hP3_164_a_d-001
--params=a,c/a,z2`

Other compounds with this structure

Ti, Zr, Hf, ZrNb, TiNb, TiV, CaI₂, Cd₂Ce, Cd₂La, Cd(OH)₂, Cd₂Pr, Cd₂Y, CdI₂, CoBr₂, CoI₂, CoO₂, CoTe₂, CrSe₂, EuGe₂, FeBr₂, FeCl₂ (HP), FeI₂, HfS₂, HfSe₂, HfTe₂, γ -HgI₂, IrTe₂, MgBr₂, MgCl₂, MgI₂, MnBr₂, MnI₂, Nb₂C, NbS₂, NbSe₂, NbTe₂, NiTe₂, PbI₂, PdTe₂, PtS₂, PtSe₂, RhTe₂, SiS₂, SiTe₂, SnS₂ (berndtite), SnS₂, SnSe₂, Ta₂C, TaS₂, TaSe₂, Ti₂O, TiBr₂, TiCl₂, TiS₂, TiSe₂, TiTe₂, TmI₂, V₂C, VBr₂, VCl₂, VI₂, VS₂, VSe₂, VTe₂, α -W₂C, YbI₂, ZnI₂, ZnTe₂, ZrS₂, ZrSe₂, ZrTe₂, BiTeBr, NiSeTe, PdSeTe, SSeSn, TiSeTe


- The ω phase can be either hexagonal ($C32$) or trigonal (shown here). The trigonal ω phase transforms into several high-symmetry structures under certain conditions:

c/a	z	Lattice
Arbitrary	$\frac{1}{2}$	Ideal Omega ($C32$)
$\sqrt{\frac{3}{8}}$	$\frac{1}{6}$	Body-Centered Cubic ($A2$)
$\sqrt{\frac{3}{2}}$	$\frac{1}{6}$	Simple Cubic (A_h)
$\sqrt{6}$	$\frac{1}{6}$	Face-Centered Cubic ($A1$)
Arbitrary	0	Simple Hexagonal Structure (A_f)

- For more details about the omega phase and materials which form in the omega phase, see (Sikka, 1982) . As noted there, most omega phase intermetallic alloys are disordered. Although the “ ω ” label comes from ω -CrTi, (Ewald, 1931) lists the prototype for *Strukturbericht* designation $C6$ as CdI₂.
- Alternative stackings for CdI₂ have been proposed, including a $6H$ stacking and the questionable $C27$ structure.

Trigonal (Hexagonal) primitive vectors

$$\begin{aligned}\mathbf{a}_1 &= \frac{1}{2}a\hat{x} - \frac{\sqrt{3}}{2}a\hat{y} \\ \mathbf{a}_2 &= \frac{1}{2}a\hat{x} + \frac{\sqrt{3}}{2}a\hat{y} \\ \mathbf{a}_3 &= c\hat{z}\end{aligned}$$

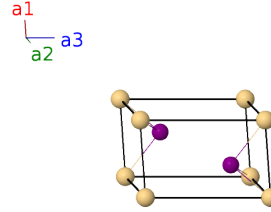

Basis vectors

	Lattice coordinates		Cartesian coordinates	Wyckoff position	Atom type
$\mathbf{B}_1$	0	$=$	0	(1a)	Cd I
$\mathbf{B}_2$	$\frac{1}{3}\mathbf{a}_1 + \frac{2}{3}\mathbf{a}_2 + z_2\mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{x} + \frac{\sqrt{3}}{6}a\hat{y} + cz_2\hat{z}$	(2d)	I I
$\mathbf{B}_3$	$\frac{2}{3}\mathbf{a}_1 + \frac{1}{3}\mathbf{a}_2 - z_2\mathbf{a}_3$	$=$	$\frac{1}{2}a\hat{x} - \frac{\sqrt{3}}{6}a\hat{y} - cz_2\hat{z}$	(2d)	I I

References

- [1] R. M. Bozorth, *The Crystal Structure of Cadmium Iodide*, J. Am. Chem. Soc. **44**, 2232–2236 (1922), doi:10.1021/ja01431a019.
- [2] S. K. Sikka, Y. K. Vohra, and R. Chidambaram, *Omega Phase in Materials*, Prog. Mater. Sci. **27**, 245–310 (1982), doi:10.1016/0079-6425(82)90002-0.

Found in

[1] P. P. Ewald and C. Hermann, eds., *Strukturbericht 1913-1928* (Akademische Verlagsgesellschaft M. B. H., Leipzig, 1931).

First cited in

M. J. Mehl, D. Hicks, C. Toher, O. Levy, R. M. Hanson, G. L. W. Hart, and S. Curtarolo, *The AFLOW Library of Crystallographic Prototypes: Part 1*, Comput. Mater. Sci. **136**, S1-828 (2017). doi: 10.1016/j.commatsci.2017.01.017